

FCT Quality Assurance Program Document

Appendix E FCT Document Cover Sheet

Name/Title of Deliverable/Milestone Complete iodine loading of NO-aged silver-functionalized silica aerogel
Work Package Title and Number Sigma Team – Off-Gas – ORNL FT-15OR031202
Work Package WBS Number 1.02.03.12 Milestone Number M3FT-15OR03120211

Responsible Work Package Manager

Bob Jubin

(Name/Signature)

05/29/15

(Date Submitted)

Quality Rigor Level for Deliverable/Milestone	<input checked="" type="checkbox"/> QRL-3	<input type="checkbox"/> QRL-2	<input type="checkbox"/> QRL-1 <input type="checkbox"/> Nuclear Data	<input type="checkbox"/> N/A*
---	---	--------------------------------	---	-------------------------------

This deliverable was prepared in accordance with

R. T. Jubin/ORNL

(Participant/National Laboratory Name)

QA program which meets the requirements of

☐ DOE Order 414.1

☒ NQA-1-2008

☐ Other: _____

This Deliverable was subjected to:

☒ Technical Review

☐ Peer Review

Technical Review (TR)

Review Documentation Provided

☐ Signed TR Report, or

TR Report No.: _____

☐ Signed TR Concurrence Sheet (attached), or

☐ Signature of TR Reviewer(s) below

Peer Review (PR)

Review Documentation Provided

☐ Signed PR Report, or

PR Report No.: _____

☐ Signed PR Concurrence Sheet (attached), or

☐ Signature of PR Reviewers below

Name and Signature of Reviewers

Electronic record attached

(Name/Signature)

(Date)

*Note: In some cases there may be a milestone where an item is being fabricated, maintenance is being performed on a facility, or a document is being issued through a formal document control process where it specifically calls out a formal review of the document. In these cases, documentation (e.g., inspection report, maintenance request, work planning package documentation, or the documented review of the issued document through the document control process) of the completion of the activity along with the Document Cover Sheet is sufficient to demonstrate achieving the milestone. QRL for such milestones may also be marked N/A in the work package provided the work package clearly specifies the requirement to use the Document Cover Sheet and provide supporting documentation.



View Record

Search

[Advanced Search](#)

Close

[Edit Item](#) | [Change Communication Type](#) | [Delete Item](#)

Pub ID	55925				
Title	Milestone Report - M3FT-15OR03120211 - Complete Iodine Loading of NO Aged Ag0-functionalized Aerogel				
Status	Submitted for review				
Communication Type	Letter report				
ORNL Review?	Scientific communication that requires ORNL review				
Information Category	Unlimited				
Contact Person	Bruffey, Stephanie H				
Responsible Organization	Nuclear Security & Isotope Technology (50303801)				
Prepared at	This scientific communication is being prepared by someone at ORNL.				
Internal Access	Available to the internal PTS users at ORNL.				
Authors	Bruffey, Stephanie H. Patton, Kaara K. Jubin, Robert Thomas	ORNL (971936) ORNL (946958) ORNL (18682)			
Acknowledgements					
Workflow	05/22/2015 09:42:01	Draft	Bruffey, Stephanie H		
	05/22/2015 09:42:02	Author Certification	Bruffey, Stephanie H		
	05/22/2015 09:42:02	Submitted for review	Bruffey, Stephanie H		
	05/22/2015 09:49:25	Supervisor	Birdwell Jr, Joseph F by Johnson, Brenda Jeffers	Approved	
	05/27/2015 10:20:08	Derivative Classifier	Begovich, John M	Cleared	
	05/27/2015 12:25:17	Technical Reviewer	Collins, Robert T	Recommended	
	05/27/2015 16:30:47	Technical Reviewer	Huckabay, Heath A	Recommended	
	05/28/2015 07:57:48	Proliferation Sensitive Review	Phillips Jr, Leonard P by Holt, Jerrid S	Approved	
	05/28/2015 10:17:05	Export Control	Migun, Rolf P by Howard, Sam C	Cleared	
	05/28/2015 12:55:47	Technical Editor	Stevens, Deborah P	Recommended	
	05/28/2015 13:22:19	Administrative Check	Johnson, Brenda Jeffers	Recommended	
	05/28/2015 13:48:38	Supervisor	Birdwell Jr, Joseph F	Approved	
	05/29/2015 08:29:05	Information Classification	Poe, Christopher D by Kyle, John S	Cleared	
	05/29/2015 14:03:59	Division Approver	Parks, Cecil V by Rowley, Kathy D	Approved	
		Waiting on the following review(s)			
		Technical Information Officer	Laymance, Leesa K		
		Distributed	Bruffey, Stephanie H		
	View Comments from Reviewers				
Requested Approval Date	May 29, 2015				
Internal Document	edited_M3FT-15OR03120211 NO aging of aerogels - rev 1b.docx				
Abstract					
Report Number	ORNL/LTR-2015/258				
Secondary ID Number					
Additional Information					
User Facility	Not applicable				
Account Number(s)	31075016				
B&R Codes	AF5805010				
IANs					
FWPs	NEAF327				
Overhead Categories					
Proposal Numbers					
Keywords	aerogel, iodine, aging				

Close

Complete Iodine Loading of NO-Aged Ag⁰-Functionalized Silica Aerogel

Fuel Cycle Research & Development

*Prepared for
U.S. Department of Energy
Materials Recovery and Waste Form
Development Campaign
S. H. Bruffey, K. K. Patton,
and R. T. Jubin*

Oak Ridge National Laboratory

May 29, 2015

FCRD-MRWFD-2015-000419

ORNL/SPR-2015/258



DOCUMENT AVAILABILITY

Reports produced after January 1, 1996, are generally available free via US Department of Energy (DOE) SciTech Connect.

Website <http://www.osti.gov/scitech/>

Reports produced before January 1, 1996, may be purchased by members of the public from the following source:

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
Telephone 703-605-6000 (1-800-553-6847)
TDD 703-487-4639
Fax 703-605-6900
E-mail info@ntis.gov
Website <http://www.ntis.gov/help/ordermethods.aspx>

Reports are available to DOE employees, DOE contractors, Energy Technology Data Exchange representatives, and International Nuclear Information System representatives from the following source:

Office of Scientific and Technical Information
PO Box 62
Oak Ridge, TN 37831
Telephone 865-576-8401
Fax 865-576-5728
E-mail reports@osti.gov
Website <http://www.osti.gov/contact.html>

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

SUMMARY

In off-gas treatment systems within a nuclear fuel reprocessing plant, capture materials will be exposed to a gas stream for extended periods during their lifetime. This gas stream may be at elevated temperature and could contain water, NO_x gas, or a variety of other constituents. For this reason, it is important to understand the effects of long-term exposure, or aging, on proposed capture materials. One material under consideration for iodine sequestration is silver-functionalized silica aerogel (Ag⁰-aerogel). The aim of this study was to determine the effect of extended exposure at 150°C to an air stream containing NO on the iodine capture capacity of Ag⁰-aerogel.

Ag⁰-aerogel was provided by the Pacific Northwest National Laboratory (PNNL), which manufactures the material at a lab scale. Prior to aging, the material has an iodine loading capacity of approximately 290 mg I/g Ag⁰-aerogel. Previous studies have aged the material in a dry air stream or in a moist air stream for up to 6 months. Both tests resulted in a 22% loss in iodine capacity.^{1,2} Aging the material in a static 2% NO₂ environment for up to 2 months results in a 15% loss of iodine capacity.³ In this study, exposure of Ag⁰-aerogel to 1% NO at 150°C for 2 months produced a loss of 43% in iodine loading capacity. This is largest loss observed for aerogel aging studies to date.

The performance of Ag⁰-aerogel in this study was compared to the performance of reduced silver mordenite (Ag⁰Z) in similar studies. Ag⁰Z is a zeolite mineral considered to be the current standard technology for iodine removal from off-gas streams of a potential US used fuel processing plant. In an aging study exposing Ag⁰Z to 1% NO for 2 months, an iodine capacity loss of over 80% was observed.³ This corresponds to a silver utilization of 13.5% for 2 month NO-aged Ag⁰Z, compared to 57% silver utilization for 2 month NO-aged aerogel. While iodine loading capacity and silver utilization are critical parameters in evaluating these materials, other properties must also be considered when selecting the appropriate material (e.g., relative material densities and potential waste form production technology). The resistance of Ag⁰-aerogel to NO is promising, and investigations of this material for use in iodine capture should continue to be pursued.

CONTENTS

SUMMARY	iii
FIGURES	v
TABLES	v
ACRONYMS	vi
1. INTRODUCTION	1
2. MATERIALS AND METHODS	1
3. TESTING RESULTS	2
4. DISCUSSION	3
5. REFERENCES	4

FIGURES

Figure 1. Effects of NO aging on Ag ⁰ -aerogel (L to R: 0 month, 1 week, and 1 month aged Ag ⁰ -aerogel).....	2
Figure 2. Effect of NO aging on I ₂ adsorption by Ag ⁰ -aerogel.....	3

TABLES

Table 1. Effects of aging environment on the iodine capacity of Ag ⁰ -aerogel ^{1,2}	1
Table 2. Iodine loading capacities for NO-aged Ag ⁰ -aerogel.	3

ACRONYMS

Ag ⁰ -aerogel	Silver-functionalized silica aerogel
Ag ⁰ Z	Reduced silver-exchanged mordenite
PNNL	Pacific Northwest National Laboratory

MATERIAL RECOVERY AND WASTE FORM DEVELOPMENT CAMPAIGN

COMPLETE IODINE LOADING OF NO-AGED Ag⁰-FUNCTIONALIZED SILICA AEROGEL

1. INTRODUCTION

In an off-gas system within a nuclear fuel reprocessing plant, any capture material will be exposed to a gas stream for months at a time. This gas stream may be at elevated temperature and could contain water, NO_x gas, or a variety of other constituents. For this reason, it is important to understand the effects of long-term exposure, or aging, on proposed capture materials. One material under consideration is silver-functionalized silica aerogel (Ag⁰-aerogel), currently being produced in bench-scale quantities by collaborators at Pacific Northwest National Laboratory (PNNL).

Previous studies have examined the effects of extended aging at 150°C under a dry air stream, a humid air stream, and a static NO₂ environment on the iodine capture capacity of Ag⁰-aerogel.^{1,2} The loss in iodine capacity due to aging in each environment is shown in Table 1. The aim of this study was to determine the effects of extended exposure at 150°C to an air stream containing NO on the iodine capture capacity of Ag⁰-aerogel. The results of this aging study in concert with other previously completed studies will provide insight into the ability of Ag⁰-aerogel to withstand exposure to corrosive off-gas streams.

Table 1. Effects of aging environment on the iodine capacity of Ag⁰-aerogel.^{1,2}

Aging environment	Aging time (months)	Capacity loss (%)
Flowing dry air; 150°C	6	22
Flowing humid air; 150°C	6	22
Static 2% NO ₂ ; 150°C	2	15

2. MATERIALS AND METHODS

Ag⁰-aerogel was provided by PNNL in FY 2015. It is a granular, friable material with a particle size of <0.85 μm. The particles are black with brown and tan areas (Figure 1).

The aging study was conducted in a deep-bed test system. A 20.4 g charge of Ag⁰-aerogel was contained in a stainless steel tube (I.D. 1.87 in.) located in a tube furnace. The furnace was held at 150°C for the duration of the study. A dry air stream (dew point < -70°C) was mixed with 100% NO gas in ¼ in. stainless steel tubing approximately 12 in. prior to entering the tube furnace. There was a second gap of approximately 12 in. in length between the bottom of the tube furnace and the sample bed; this was to ensure that the gas was fully heated prior to encountering Ag⁰-aerogel and that the sample charge was fully located in the heating zone of the furnace. Thermocouples were placed in this heating zone, in the

sample bed, and at the tube exit to monitor the gas and sample temperatures. The gas velocity through the tube was 3.5 m/min.

At selected intervals of 1 week, 1 month, and 2 months, the flow was suspended and the oven cooled. The material was removed from the tube and gently mixed to ensure homogeneity; a ≈ 5 g sample was subsequently removed, and the remainder of the material was returned to the tube for continued aging. After the aging test was complete, the 1 and 2 month samples were loaded with 50 ppm iodine from a dry feed stream ($< -70^{\circ}\text{C}$ dew point) in a thermogravimetric analyzer, described in detail in a previous report.⁴ The gas velocity for iodine loading was 10 m/min, and the temperature was held at 150°C . The iodine loading for each sample was determined by sample weight upon conclusion of iodine loading.

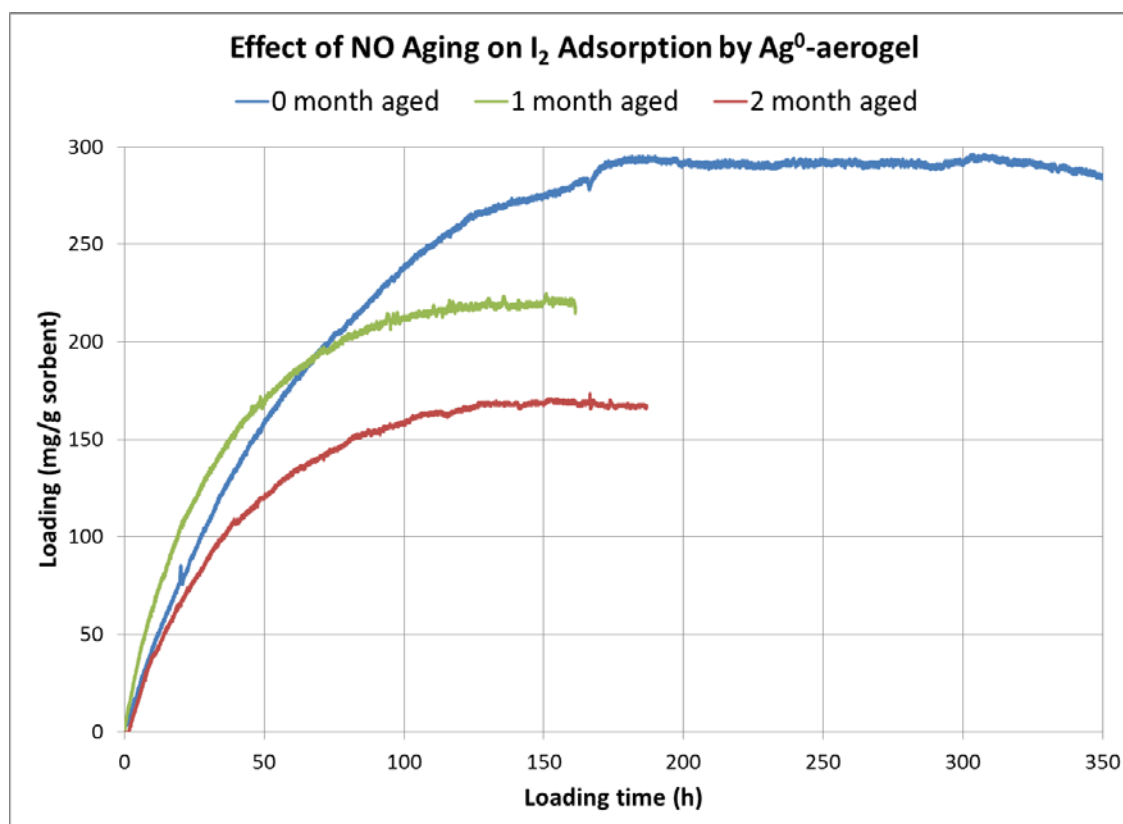
3. TESTING RESULTS

Exposure to 1% NO gas significantly affected the structure and appearance of the aerogel. As shown in Figure 1, an initial change in material color was observed after 1 week of aging. The black granules did not change color, but the lighter colored granules turned bright orange and red. After 1 month of aging, a substantial amount of fines had developed and the material was mostly dark brown with orange, white, yellow, and red granules dispersed throughout. The material was sieved through a 30×30 mesh, and the fines were found to constitute 30% by weight of the material remaining in the tube after the 1 week sample was removed. The fines were not returned to the tube furnace for continued aging. No additional change in color was observed upon 2 months of aging, and no significant amount of additional fines was created during the second month of aging.



Figure 1. Effects of NO aging on Ag⁰-aerogel (L to R: 0 month, 1 week, and 1 month aged Ag⁰-aerogel).

Iodine loading curves for 0, 1, and 2 month aged samples are shown in Figure 2, and the total iodine capacity for each is shown in Table 2. A loss of 24% iodine capacity was observed within the first month of aging, and after 2 months, the total capacity loss increases to 43%.

Figure 2. Effect of NO aging on I₂ adsorption by Ag⁰-aerogel.Table 2. Iodine loading capacities for NO-aged Ag⁰-aerogel.

Aging time (months)	Iodine loading capacity (mg I/g Ag ⁰ -aerogel)	Decrease in Iodine Capacity (%)
0	290	-
1	220	24
2	165	43

4. DISCUSSION

In this study, exposure of Ag⁰-aerogel to 1% NO at 150°C for 2 months produced a loss of 43% in iodine loading capacity. This is largest loss observed for aerogel aging studies to date. The performance of Ag⁰-aerogel in this study was compared to the performance of reduced silver mordenite (Ag⁰Z) in similar studies.⁵ Ag⁰Z is a zeolite mineral considered to be the current standard technology for iodine removal from the off-gas streams of a potential US used fuel processing plant. In an aging study exposing Ag⁰Z to 1% NO for 2 months, an iodine capacity loss of over 80% was observed. This corresponds to a silver utilization of 13.5% for 2 month NO-aged Ag⁰Z, compared to 57% silver utilization for 2 month NO-aged aerogel. While iodine loading capacity and silver utilization are critical parameters in evaluating these materials, other properties must also be considered when selecting the appropriate material. The density

of these two materials is significantly different (Ag⁰Z, 0.77 g/cm³; Ag⁰-aerogel, 0.35 g/cm³) and is an important factor in plant design. Additionally, the potential waste forms that might be appropriate for final disposition of either material are still under investigation and will guide the selection of a sorbent that is ultimately required to be treated as high-level waste. However, the results of this study demonstrate that the resistance of Ag⁰-aerogel to NO is promising, and both fundamental and applied investigations of this material for use in iodine capture should continue to be pursued.

5. REFERENCES

1. S. H. Bruffey et al., *Humid Aging and Iodine Loading of Silver-functionalized Aerogels*, FCR&D-SWF-2013-000258, US Department of Energy Separations and Waste Forms Campaign, August 2013.
2. S. H. Bruffey et al., *Aging and Iodine Loading of Silver-functionalized Aerogels*, FCRD-SWF-2012-000256, US Department of Energy Separations and Waste Forms Campaign, 31 August 2012.
3. S. H. Bruffey, personal communication with R.T. Jubin, Oak Ridge National Laboratory, 2014.
4. R. T. Jubin, *Report of the FY11 Activities of the Off-Gas Sigma Team*, FCR&D-SWF-2011-000306, US Department of Energy Separations and Waste Forms Campaign, September 2011.
5. S. H. Bruffey et al., *Complete NO and NO₂ Aging Study for AgZ*, FCRD-MRWFD-2015-000631, US Department of Energy Material Recovery and Waste Form Development Campaign, March 2015.