

Low-temperature synthesis of a green material for lithium-ion batteries cathode

Aliyar Mousavi , Azzedine Bensalem & Becky Gee

To cite this article: Aliyar Mousavi , Azzedine Bensalem & Becky Gee (2010) Low-temperature synthesis of a green material for lithium-ion batteries cathode, Green Chemistry Letters and Reviews, 3:2, 135-142, DOI: [10.1080/17518251003619184](https://doi.org/10.1080/17518251003619184)

To link to this article: <https://doi.org/10.1080/17518251003619184>



Copyright Taylor and Francis Group, LLC



Published online: 30 Jul 2010.



Submit your article to this journal [↗](#)



Article views: 662



View related articles [↗](#)



Citing articles: 3 View citing articles [↗](#)

RESEARCH LETTER

Low-temperature synthesis of a green material for lithium-ion batteries cathode

Aliyar Mousavi, Azzedine Bensalem* and Becky Gee

Department of Chemistry and Biochemistry, Long Island University (Brooklyn Campus), Brooklyn, NY 11201, USA

(Received 31 July 2009; final version received 13 January 2010)

Battery technology is an important anthropogenic source of the heavy metals which are highly threatening to human health. A category of rechargeable lithium batteries that is of great interest is the set of batteries where the cathode material is a lithium iron phosphate (LiFePO_4). LiFePO_4 is an environmentally friendly and safe lithium-ion battery cathode material, but it has a key limitation, and that is its extremely low-electronic conductivity, a problem that can be greatly overcome by zinc-doping LiFePO_4 . For the first time to our knowledge, a low-temperature method, that is advantageous both economically and technologically, for the synthesis of a zinc-doped LiFePO_4 is presented. Since the method appears to be applicable for synthesizing various zinc-doped LiFePO_4 compounds with the general formula $\text{LiFe}_{1-x}\text{Zn}_x\text{PO}_4$ ($0 < x < 1$), it is very promising for the production of a green cathode material for lithium-ion batteries.

Keywords: green; rechargeable lithium batteries; lithium zinc iron phosphate; cathode; synthesis

Introduction

The main threats to human health from heavy metals are associated with exposure to lead, cadmium, and mercury (1). Rechargeable nickel–cadmium batteries are where cadmium compounds are currently mainly used (1), lead-acid cells are a main family of batteries (2), and some small batteries represent potential sources of mercury (3). It is, therefore, appropriate to say that battery technology has been in need of improvement as for environmental friendliness and safety.

Lithium-ion batteries were introduced by the Sony Corporation in the early 1990s (4). They are of great technological importance because of their usage in personal electronic devices, such as cellular phones, notebook computers, laptops, and high-end desktop computers. Also, advanced rechargeable lithium batteries have, in principle, the capability of satisfying all of the performance requirements of an electric vehicle (5). A category of rechargeable lithium batteries that is of great interest is the set of batteries where the cathode material is a lithium iron phosphate (LiFePO_4) (6). LiFePO_4 is an environmentally friendly and safe (6). It has a high-lithium intercalation voltage (~ 3.5 V relative to lithium metal), high-theoretical capacity (170 mA h g^{-1}), low raw materials cost, and stability when used with common electrolyte systems (6). Yet, it also has a key limitation, and that is its extremely low-electronic conductivity (6). A feasible way to enhance


the intrinsic conductivity is doping alien cations of elements such as Mn, Mg, Ti, and Zr (7). Zinc is the most electronegative transition metal in nature, and zinc-doping LiFePO_4 , therefore, can improve the electronic conductivity of LiFePO_4 most greatly. Experimental studies on electrochemical behavior of zinc-doped LiFePO_4 for lithium battery positive electrode have shown not only that zinc-doping can increase the conductivity of LiFePO_4 , but also that the conductivity of zinc-doped LiFePO_4 varies with Zn:Fe ratio (8).

Lithium battery cathode materials are often synthesized by using “solid-state” synthetic methods. In this synthetic path, exact stoichiometric amounts of starting materials are well mixed, ground, and then left to react at high temperatures. Although the compounds of interest are achieved, two main problems stay unsolved. First of all, the solid-state synthesis is often costly, due especially to the required high heat. As for the other problem, due to large particle size, the surface areas of the compounds obtained by using the solid-state synthesis are relatively small. The alternative method used for the synthesis of lithium battery cathode materials is a set of “wet” synthetic methods. This is a low-temperature synthetic method. In wet methods, the precursors react in solutions. Since the problem of very high temperatures does not exist in this synthetic path, it is much more economically feasible. Also, the products have larger surface areas compared to those of the solid-state methods.

*Corresponding author. Email: azzedine.bensalem@liu.edu

LiFePO_4 has originally been synthesized using the solid-state path by heating lithium carbonate (Li_2CO_3), ammonium dihydrogenphosphate ($\text{NH}_4\text{H}_2\text{PO}_4$), and

past as a starting material for high-temperature synthesis of both LiFePO_4 (9) and zinc-doped LiFePO_4 (10). The proposed reaction is as follows:



iron oxalate dihydrate ($\text{FeC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$) in nitrogen or argon gas at 600–850°C (6). Using the same sources for lithium, phosphate, and iron, and using zinc oxide (ZnO) as the source for zinc, a zinc-doped LiFePO_4 material has also been prepared by a solid-state route by Liu et al. (7). Iron (II) sulfate has been used in the

Results and discussion

X-ray diffraction analysis

The X-ray powder diffraction analysis of the zinc-doped product showed that the prepared sample was amorphous. In order to make the compound crystalline,

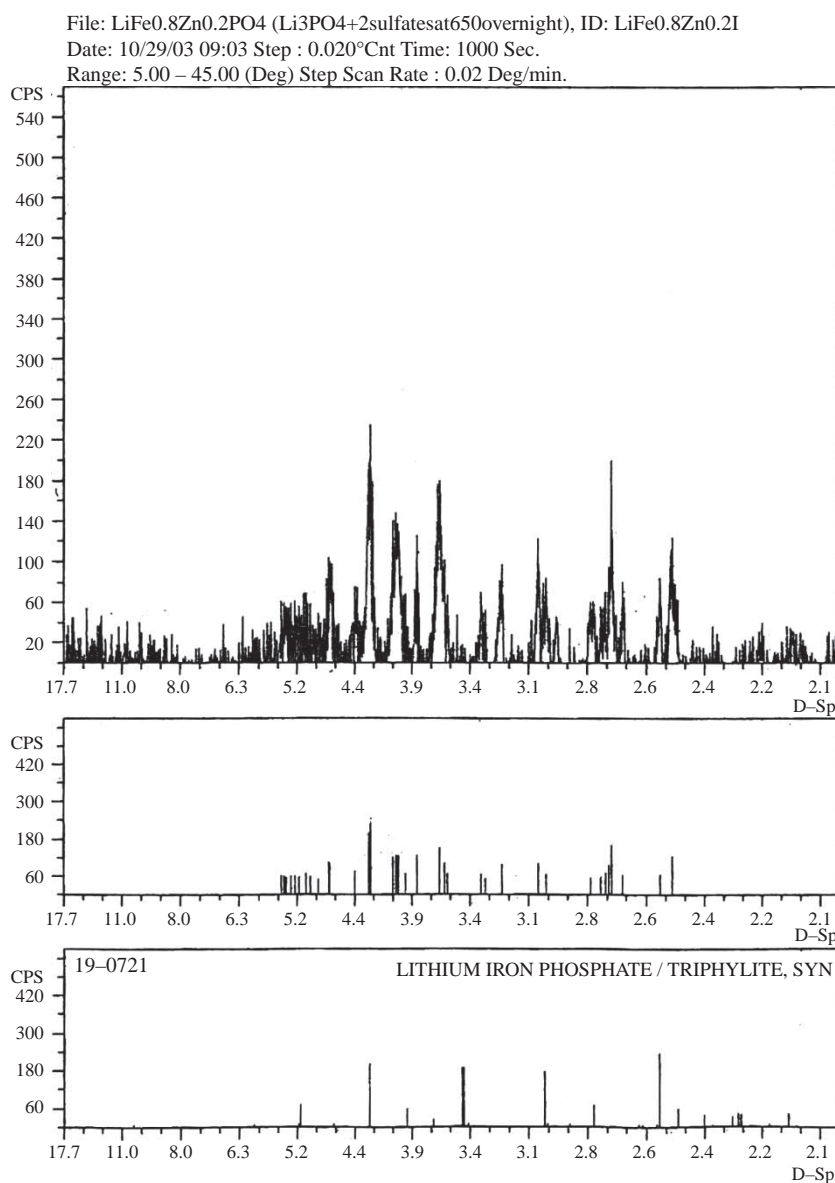


Figure 1. X-ray pattern of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ (versus LiFePO_4).

the prepared sample was heated to higher temperatures. The sample showed meaningful crystallinity only after being heated at 650°C for 24 hours (Figure 1) (11). The X-ray powder pattern showed that the crystalline phase is isostructural with LiFePO_4 . It also shows some extra diffraction peaks that we were able to assign to some Li_2SO_4 impurities (Figure 2). Table 1 lists the interplanar spacings of our product versus those of LiFePO_4 (12) and Li_2SO_4 (13).

Fourier Transform Infrared (FTIR) spectroscopy

In order to confirm the results of the X-ray powder diffraction analysis, Fourier Transform Infrared

(FTIR) spectra of both the sample heated to 110°C for three hours and the one heated to 650°C were obtained (Figures 3 and 4). Both spectra show a wide peak between 1000 and 1100 cm^{-1} . That peak corresponds to vibrations due to PO_4^{3-} ions (14). However, a sharper peak is found in both spectra at 1100 cm^{-1} exactly. That peak corresponds to vibrations due to SO_4^{2-} ions (14). However, a sharper peak is found in both spectra at 1100 cm^{-1} exactly. The peaks observed at 1600 and 3500 cm^{-1} are both due to vibrations in water molecules (14). This is water adsorbed by the prepared sample due to exposure of the sample to the atmosphere.

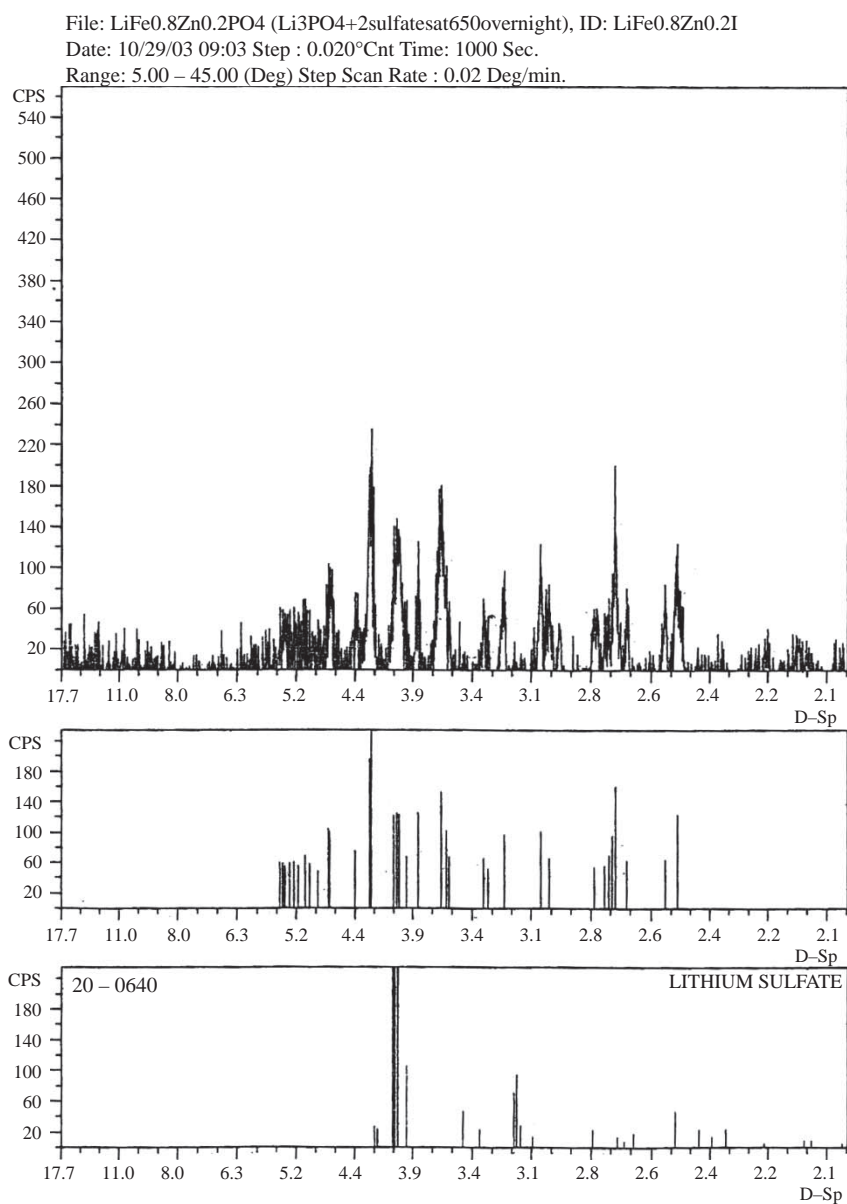


Figure 2. X-ray pattern of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ (versus Li_2SO_4).

Table 1. The interplanar spacings of our product versus those of LiFePO_4 and Li_2SO_4 .

$d_{\text{our product}}$	d_{LiFePO_4}	$d_{\text{Li}_2\text{SO}_4}$
4.6861	4.6900	
4.2329	4.2700	
3.9974		3.9990
3.9242	3.9100	
3.6243	3.6900	
3.5561	3.4800	
3.3313		3.3820
3.2186		3.1770
3.0234		3.0740
3.0142	3.0000	
2.9770	2.9990	
2.9241	2.8790	
2.7659	2.7720	
2.6895		2.6910
2.6868		2.6910
2.6361		2.6280
2.5067	2.5160	
2.4506	2.4530	

TGA and DTA analysis

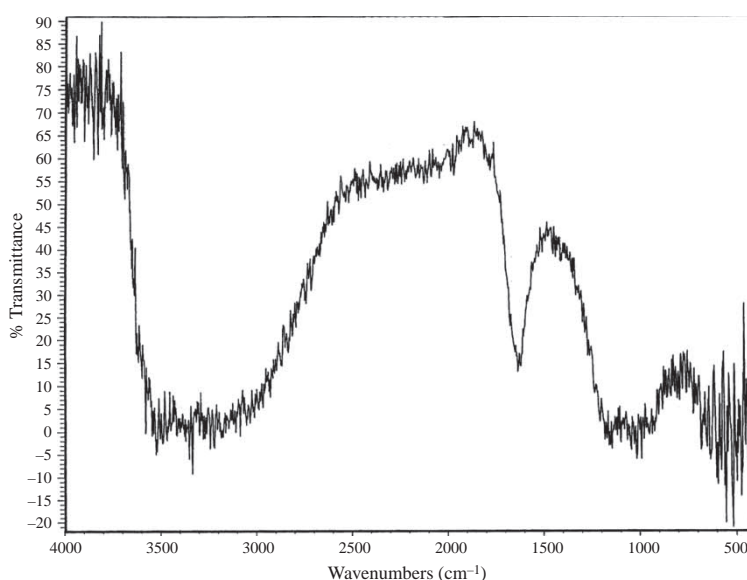
In order to check if the original product is the same as the one available after being heated at 650°C , Thermogravimetric Analyzer (TGA) along with Differential Thermal Analyzer (DTA) were used. The thermal gravimetric diagram shows only one weight loss that starts at about 80°C (Figure 5). This weight loss is due to the endothermic thermal event observed by differential thermal analysis (Figure 6). This event is attributed to the loss of water. This is well shown by FTIR Spectroscopy where vibrations peaks due to

water molecules are greatly diminished when the sample is heated to 650°C . The change is a decrease in mass during the temperature increase of the sample (from 75 to 125°C). The differential thermal diagram shows one endothermic peak in that temperature range. That peak indicates the loss of water. The DTA also shows an exothermic peak at around 540°C (Figure 6). The X-ray powder diffraction results show that this exothermic peak corresponds to the process of the crystallization of our product.

Lithium-7 solid-state nuclear magnetic resonance (NMR) spectroscopy

The Li-7 Magic Angle Spinning Nuclear Magnetic Resonance (MAS-NMR) spectrum of undoped LiFePO_4 is available in the literature (15). The Li-7 MAS-NMR spectra of our doped product were obtained and compared with the literature results (Figures 7 and 8).

In each spectrum, the Li-7 magnetic resonance shift was found at -0.982 ppm relative to 0.01 M LiCl (aq). Figures 7 and 8 show the Li-7 MAS-NMR spectra obtained at two different spinning frequencies in order to differentiate between spinning sidebands, due to the inability to average-out all anisotropic interactions, and the Li-7 resonance shift. The Li-7 magnetic resonance shift in Figures 7 and 8 is in agreement with the literature. It is noteworthy that the Li-7 NMR signal for Li_2SO_4 appears at about 0 ppm relatively to 0.01 M LiCl (aq). Therefore, it is not possible at ambient temperature to distinguish the Li_2SO_4 impurity in the solid-state NMR spectrum from the material of interest.

Figure 3. FTIR spectrum of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ (heated at 110°C).

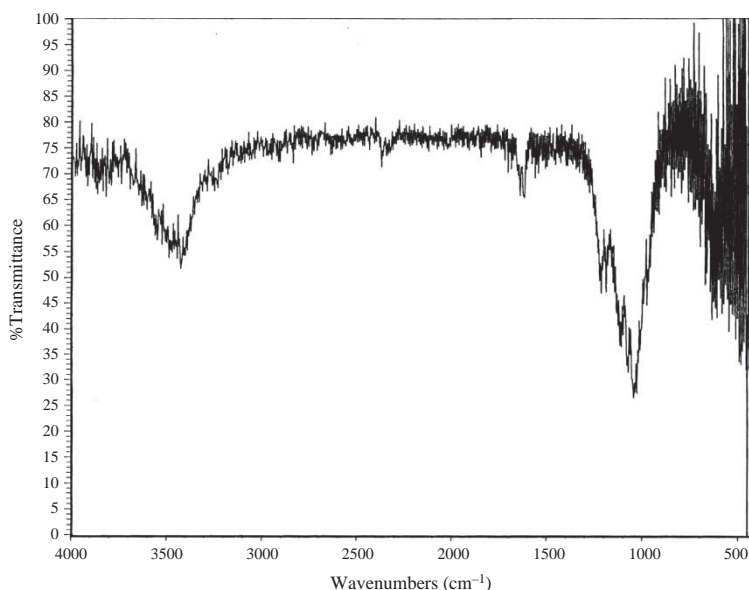


Figure 4. FTIR spectrum of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ (heated at 650°C).

Elemental analysis

Another characterization technique that confirms the formation of a zinc-doped LiFePO_4 material, as well as the coexistence of some lithium sulfate in our product, is elemental analysis. The technique was applied for both the original product (i.e. the one obtained at 110°C), as well as the one heated at 650°C . The results of the analysis are listed in Table 2. The data in Table 2 along with the fact that the molar ratio of iron to zinc in the desired product is $1-x$ to x lead us to the composition results listed below:

Sample 110°C $\text{Li}_{1.52}\text{Fe}_{0.842}\text{Zn}_{0.160}\text{P}_{0.942}$

Sample 650°C $\text{Li}_{1.70}\text{Fe}_{0.833}\text{Zn}_{0.165}\text{P}_{1.09}$.

Expressing the subscripts by one significant figure, the elemental composition of the analyzed material for Li, Fe, Zn, and P is $\text{Li}_2\text{Fe}_{0.8}\text{Zn}_{0.2}\text{P}$. The subscripts of 0.8, 0.2, and 1 for Fe, Zn, and P are numerically equal to the molar ratios of the starting materials $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$, $\text{ZnSO}_4 \cdot 6\text{H}_2\text{O}$, and lithium phosphate (Li_3PO_4), which were also expressed by

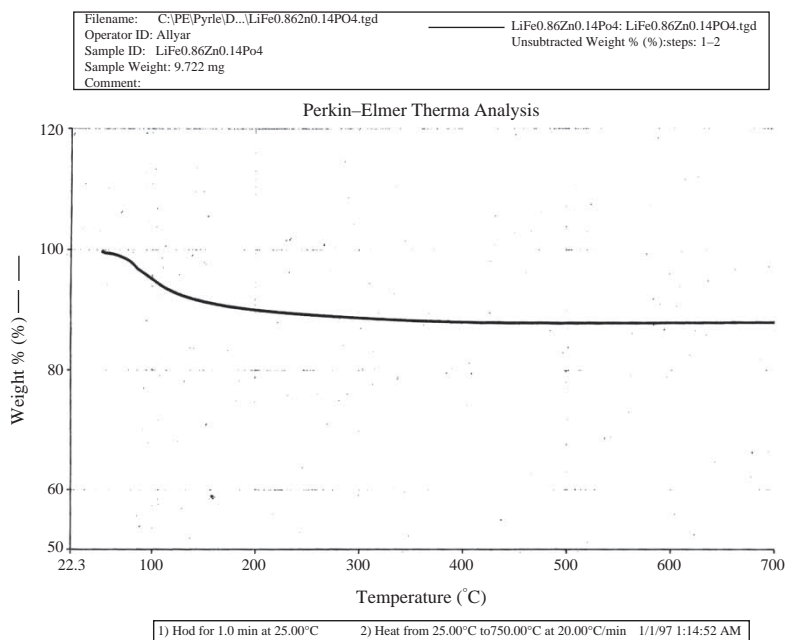
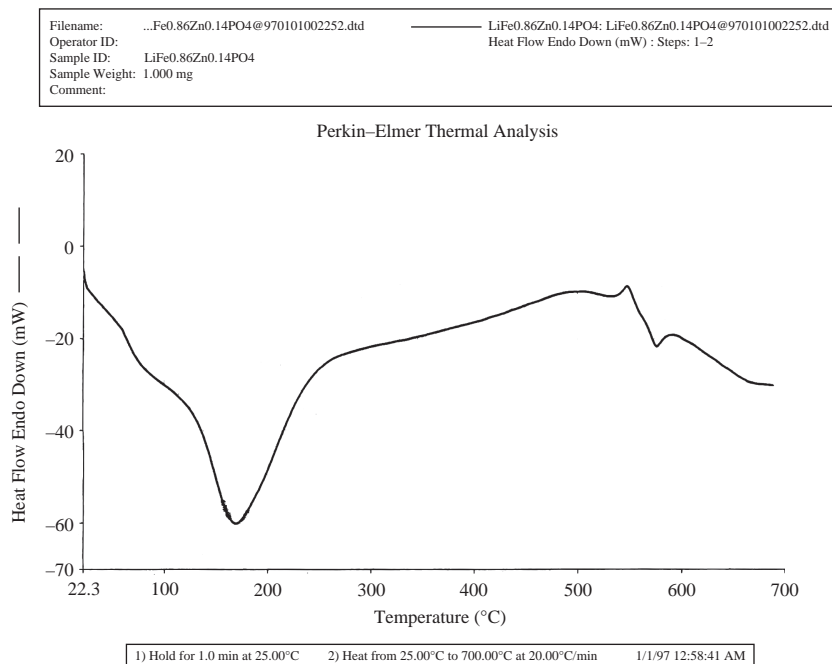


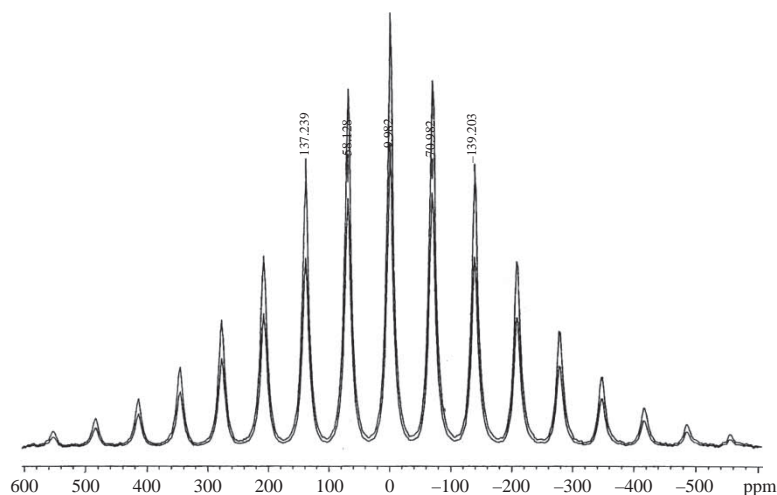
Figure 5. TGA diagram of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$.

Figure 6. DTA diagram of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$.

one significant figure. The elemental composition $\text{Li}_2\text{Fe}_{0.8}\text{Zn}_{0.2}\text{P}$ is the same as the one of zinc-doped lithium iron phosphate ($\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$; for Li, Fe, Zn, and P) except for an excess of lithium. This observation verifies both the production of a zinc-doped LiFePO_4 compound with the formula $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ and the existence of Li_2SO_4 in the product. It is also important to note that as the Li_2SO_4 byproduct is produced in the aqueous phase and, consequently, a significant fraction of it ends up in the filtrate, the Li_2SO_4 impurity in the product does not account for the entire Li_2SO_4 (aq) produced.

Product purification

This work has been aimed at developing a low-temperature method for the synthesis of zinc-doped LiFePO_4 . As the product was originally obtained in the form of a precipitate, the entire precipitate was what went through characterization. The purification of the zinc-doped LiFePO_4 can be achieved by mixing the precipitate with hot water followed by the filtration-based removal of the impurity as aqueous Li_2SO_4 in the filtrate. We were very careful during the cleaning process of our prepared product, making sure to avoid any treatment that may alter or change the identity or originality of our prepared sample.

Figure 7. Li-7 MAS-NMR spectrum of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ (spin frequency = 8 kHz).

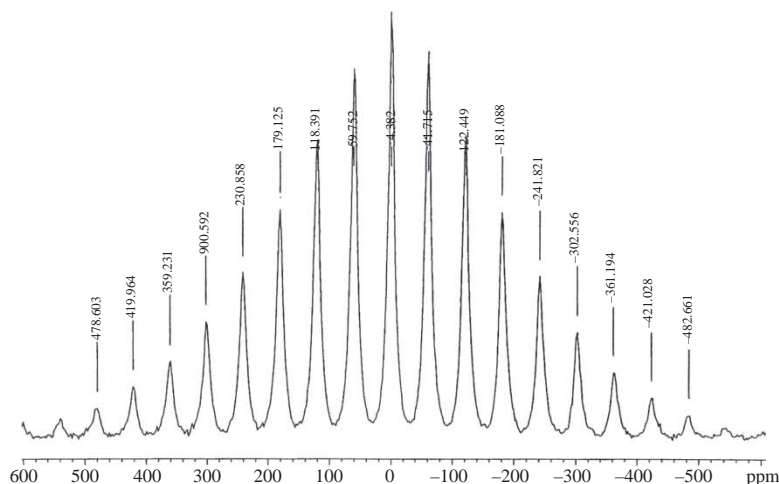


Figure 8. Li-7 MAS-NMR spectrum of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$ (spin frequency = 7 kHz).

Although product purity is important, at this early stage, the focus was more on the type of raw product our technique can lead to, than on yield or purity.

Experimental

Materials

The starting materials used for the synthesis were Li_3PO_4 from Aldrich Chemical Co., ferrous sulfate crystals ($\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$) from Baker and Adamson Chemical Co., and zinc sulfate crystals ($\text{ZnSO}_4 \cdot 6\text{H}_2\text{O}$) from Mallinckrodt Chemical Co.

Preparation

In the wet synthesis of $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$, centimolar amounts of Li_3PO_4 (MW = 115.79 g/mol), $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ (MW = 278.01 g/mol), and $\text{ZnSO}_4 \cdot 6\text{H}_2\text{O}$ (MW = 269.54 g/mol) are used in the molar ratios of 1 Li_3PO_4 :0.8 $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$:0.2 $\text{ZnSO}_4 \cdot 6\text{H}_2\text{O}$. Using deciliter volumes of de-ionized water, the Li_3PO_4 sample is mixed with de-ionized water with continuous stirring, while water is brought to boiling, and the hydrated iron and zinc sulfate samples are dissolved together in another aliquot of de-ionized water. Then the solution is added to the Li_3PO_4 suspension all at once. The reaction mixture is stirred and heated continuously for about two hours to have the iron and zinc ions precipitated (as $\text{LiFe}_{0.8}\text{Zn}_{0.2}\text{PO}_4$) com-

pletely (as the proposed reaction equation predicts based on the used molar ratios of the starting materials). In about two hours, the heat is removed. After half an hour, the mixture is filtered using the suction filtration method. The green precipitate is heated in an oven at 110°C for three hours. The product (that is, the final product) is amorphous. In order to crystallize it for the purpose of characterization, some of the prepared sample was heated at 650°C for 24 hours.

Characterization

In order to characterize the product, the following characterization techniques and procedures were applied.

X-ray diffraction

X-ray powder patterns were obtained for both the sample heated at 110°C and the one heated at 650°C using a SCINTAG automated PAD-X diffractometer utilizing monochromatic $\text{CuK}\alpha$ radiation. The diffraction patterns were taken in the range of $5 < 2\theta < 45$ degrees. The 2θ step size was 0.02 degrees and the count time was one second. Quartz was used as an internal standard.

Fourier Transform Infrared (FTIR) spectroscopy

FTIR spectra of both the sample heated at 110°C and the one heated at 650°C were collected using a Nicolet Magna 760 spectrometer. Both spectra were collected with a resolution of 4 cm^{-1} and 64 scans per sample in the mid-IR region of $4000\text{--}400\text{ cm}^{-1}$. Potassium bromide was used as the reference.

Table 2. Results from elemental analysis.

Mass (%)	Sample 110°C	Sample 650°C
Iron (%)	20.57	18.43
Lithium (%)	4.63	4.66
Phosphorous (%)	12.78	13.32
Zinc (%)	4.58	4.27

TGA and DTA

Thermal gravimetric analysis (TGA) and differential thermal analysis (DTA) diagrams of the sample heated at 110°C were obtained using a TG 7/DT 7 Perkin Elmer Analyzer in flowing nitrogen with heating from 22.3 to 700°C at a rate of 10°C/min.

Lithium-7 solid-state nuclear magnetic resonance (NMR) spectroscopy

The Li-7 MAS-NMR spectra were acquired on a Varian Unity Pulse 300 solids spectrometer equipped with a XC-5 MAS probe from Doty Scientific. Samples were packed in the ambient in either silicon nitride or zirconia rotors with Aurum or Kel-F caps. MAS data for each sample were acquired at two spinning speeds with at least a difference of 1000 Hz to determine the isotropic shift with reference to 0.01 M LiCl (aq). Spinning speeds are provided in the appropriate figure caption.

Elemental analysis

Both the sample heated at 110°C and the one heated at 650°C were given to Schwarzkopf Microanalytical Laboratory, Inc. in Woodside, New York (<http://www.schwarzkopfmicrolab.com/>) for their mass percentages determination for iron, lithium, phosphorus, and zinc.

Conclusion

In order to substitute the environmentally friendly lithium-ion battery cathode material LiFePO₄ with an environmentally and technologically similar advantageous material which has a higher electronic conductivity, a LiFe_{0.8}Zn_{0.2}PO₄ was synthesized using, for the first time, a synthetic method which is low-temperature and is, therefore, in comparison to the high-temperature method, expected to be resulting in a product with a relatively large surface area. The developed synthetic method has also the advantage of costing less as far as heating is the concern (as instrumentally applying more heat requires a higher thermal budget). Following purification, the compound can be electrochemically tested and evaluated as a green cathode material. With the iron-to-zinc molar ratio in the produced zinc-doped LiFePO₄ being

the same as the one in the quantities of the iron and zinc starting materials, the method appears to be applicable for synthesizing various zinc-doped LiFePO₄ compounds with the general formula LiFe_{1-x}Zn_xPO₄ (0 < x < 1). This makes the method very promising for the low-temperature production of a high-electronic-conductivity green cathode material for lithium-ion batteries.

Acknowledgements

We would like to thank all the staff of the Long Island University (Brooklyn Campus) chemistry preparation rooms for their great cooperation in providing us with the chemicals used in this work. Becky Gee thanks Professor Ruth Stark and Dr. Hsin Wang (Department of Chemistry, College of Staten Island, City University of New York) for use of their solid-state NMR instrumentation.

References

- (1) Järup, L. *Br. Med. Bull.* **2003**, 68, 167–182.
- (2) Alper, J. *Chem. Mag. (ACS)* **2002**, Autumn, 11–14.
- (3) Risher, J.F.; De Rosa, C.T. *J. Environ. Health* **2007**, 70, 9–16.
- (4) Thomas, J. *Nat. Mater.* **2003**, 2, 705–706.
- (5) Nazri, G. *MRS Bull.* **2002**, 27, 628–631.
- (6) Chung, S.; Bloking, J.T.; Chiang, Y. *Nat. Mater.* **2002**, 1, 123–128.
- (7) Liu, H.; Cao, Q.; Fu, L.J.; Li, C.; Wu, Y.P.; Wu, H.Q. *Electrochem. Commun.* **2006**, 8, 1553–1557.
- (8) Shenouda, A.Y.; Liu, H.K. *J. Alloys Compd.* **2009**, 477, 498–503.
- (9) Xu, C.B.; Lee, J.; Teja, A.S. *J. Supercrit. Fluids* **2008**, 44, 92–97.
- (10) Ni, J.F.; Zhou, H.H.; Chen, J.T.; Zhang, X.X. *Mater. Lett.* **2005**, 59, 2361–2365.
- (11) Santoro, R.P.; Newnham, R.E. *Acta Crystallogr.* **1967**, 22, 344–347.
- (12) 19-0721. JCPDS-International Centre for Diffraction Data; 1996.
- (13) 20-0640. JCPDS-International Centre for Diffraction Data; 1996.
- (14) Nyquist, R.A.; Kagel, R.O. *Infrared Spectra of Inorganic Compounds*; New York and London: Academic Press, 1971.
- (15) Tucker, M.C.; Doeff, M.M.; Richardson, T.J.; Fiones, R.; Cairns, E.J.; Reimer, J.A. *J. Am. Chem. Soc.* **2002**, 124, 3832–3833.