

Minimum and Full Fluidization Velocity for Alumina Used in the Aluminum Smelter

Regular Paper

Paulo Douglas S. de Vasconcelos^{1,*} and André L. Amarante Mesquita²

¹ Albras - Alumínio Brasileiro S/A

² Federal University of Pará

* Corresponding author E-mail: pdouglas@albras.net

Received 27 Jul 2011; Accepted 02 Nov 2011

Abstract Fluidization is an engineering unit operation that occurs when a fluid (liquid or gas) ascends through a bed of particles, and these particles get a velocity of minimum fluidization V_{mf} enough to stay in suspension, but without carrying them in the ascending flow. As from this moment the powder behaves as liquid at boiling point, hence the term “fluidization”. This operation is widely used in the aluminum smelter processes, for gas dry scrubbing (mass transfer) and in a modern plant for continuous alumina pot feeding (particles’ momentum transfer). The understanding of the alumina fluoride rheology is of vital importance in the design of fluidized beds for gas treatment and fluidized pipelines for pot feeding.

This paper shows the results of the experimental and theoretical values of the minimum and full fluidization velocities for the alumina fluoride used to project the state of the art round non-metallic air-fluidized conveyor of multiples outlets.

Keywords Fluidized bed, Minimum fluidization velocity, Permeameter, Maximum pressure drop

1. Introduction

Gas-solid flow occurs in many industrial operations. The majority of chemical engineering units operations, such

as drying, separation, adsorption, pneumatic conveying, fluidization and filtration involve gas-solid flow.

Poor powder handling in an industrial process operation may result in a bad performance, leading to errors in the mass balance, erosion caused by particles impacts in the pipelines, attrition and elutriation of fines overloading the bag houses. Lack of a good gas-solid flow rate measurement can cause economic and environmental problem due to airborne particles.

This paper focuses on the applications of powder technology related to the aluminum smelters processes such as dry scrubbing of gases and pot feeding to produce primary aluminum.

To optimize the residence time in the gas-adsorption process and minimize the energy consumption in the pot feeding, the precise determinations of the minimum and full fluidization velocities as well as the aerated and non-aerated angle of repose of the fluoride alumina are mandatory.

2. Fundamentals of powder fluidization

In the powder processes discussed above, it is important to know the hydrodynamic behavior of the particles in fluidized beds. It is known that the fluidization behavior

of a gas-solid bed depends on the particle diameter and density. (Geldart, (1972-1973))¹ classified powders into four types: C, A, B and D, based on their fluidization behavior. Geldart's diagram is illustrated in figure 1.

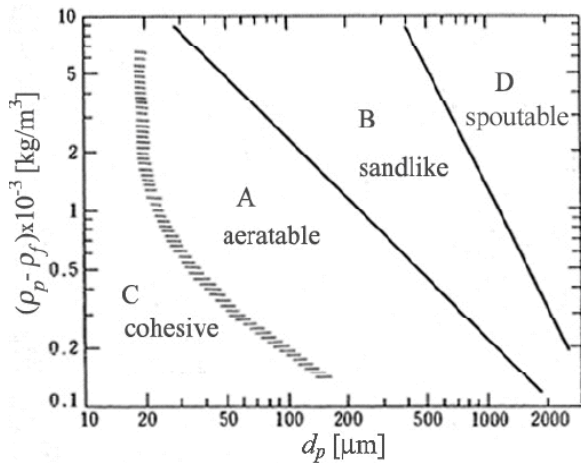


Figure 1. Powder classification diagram for fluidization by air – source: (Geldart, (1972-1973))¹.

The fluidized bed regime map is illustrated in figure 2. Group C particles have small diameters and are very difficult to fluidize. Channeling the bed of particles becoming difficult to determine the minimum fluidization velocity – ultrafine alumina ($d_p < 20 \mu m$). Group A particles are aeratable and readily fluidize – fine alumina ($d_p \sim 40.5 \mu m$). Group B alumina forms a bubble bed after the fixed bed with increasing gas velocity – $d_p > 70 \mu m$. Group D particles are relatively large bean-shape particles – $d_p \sim 1000 \mu m$. This bed of particles is spoutable, re-circulating the particles in the fluidized bed

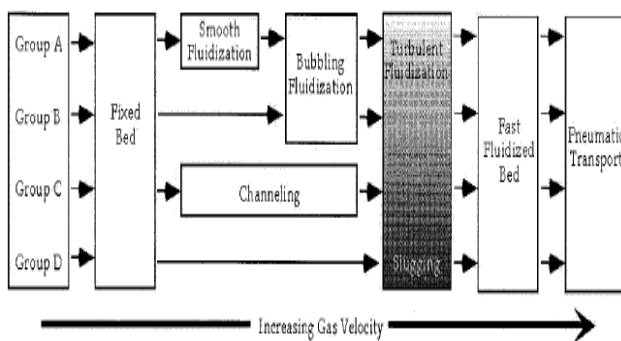


Figure 2. Flow regime map for various powders

2.1 Minimum fluidization velocity calculation

This is generally defined as minimum superficial velocity at which the drag force and the upward buoyant force due to the fluid is balanced by the weight of the particles illustrated in figure 3.

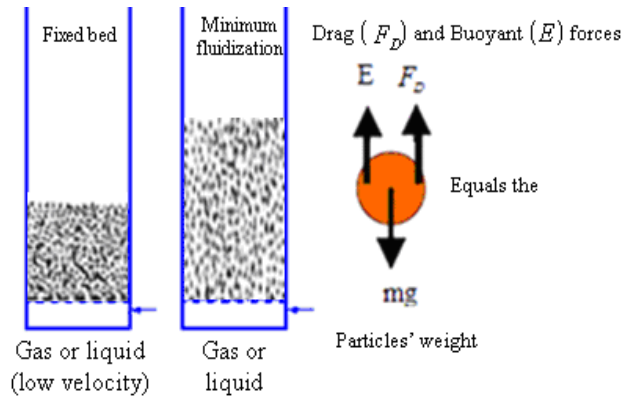


Figure 3. Fixed and a fluidized bed of particles at a minimum fluidization velocity – source: (Vasconcelos and Mesquita, 2011)²

2.1.1 Theoretical model equations for predict: V_{mf}

(Ergun, 1952)³ developed, for fixed beds, a pressure-drop correlation at incipient fluidization based on drag force considerations of a single particle in a bed of particles of the same size and neglecting the buoyant force as follows in equation 1.

$$(1 - \epsilon_{mf})(\rho_s - \rho_g)g = 150 \frac{(1 - \epsilon_{mf})^3}{\epsilon_{mf}^3} \frac{\mu_g V_{mf}}{(\phi_s d_p)^2} + 1.75 \frac{(1 - \epsilon_{mf})}{\epsilon_{mf}^3} \frac{\rho_g V_{mf}^2}{\phi_s d_p} = A V_{mf} + B V_{mf}^2 \quad (1)$$

Calculating C by equation 2 one gets an equation of second power, which the positive solution is calculated by equation 3.

$$C = (1 - \epsilon_{mf})(\rho_s - \rho_g)g \quad (2)$$

$$V_{mf} = \frac{-A + \sqrt{A^2 + 4BC}}{2B} \quad (3)$$

Where A and B are the viscous and the inertial factor of the Ergun equation, C is the weight per unit volume of the bed of particles.

Fluidization is related with small velocities, the factor B is negligible and the Ergun equation can be simplified with an error less than 5% related to equation 3 by the equation 4.

$$V_{mf} = \frac{C}{A} \Rightarrow V_{mf} = \frac{(\rho_s - \rho_g)g \epsilon_{mf}^3 (\phi_s d_p)^2}{150(1 - \epsilon_{mf})\mu_g} \quad (4)$$

The prediction of V_{mf} by Ergun's equation for pressure drop requires the knowledge of sphericity of the particle (ϕ_s) and bed voidage (ϵ_{mf}). Many researchers has been trying to overreach the difficult to determine the voidage and sphericity of the particle, combining equations 1 and 2, plus the Arquimedes, Froude and Reynolds numbers with their experimental results adjusting their equations to predict V_{mf} as can be seen in table 1.

Authors	Equation
Leva ⁴	$V_{mf} = 9.23 \times 10^{-3} d_p^{1.81} \left(\frac{\rho_s}{\mu_g} \right)^{0.88} \left(\frac{\rho_s}{\rho_g} \right)^{0.94} \quad (5)$
Abrahamsen & Geldart ⁵	$V_{mf} = 9 \times 10^{-4} d_p^{1.8} \left[(\rho_s - \rho_g) g \right]^{0.934} \rho_g^{-0.066} \mu_g^{-0.87} \quad (6)$
Coltters & Rivas ⁶	$V_{mf} = 3.7774 \times 10^{-5} \left(\frac{d_p^2 (\rho_s - \rho_g) g}{\mu_g} \right)^{0.603559} \left(\frac{\rho_s}{\rho_g} \right)^{1.23} \quad (7)$
Wen & Yu ⁷	$V_{mf} = \frac{\mu_g}{\rho_g d_p} \left(\sqrt{33.7^2 + 0.0408 A_r} - 33.7 \right) \quad (8)$
Miller & Logwinuk ⁸	$V_{mf} = 1.25 \times 10^{-3} \left(\frac{d_p^2 (\rho_s - \rho_g)^{0.5} \rho_g^{1.1} g}{\mu_g} \right) \quad (9)$

Table 1. Semi-empirical equations for predicting minimum fluidization velocity V_{mf}

For an incipient fluidization, when the weight of particles equals the drag force, it is a good attempt to consider the porosity at the minimum fluidization velocity ε_{mf} equals or close the porosity ε of the fixed bed. The porosity of the fixed bed is calculated by the equation 10.

$$\varepsilon = 1 - \frac{\rho_{bmv}}{\rho_s} \quad (10)$$

$$\rho_{bmv} = \frac{M_s}{V_{total}} \quad (11)$$

Where ρ_{bmv} is the non-vibrated bulk density, ρ_s is the solid real density derived in a laboratory by a pycnometer, M_s is the total mass of particles weighted on an electronic scale, V_{total} is the total volume of particles and voids in the sample previously weighted on an electronic scale, d_p is the particle mean diameter obtained by sieve analysis in a laboratory, ϕ_s is the particle sphericity, that can be estimated from figure 4 considering a normal packing bed of particles. Based on the work of (Biswal *et al*, 2007)⁹ and data for alumina fluoride obtained upon a thesis by (Vasconcelos, 2011)¹⁰ for doctorate degree at Federal University of Pará, equation 12 was proposed to predict the minimum fluidization velocity.

$$V_{mf} = 0.21 (A_r)^{0.25} \left(\frac{\phi_s}{1.05 \varepsilon} \right)^{0.7} (d_p g)^{0.5} \quad (12)$$

Where:

$$\text{Arquimedes Number: } A_r = \frac{d_p^3 (\rho_s - \rho_g) \rho_g g}{\mu_g} \quad (13)$$

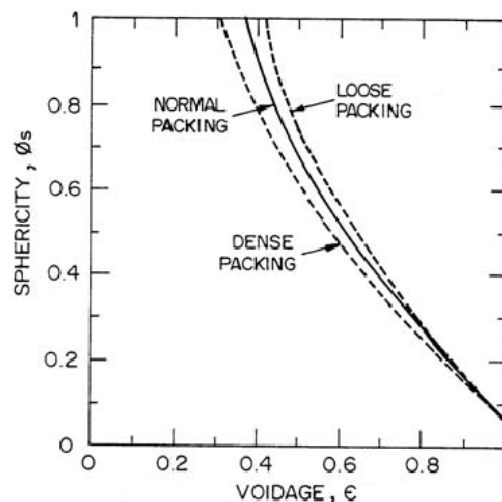


Figure 4. Voidage in uniformly sized and randomly packed beds- adapted from (Kunii and Levenspiel, 1991)¹¹

And ρ_g ; μ_g ; g are respectively the real density and viscosity of the gas (air); acceleration due to gravity.

The experimental value of V_{mf} and minimum velocity of full fluidization V_{mff} are obtained using a permeameter as showed in figure 5 measuring the gas superficial velocity and the pressure drop through the bed of particles.

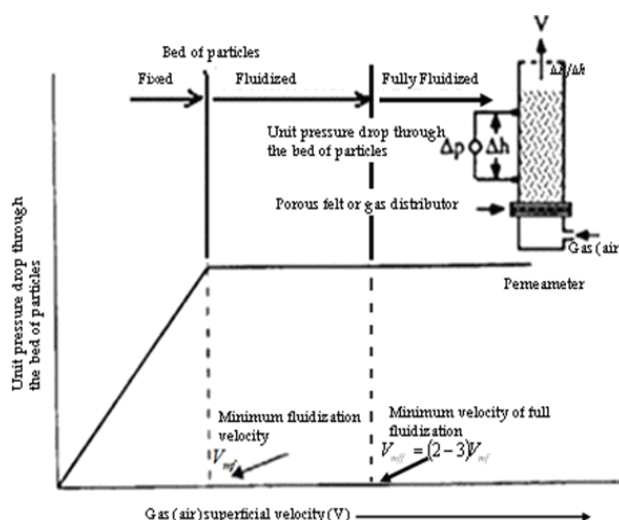


Figure 5. Pressure drop through a bed of uniformly particles versus superficial air velocity – source: (Mills, 1990)¹².

2.1.2 Experimentals details

A schematic diagram of the experimental set-up is shown in figure 6. The arrangement of the permeameter made of fiberglass with acrylic sheets to allow visual observation of the fluidized particles. Two rectangular and one circular shape permeameters were built as illustrated in figure 7. Air flow rate is measured by rotameters with precision of $\pm 3\%$ full scale and the pressure drop with the appropriate dust filter in the pressure taps is

measured by digital pressure transmitters at a precision of $\pm 1\%$ of full scale. Air at a temperature of 303 K, ($\rho_g = 1.189 \text{ kg m}^{-3}$ and $\mu_g = 18.602 \times 10^{-6} \text{ Pa.s}$) under one atmospheric pressure, used as the fluidizing medium was passed through a dust filter and humidity eliminator. The pressure was regulated at 2 bars in the inlet of the rotameters.



Figure 6. Permeameters used at Albras' laboratory to survey the minimum fluidization velocity of the powders used in the primary aluminum industry - source: (Vasconcelos, 2011)¹⁰.

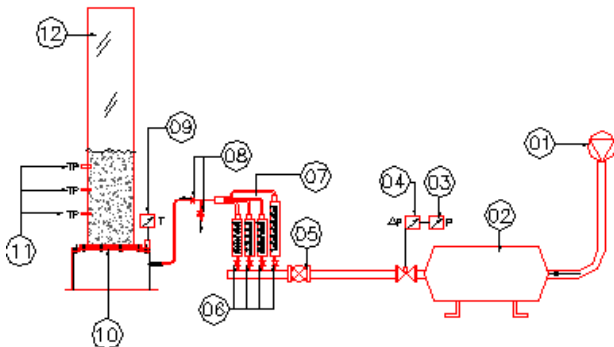


Figure 7. Experimental set-up: 1) air mover; 2) air receiver; 3) manometer; 4) air pressure regulator (0 – 3) bar; 5) ball valve; 6) air flow regulator; 7) rotameters (0 – 10; 0 – 25; 0 – 100; 0 – 700) LPM; 8) ball valves; 9) thermometer; 10) polyester porous membrane; 11) pressure drop transmitters (0 – 125; 0 – 1250; 0 – 5000) Pa; 12) permeameter.

Diameter range (μm)	d_p^- (μm)	Weight fraction x_i	$(x/d_p^-)_i$
0 – 37	18.5	0.0465	0.002513
37 – 44	40.5	0.0395	0.000975
44 – 74	59	0.2743	0.004649
74 – 147	110.5	0.6027	0.005454
147 – 250	200	0.0365	0.000182
		$\sum (x/d_p^-)_i$	0.0013774
	d_p (μm)	$d_p = 1/\sum (x/d_p^-)_i$	72.6 \pm 2.7

Table 2. Fluoride alumina sieve analysis – 100 samples (minimum /maximum size and standard deviation): (68.68/78.23 and 2.7) μm - source: (Vasconcelos, 2011)¹⁰.

2.1.3 Procedures

Alumina is a mixture of multi-size particles, so before to start the fluidization survey, it was necessary to perform a sieve analysis to characterize the particles size as can be seen in table 2.

Firstly, a determined initial mass (15 – 53 kg) of alumina fluoride was introduced in the big rectangular 14" permeameter and (3 – 12 kg) in the circular 8" permeameter in order to ensure a bed height of about 0.1-0.4 m. Prior to actual fluidization tests, the bed was pre-conditioned to reduce the influence of interparticles forces in the dense bed packing. To this end, the superficial air velocity was rapidly increased around the predicted V_{mf} and then decreased in more or less 30 s. This procedure guarantees better homogeneity of the bed. After this preparation the air flow rate was increased in steps of 2 LPM (liters per minute) for about one minute and subsequently the pressure drop in bed of particles was measured until the pressure drop stays constant at a variation less than 5%. Then, the air stream was decreased in steps of 2 LPM until 0 LPM see figure 8. Each fluidization cycle test (batches of alumina fluoride summarized in table 3) was repeated twice.

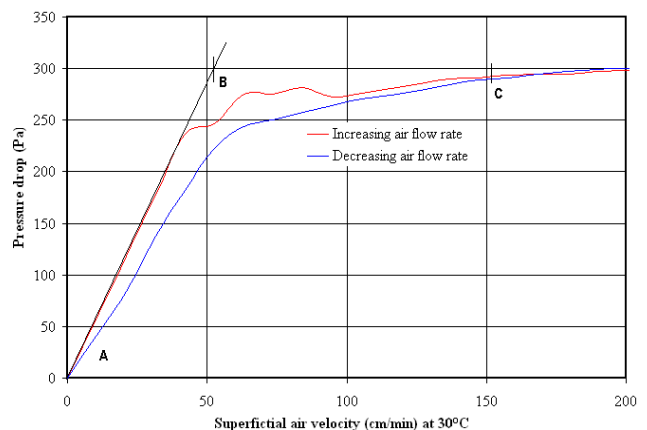


Figure 8. Experimental pressure drop in the bed of alumina fluoride - (72.6 \pm 2.7) μm / 3387.3 kg.m^{-3} versus superficial air velocity - source: (Vasconcelos, 2011)¹⁰.

From point A to point B in figure 8 the pressure drop increases with velocity (fixed bed). The transition from the stagnant bed to fluidized bed occurs at point B, i.e. at the minimum fluidization velocity V_{mf} (52 cm/min) intersection with the maximum pressure drop. From point B the pressure drop increases until point C, i.e. at the minimum velocity of full fluidization V_{mff} (153 cm/min). The pressure drop remains constant with variation around 5% of the maximum pressure drop. After point C the bed is fully fluidized.

The same procedures explained above were used to obtain the experimental values of V_{mf} and V_{mff} .

summarized in table 3 for others diameters of the alumina fluoride used at Albras aluminum smelter.

3. Results and Discussions

The minimum fluidization velocity was predict using equation 12 proposed by (Vasconcelos, 2011)¹⁰ with an average absolute error less than 0,5% compare with the experimental showed in figure 8.

For the granulometries sub 37 μm (- 400 mesh), it was used a small rectangular permeameter illustrated in figure 9, because after more than 150 sieve analysis of the fluoride alumina we got only one kilogram of this fraction to study. As can be observe in figure 9 it was impossible to determine the minimum fluidization velocity in this test due to channeling in the bed of particles.

The experimental data obtained for the minimum fluidization velocity V_{mf} were compare with the equations proposed by (Vasconcelos, 2011)¹⁰, (Ergun, 1952)³ and others researchers listed in table 1. The comparison of calculated and experimental V_{mf} for a stagnant bed of particles with the data related in table 2 is shown in table 4 with the respective absolute error (%) based on experimental value. Figures 10 and 13 show the graphic analysis.

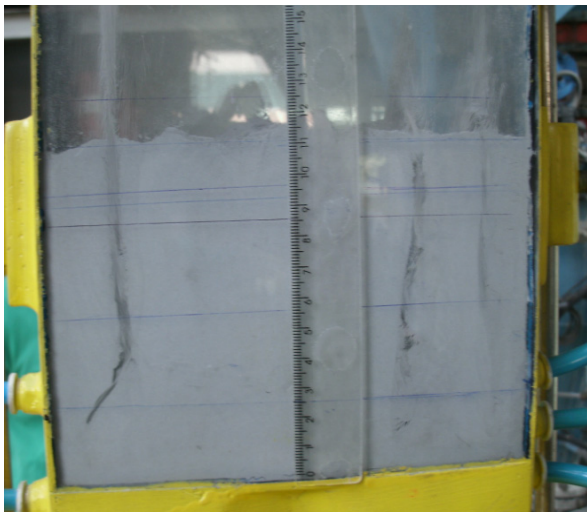


Figure 9. Permeameter of 50x200 mm used to fluidize alumina fluoride sub 37 μm (Geldart group C).

Material	Particle density	Bed Voidage	Particle sphericity	V_{mf} (cm / min.)
Alumina fluorida	$kg.m^{-3}$	(-)	(-)	Experimental
Particle diameter (m)				
0.0000405	3310.3	0.709996	0.37	14
0.000059	3336.1	0.71523	0.36	42
0.0000726	3387.3	0.71658	0.365	52
0.0001115	3381.9	0.707265	0.371	94
0.0002	3263	0.59852	0.52	250

Table 3. Parameters of the fluidized bed of alumina fluoride's particles - source: (Vasconcelos, 2011)¹⁰.

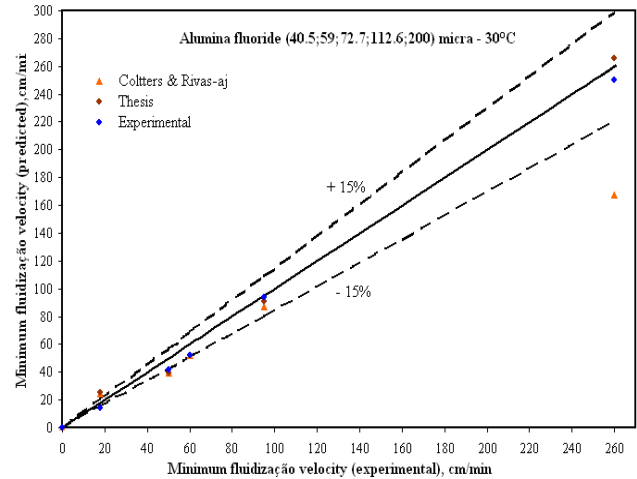


Figure 10. Comparison of experimental values of V_{mf} and predicted by Vasconcelos and Colters and Rivas.

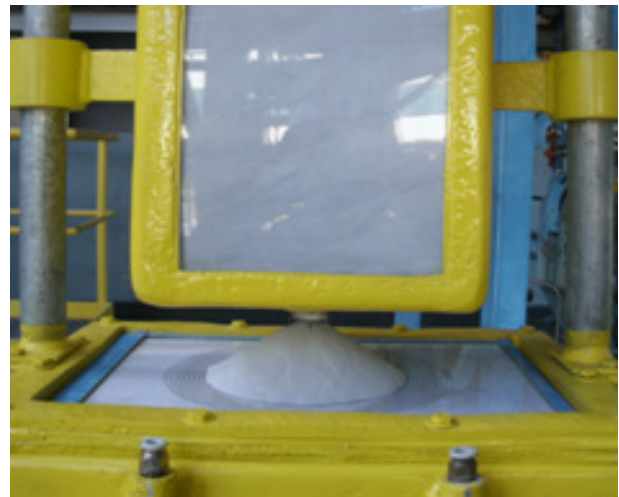


Figure 11. Apparatus to measure the non-aerated and aerated angle of repose – alumina fluoride non-aerated angle of repose (32.73+0.437)°.



Figure 12. Albras non metallic air fluidized conveyor of three outlets

Material		$V_{mf}(cm/min)$								Absolute error (%) based on exp. value								
Alumina fluoride		(a)	(b)	(c)	(d)	(e)	(f)	(g)	(h)	(b)	(c)	(d)	(e)	(f)	(g)	(h)		
dp [μm]																		
	40.5		14	25.36	18.74	16.93	14.12	24.9	10.4	11.13		81.14	33.86	20.92	0.86	77.86	27.86	19.78
	59		42	39.70	39.44	33.84	28.00	39.6	22.23	23.79		5.48	6.1	19.43	33.33	5.71	47.1	43.36
	72.6		52	52.16	63.19	50.18	41.36	52	34.26	36.61		0.31	21.52	3.5	20.46	0.00	34.11	29.6
	111.5		94	90.85	142.53	109.16	89.20	87	80.39	86.02		3.35	51.62	16.12	5.10	7.45	14.48	8.49
	200		250	266.09	380.39	305.60	246.95	167.8	247.97	267.99		6.43	52.15	22.24	1.22	32.88	0.81	7.2

(a) Experimental;

(b) Thesis;

(c) (Ergun, 1952);

(d) (Leva, 1959);

(e) (Abrahamsen e Geldart, 1980);

(f) (Coltters e Rivas, 2004) ajustada;

(g) (Wen e Yu, 1996);

(h) (Miller e Logwinuk, 1951).

Table 4. Comparison of experimental and predicted minimum fluidization velocity for stagnant bed of alumina fluoride – source: (Vasconcelos, 2011)¹⁰.

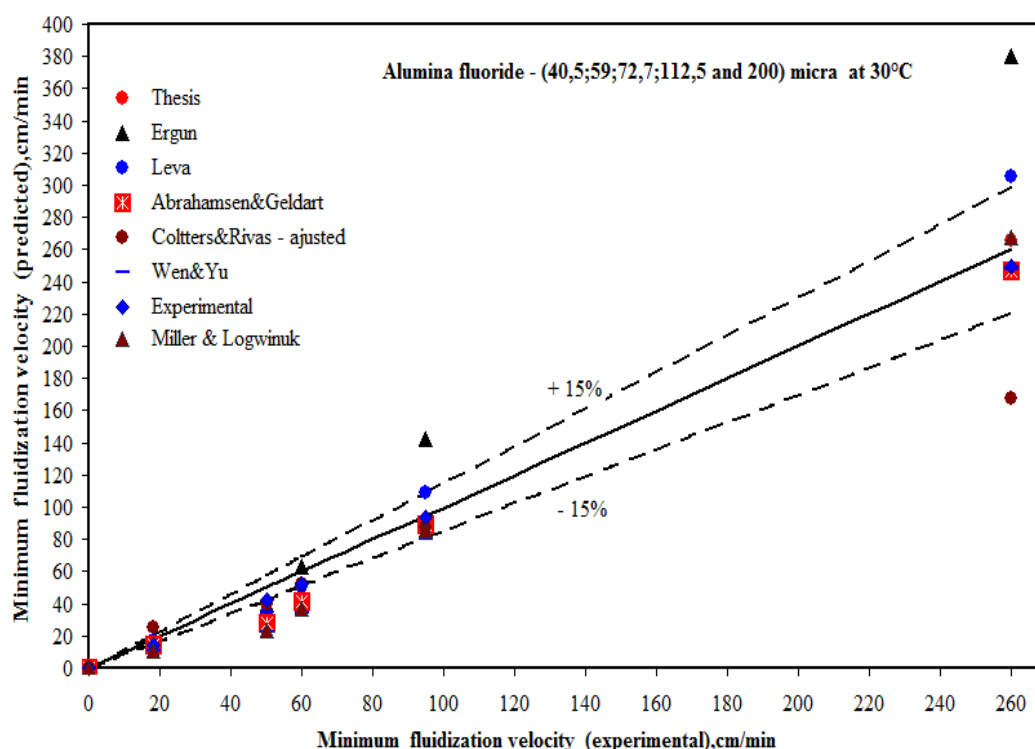


Figure 13. Comparison of experimental values of V_{mf} with predicted values

4. Conclusions

Experimentals were carried out with alumina fluoride and four fractions of this alumina in the fluidization laboratory erected at Albras smelter to survey the alumina rheology in order to optimize energy consumption of the state of art air fluidized conveyor developed and showed in figure 12.

An equation was developed to predict the minimum fluidization velocity upon a thesis by (Vasconcelos, 2011)¹⁰ compared with other researchers and the experimental values. The predict values by Vasconcelos and Coltters and Rivas adjusted by the experimental

result for $d_p = 70.6 \mu m$ are quite satisfactory with the experimentals results with an error less than 0,5% as can see in table 4 and in figure 10 and 13.

The correlations of Abrahamsen and Geldart fit very well with fine powders of group C and A. The equations of Wen and Yu and Miller and Logwinuk show better results for large particles of group B and D. The equation of Leva fit better with group B powders.

The correlations of Ergun and Vasconcelos are very sensitive to porosity and the sphericity of the particles and hence care should be taken to measure the porosity very accurately and also in estimate the sphericity using figure 4.

The proposed correlation by this paper could also find practical utility in designing and operations of fluidized bed for gas dry scrubbing to estimate the residence time of the particles in contact with gases and also optimized the size and energy consumption of air slides.

Other important parameter is the non aerated and aerated angle of repose illustrated in figure 11 to estimate flowability of the powder to be transport in conventional or new development of air fluidized conveyors of multiples outlets.

5. Acknowledgment

The authors would like to thanks the Lord God for this opportunity, Albras Alumínio Brasileiro SA for the authorization to public this paper, the Federal University of Pará for my doctorate in fluidization engineering and to my manager Marcelino Vasconcelos and the general managers Luís Carlos Carvalho Costa and Braz Mileo Ferraioli.

6. References

- [1] Geldart, D. Types of Gas Fluidization Powder Technology, 7, 285 – 292 (1972 – 1973).
- [2] Vasconcelos, P. D. and Meaquita, L. A. Gas-solid flow applications for powder handling in industrial furnaces operations. Heat Transfer/Book 5, ISBN 978-953-307-585-3. Intech open access publisher, Rijeka, (2011).
- [3] Ergun, S. Fluid Flow through Packed Columns, Chem. Engrg. Progress, Vol. 48, No. 2, pp. 89 – 94 (1952).
- [4] Leva, M., Fluidization, McGraw-Hill, New York (1959).
- [5] Abrahamsen, A. R. and Geldart, D. Behavior of gas fluidized beds of fine powders. I. Homogenous expansion, Powder technology, Vol. 26, 35, (1980).
- [6] Coltters, R. and Rivas, A. L. Minimum fluidization velocity correlations in particulate systems, Powder Technology Vol. 147 pp. 34 – 48 (2004).
- [7] Wen, C. Y. and Yu, Y. H., Mechanics of Fluidization, Chem. Engrg. Progress Symp. Series, Vol. 62, No. 62, pp. 100 – 111 (1966).
- [8] Miller, C. O. and Logwinuk, A. K. Ind. Eng. Chem., 43 (1951) 1220.
- [9] Biswal *et al.* Minimum fluidization velocities and maximum bed pressure drops for gas-solid tapered fluidized beds.
- [10] Vasconcelos, P. D. Doctorate Thesis, Federal University of Pará at Belém, 2011.
- [11] Kunii, D. & Levenspiel O. Fluidization Engineering, second edition, Butterworth-Heinemann, Boston (1991).
- [12] Mills, D. Pneumatic Conveying Design Guide, Butterworths, London, (1990).