

Investigation of tribological and mechanical properties of metal bearings

BEKIR SADIK ÜNLÜ

Department of Machinery, Vocational High School, Celal Bayar University, 45400-Turgutlu-Manisa, Turkey

MS received 18 August 2008; revised 2 September 2009

Abstract. Copper, aluminum and tin–lead based alloys are widely used as journal bearing materials in tribological applications. Bronze and brass are widely used as journal bearing materials for copper based alloys. Zamacs find applications as journal bearing materials for zinc based alloys, while duralumines are chosen as journal bearing materials for aluminum based alloys. In addition, white metals are widely used as journal bearing materials for tin–lead based alloys. These alloys ensure properties expected from journal bearings. In this study, tribological and mechanical properties of these journal bearings manufactured by metals were investigated. SAE 1050 steel shaft was used as counter abrader. Experiments were carried out in every 30 min for a total of 150 min by using radial journal bearing wear test rig.

Keywords. Non-ferrous metals; bearings; tribology; mechanical properties.

1. Introduction

In the past few years, wood, iron and skin have been used as journal bearing materials. Later, brass, bronze and white metal have also found some applications. Currently, in addition to these bearing materials, aluminum and zinc based materials are used as journal bearing materials. With technological improvements, self-lubricated sintered bearings and plastic materials are used where continuous lubricating is impossible. Therefore, it is essential that the bearing material be chosen depending upon area of application.

Wear resistance is one of the most important properties that journal bearings should possess. There are several studies and investigations dealing with wear resistance improvements of these materials (Eyre 1991; Schatt and Wieters 1997; Enomoto and Yamamoto 1998; Ünlü 2004).

Copper based materials are widely used as bearing materials because they have high thermal and electrical conductivity, self-lubrication property, good corrosion and wear resistance (Schmidt and Schmidt 1993; Paulo 2000). The effect of tin on wear in copper based materials is important. Copper based tin bronzes are used as bearing materials to have a high wear resistance (Prasad 1997). Friction and wear properties of these materials can be improved by adding tin (Backensto 1990). Tin bronze (90% Cu and 10% Sn) is the most suitable bearing material under corrosive conditions, at high temperatures and high loads (Pratt 1973).

Zinc based alloys were used instead of bronze during World War II as journal bearing materials to compensate

for copper deficiency in Germany (Pürçek 1994). Zn based alloys are used due to high strength, high hardness and good friction properties in several engineering applications. Tribological properties of Al and Cu alloys are better than those of pure Zn and Zn–Al alloys. Tribological and mechanical properties of Zn–Al alloys can be improved by heat treatment and by Mn, Si, and Cu addition. Therefore, these alloys can be used as journal bearing materials (Hanna *et al* 1997). Zn based alloys are used because of their good physical, mechanical and tribological properties, low cost, high wear resistance as journal bearing materials. Tribological properties of ZnAlCuSi alloy were higher than those of ZnAl and bronze (Pürçek *et al* 1999; Savaşkan *et al* 2002; Çuvalcı and Baş 2004). ZA27 is an alloy with good tribological properties. If 2.5% Si was added to alloys, wear resistance would increase (Harmsen *et al* 1996). These alloys are important for high loading, low speed applications as journal bearing materials. Tribological properties of these alloys are higher than those of bronze materials. They are preferred to Al alloy, and cast iron due to high non-seizure, mechanical and wear resistance property for journal bearing applications. Hardness decreases, but friction coefficient and wear resistance increase by graphite addition (Sharma *et al* 1998).

Al alloys containing Cu, Mg and Mg, Si; Sn are used as bearing materials (Lepper *et al* 1997). Until the early 1940s, white metal was used and then Al alloys were used as bearing materials (Niinomi *et al* 1997). Al alloys can be used in applications where corrosion is a problem. Wear resistance of Si added Al alloys is higher than that of the other Al alloys (Haque and Sharif 2001). Al–Si alloys have good castability, thermal conductivity, and

(bekir.unlu@bayar.edu.tr)

weldability, high strength and excellent corrosion resistance. They are used in pistons and bearings due to these properties. Si particles can be distributed into structure uniformly, thus material hardness increases (Prasad and Rohatgi 1987). In addition, Al–Mg–Si alloys are used in tribology applications due to excellent sliding and mechanical properties such as high strength, high deformability and good wear resistance (Liu *et al* 1999).

Tribo-materials used have embability and high wear resistance for crank shaft in automobiles. These bearings have lead, tin, aluminium and copper. These elements are coated to steel bearing due to their superior wear properties (Upadhyaya *et al* 1997; Dawson 1998; Enomoto and Yamamoto 1998).

Lead and tin based white metal alloys are used due to their antifriction property as bearing materials. These alloys are produced by casting and spray deposition method. These casting alloys contain intermetallic phase. The process variables during spray forming of babbitt bearing metal alloy strongly influence the microstructure and porosity of the spray deposits. The wear rate of the spray-formed alloy is lower than that of the as-cast alloy. Wear properties of the spray-formed alloy are attributed to the decreased intermetallic phases and modification in the microstructure of the eutectic phases (Upadhyaya *et al* 1997). SnPbCuSb (white metal) alloys are important due to non-seizure and good wear resistance as journal bearing material (Ünlü 2004).

Journal bearing materials are expected to have several properties such as low friction coefficient, high load capacity, high heat conductivity, compatibility, high wear and corrosion resistance. These properties directly affect the fatigue and wear life (Pratt 1973; Backensto 1990; Prasad 1997). White metal (babbitt), cast iron, bronze, aluminum, and zinc–aluminum-based materials have been widely used as journal bearings due to their superior wear properties (Barhust 1989; Çuvalcı and Baş 2004; Zeren 2007). Some metal bearings provide these properties. In this study, friction coefficient, temperature values and wear losses of bearing-journal samples were determined by wearing (Atik *et al* 2001; Ünlü and Atik 2007) on radial journal bearing wear test rig designed specially for this purpose manufactured by CuSn10 bronze, CuZn30 brass, ZnAl zamac, AlCuMg2 duralumine, and SnPbCuSb white metal for Cu, Zn, Al, and Sn–Pb based alloys. These alloys are especially used in automotive and machine element applications as journal bearing materials (Ünlü 2004).

2. Experimental

2.1 Preparation of experimental materials

In this study, CuSn10 bronze, CuZn30 brass, ZnAl zamac, AlCuMg2 duralumine, and SnPbCuSb white metal

specimens were used as journal bearing and SAE 1050 was used as shaft. The chemical composition of the journal materials used in the experiments is given in table 1. The chemical composition of the bearings materials used in the experiments is given in table 2. Dimensions of bearing specimens were as follows: inner diameter $10^{+0.05}$ mm, width 10 mm, and outer diameter, 15 mm.

The specimens were worn by radial journal bearing wear test rig under lubricated condition. The wear losses were measured under lubricated conditions of 20 N loads, 1500 rpm ($v = 0.785$ m/s velocity) and every 30 min for 2.5 h (7065 m sliding distance). Lubricating was accomplished by using SAE 90 gear oil. The microstructures of wear surfaces were photographed using optical and scanning electron microscope.

Tensile, compressive, notch impact, three-point bending, radial fracture and hardness were performed using ALŞA type tensile test rig depending on TS-138, and TS-269 (Turkish Standard) for mechanical properties. Moreover, the hardness was measured using a SADT HARTIP-3000 type.

2.2 Radial journal bearing wear test rig

Bearing materials in journal bearings were generally selected from materials which had lower wear strength than the shaft material, thereby lowering the wearing of the shaft significantly. For this reason, journal bearing wear test apparatus were designed to examine the wearing of bearing materials. In this study, a special bearing wear test apparatus has been designed to examine the wearing behaviour of bearing material and the shaft together. Therefore, it is possible to investigate different bearing and shaft materials and the effects of heat treatments on these materials. Such a mechanism provides wear of bearings rather than using standard methods as this is more appropriate (Atik *et al* 2001).

The system was formed by a weight applied by a rigid bar, a steel bar connected to the bearing from a distance and a comparator. Friction coefficient was determined from the friction force formed along the rotating direction of the bearing and from the movement of the steel bar connected to the bearing (Ünlü and Atik 2007). Radial wear test rig is illustrated in figure 1.

In the experiments under lubricated conditions, very little movement took place for high comparator's spring coefficient and low friction. Therefore, a tensile spring of $k = 0.004$ N/mm was connected on the opposite side to the comparator. The movements formed by the effect of the friction force were measured by this method.

Table 1. Chemical composition of journal materials (wt %).

Material	C	Si	Mn	P	S	Fe
SAE1050	0.51	0.3	0.7	0.04	0.05	Based

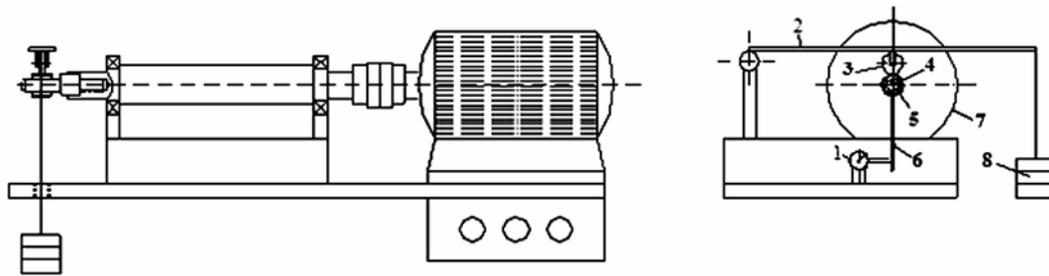


Figure 1. Radial journal bearing wear test rig (1. Comparator, 2. rigid bar, 3. load contact point (rolling bearing), 4. journal sample, 5. journal bearing samples, 6. plate bar, 7. motor, 8. loads).

Table 2. Chemical composition of bearing materials (wt %).

Materials	Sn	Pb	Sb	Al	Cu	Mg	Si	Fe	Mn	Zn	Cr
CuSn10	10	–	–	–	90	–	–	–	–	–	–
CuZn30	–	–	–	–	70	–	–	–	–	30	–
ZnAl	–	–	–	5	–	–	–	–	–	95	–
AlCuMg2	–	–	–	Based	3.8	1.2	0.5	0.5	0.3	0.25	0.1
SnPbCuSb	80	3	11	–	6	–	–	–	–	–	–

Table 3. Roughness of bearing materials.

Roughness (μm)	CuSn10	CuZn30	ZnAl	AlCuMg2	SnPbCuSb
Before wear	1.61	2.5	1.01	3.51	1.33
After wear	1.03	1.85	1.12	5.21	2.62

3. Results and discussion

3.1 Surface roughness properties

Values of surface roughness before and after wearing process are shown in table 3. These values of surface roughness, CuSn10 and CuZn30, decreased and the other bearings increased after wear tests. These tests were performed on Mitutoyo-CE surface roughness test rig.

3.2 Wear properties

Friction coefficient, bearing temperature, bearing and journal weight loss values are given in figures 2–6. The friction coefficient–time variation of bearings is shown in figure 2. The temperature–time variation of bearings is given in figure 3. The wear losses of bearing–time variation of bearings are shown in figure 4. The wear losses of journal–time variation of bearings are shown in figure 5. The wear rate values of bearings depending on materials are shown in figure 6. Friction coefficient was determined as a function of normal and friction force. The highest friction coefficients and bearing temperatures occurred in CuSn10 and CuZn30 bearings, whereas the lowest friction coefficients and bearing wear losses

occurred in other ZnAl, AlCuMg2 and SnPbCuSb bearings. The highest journal weight loss occurred in CuZn30 and AlCuMg2 bearings, whereas the lowest journal wear loss occurred in ZnAl and SnPbCuSb bearings. The highest bearing wear rate occurred in CuSn10 and CuZn30 bearings, while the lowest bearing wear rate occurred in ZnAl bearing.

Pürçek (1994), Pürçek *et al* (1999), Savaşkan *et al* (2002) and Çuvalcı and Baş (2004) investigated tribological properties of Zn–Al based journal bearings. They reported that these bearings had better tribological properties than those of bronze bearings. They determined the friction coefficient as ~ 0.02 at zinc–aluminum bearings. Rapoport *et al* (2002) and Gronostajski *et al* (2002) determined the friction coefficient of ~ 0.08 in bronze bearings. Türk *et al* (2007) determined the friction coefficient of ~ 0.25 , wear rate of 25 mg/km in SAE 660 bronze bearings at 0.5 m/s sliding speed and 30 N loads. In these studies, they reported that the wear rate increased with increasing applied load, and decreased with increasing sliding distance.

The differences in our results and those of other previous studies may be attributed to the fact that their materials were different from our materials. In addition, our results show that radial journal bearing test rig gives more accurate measurements.

3.3 Mechanical properties

Mechanical properties of copper based bronze, brass and aluminum based duralumin bearing materials generally occurred than those of zinc based zamac and tin-lead based white metal bearing materials. Hardness of these bearing specimens was found to be around 100 HB. Results of mechanical tests are given in table 4.

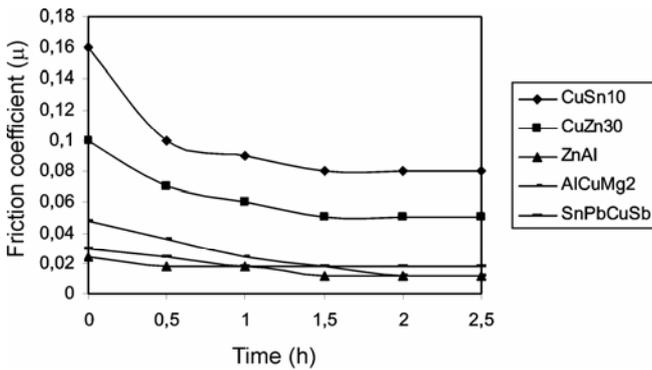


Figure 2. Friction coefficient–time variation of metal bearings.

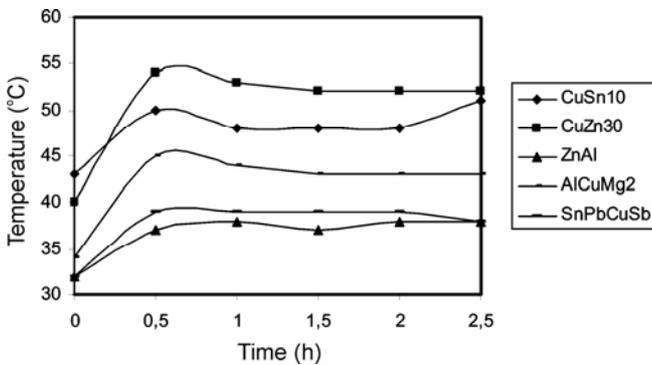


Figure 3. Temperature–time variation of metal bearings.

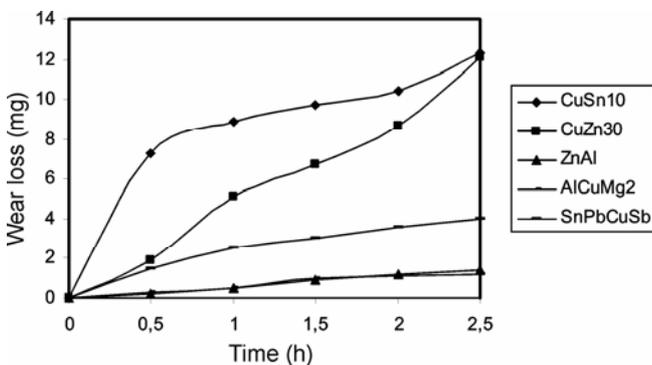


Figure 4. Wear losses bearing–time variation of metal bearings.

3.4 Microstructure properties

The wear surfaces in the specimens were examined using the optical (Hund Wetzlar CCD-290) and scanning electron microscope (Jeol JSM-6060). Microstructures of wear surface of metal bearings are presented in figure 7. SEM microstructures of wear surfaces of metal bearings are shown in figure 8. Homogen and small wear tracks were present in bronze bearing, and big wear tracks occurred in brass bearing. Microfractures occurred in zamac bearing. Huge wear tracks occurred in duralumin bearing due to different element phases. Wear tracks occurred apparently on friction orientation in white metal bearing (figures 7–8).

Pürçek (1994), Pürçek *et al* (1999), Savaşkan *et al* (2002) and Çuvalcı and Baş (2004) observed micro fractures in Zn based bearings. They have observed big wear tracks in bronze bearings. Rapoport *et al* (2002), Gronostajski *et al* (2002) and Türk *et al* (2007) have observed homogen and small wear tracks in bronze bearings. In this study, similar wear tracks were observed at medium loads.

SEM microstructure of tensile fracture surfaces of metal bearing materials are shown in figure 9. As can be seen in tensile fracture surfaces, fractures in bronze, brass

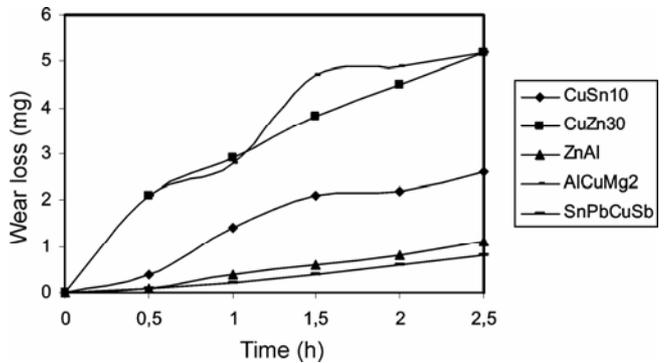


Figure 5. Wear losses journal–time variation of metal bearings.

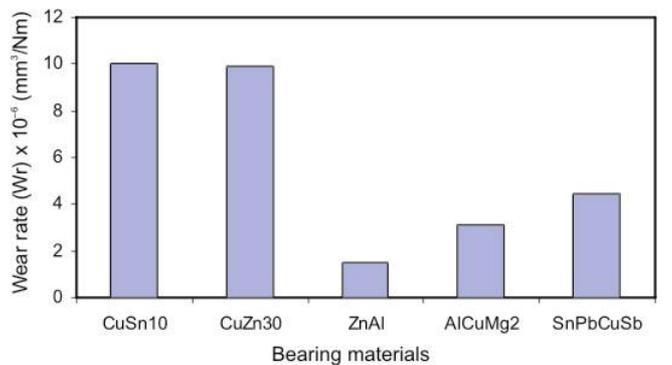
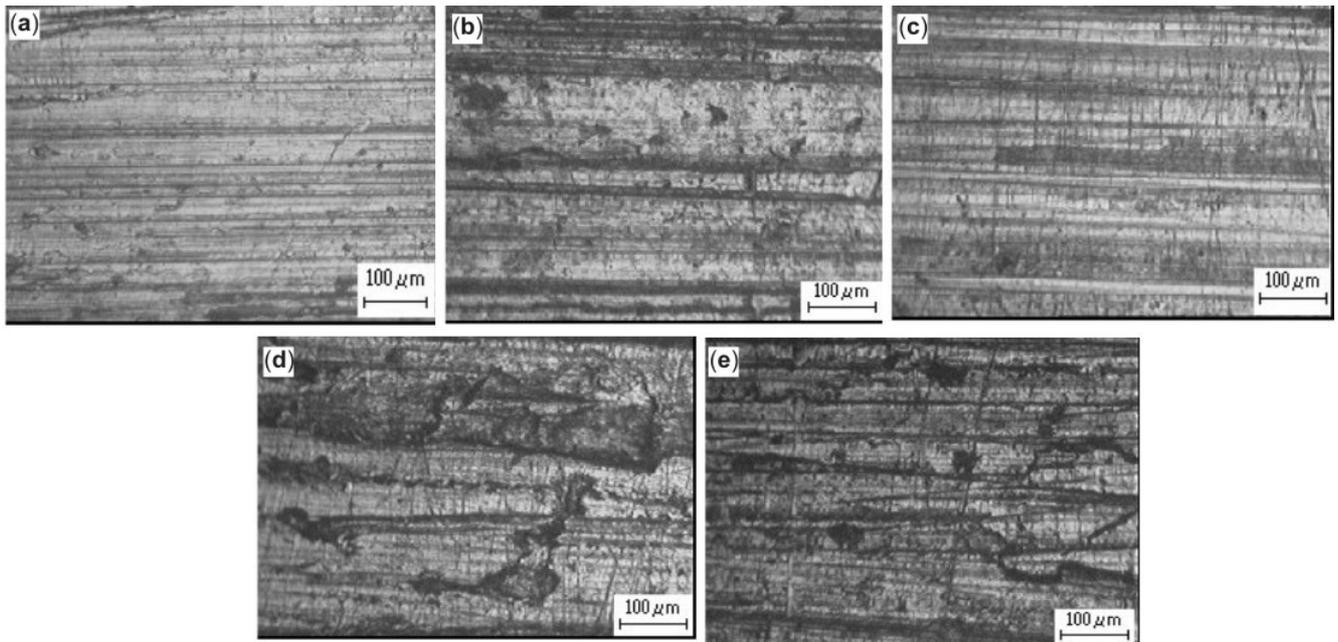
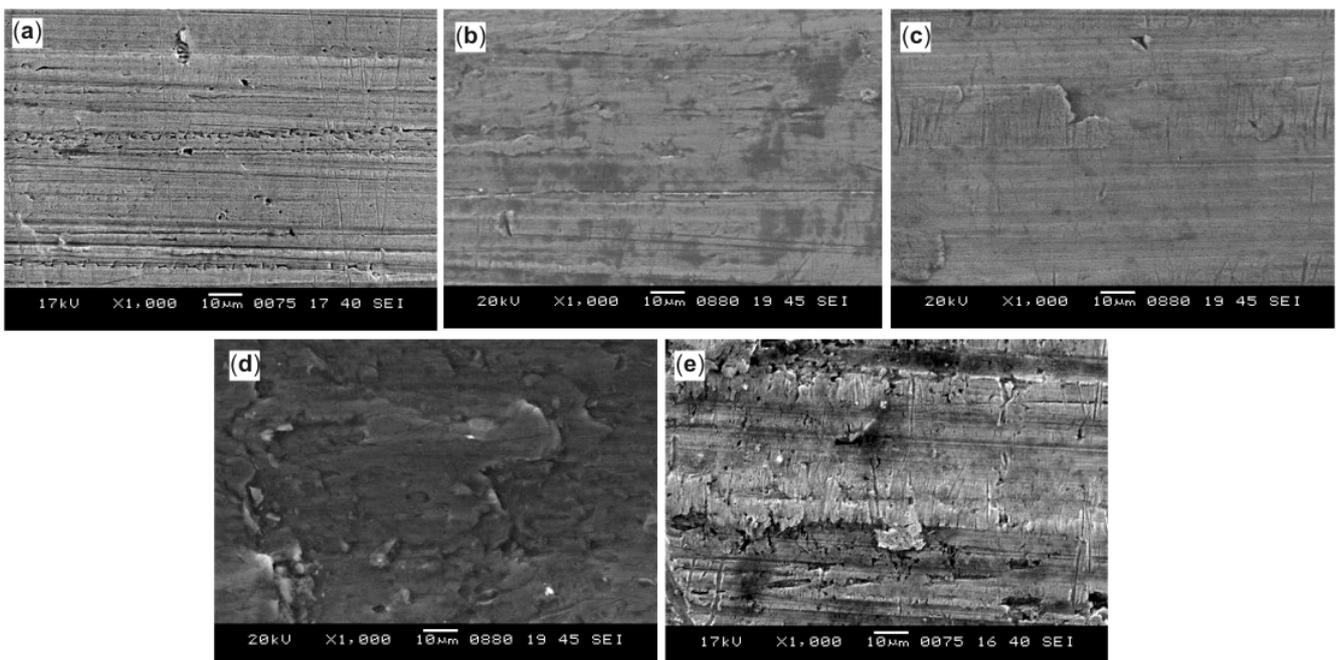


Figure 6. Comparison of wear rates of bearing materials.

Table 4. Mechanical properties of bearing materials.

Materials	Yield strength, $R_{p0.2}$ (MPa)	Tensile strength, R_m (MPa)	Break strength, σ_b (MPa)	Elongation (% ϵ)	Compressive strength (σ_c) (MPa)	Notch impact strength (J)	Bending angle (α^0)	Hardness (HB)	Radial strength fracture (σ_{fr}) (MPa)
CuSn10	260	370	280	16	1200	16	125	100	83
CuZn30	450	500	480	16	1000	14	140	120	105
ZnAl	190	210	200	3	750	3	180	70	16
AlCuMg2	205	340	320	23	668	50	135	84	81
SnPbCuSb	70	100	100	3.5	224	3	180	30	3

**Figure 7.** Microstructure of wear surfaces of metal bearings (a) CuSn10, (b) CuZn30, (c) ZnAl, (d) AlCuMg2 and (e) SnPbCuSb ($\times 100$).**Figure 8.** SEM microstructure of wear surface of metal bearings: (a) CuSn10, (b) CuZn30, (c) ZnAl, (d) AlCuMg2 and (e) SnPbCuSb ($\times 1000$).

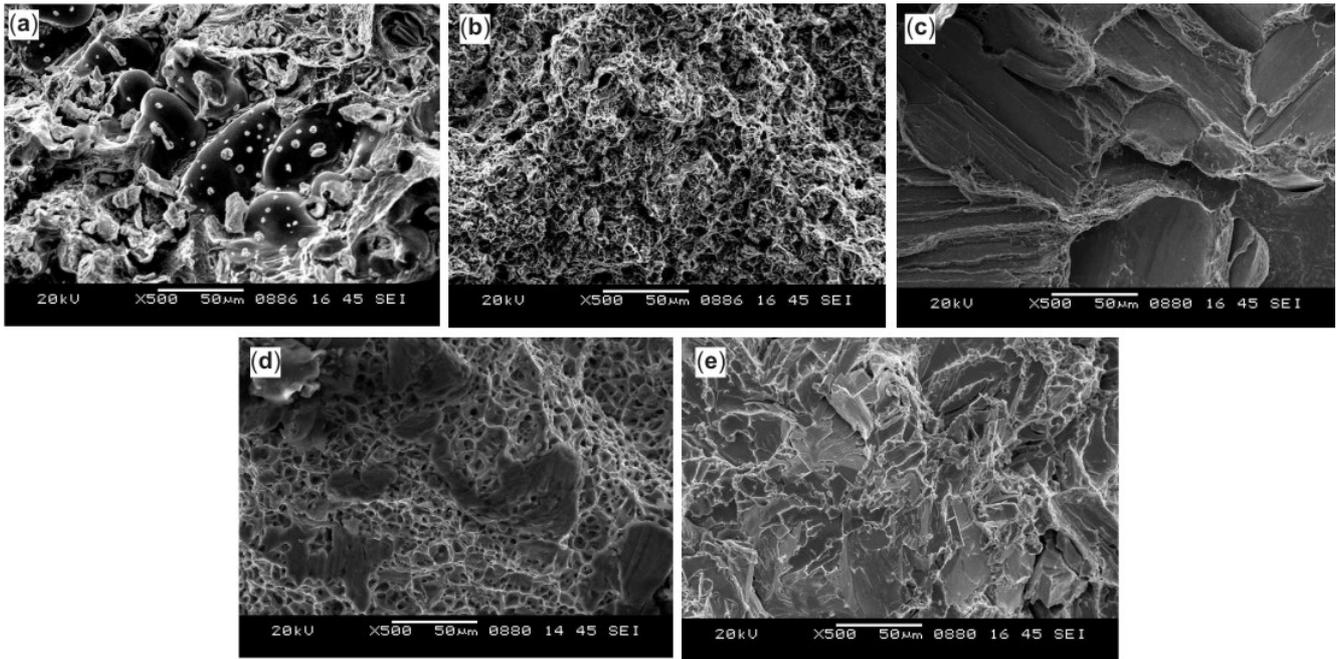


Figure 9. SEM microstructure of tensile fracture surface of metal bearing materials: (a) CuSn10, (b) CuZn30, (c) ZnAl, (d) AlCuMg2 and (e) SnPbCuSb ($\times 500$).

and duralumin bearing materials occurred as thinly grained, while zamac and white metal bearing materials had thick fractures.

4. Conclusions

We conclude that journal bearings manufactured from metal based materials may be effectively used in the industry due to better tribological and mechanical properties. In this study, tribological and mechanical properties of journal bearings manufactured by metals were investigated. The following conclusions can be drawn:

- (I) Post wear values of surface roughness decreased in CuSn10 and CuZn30 and increased in other bearings.
- (II) The highest friction coefficient and bearing temperature occurred in CuSn10 and CuZn30 bearings, whereas the lowest friction coefficient and bearing weight loss occurred in other ZnAl, AlCuMg2 and SnPbCuSb bearings. The highest journal weight loss occurred at CuZn30 and AlCuMg2 bearings.
- (III) The highest bearing wear rate occurred in CuSn10 and CuZn30 bearings, and the lowest bearing wear rate occurred in ZnAl bearing.
- (IV) The mechanical properties of CuSn10, CuZn30 and AlCuMg2 bearing materials were better than those of ZnAl, and SnPbCuSb bearing materials.

References

Atik E, Ünlü B S and Meriç C 2001 *Design of radial journal bearing wear test rig, Conference of Mach. Mater. and Technol.* (in Turkish) (Turkey), 2 pp 98–103

- Backensto A B 1990 *Effects of lubricants on the properties of copper-tin powders and compacts, Advances in P/M, Proc. of PM conf., APMI, N. Jersey*, pp 303–314
- Barhurst R J 1989 Guidelines for designing zinc alloy bearings—a technical manual, Soc. Auto Eng., Paper no: 880289
- Çuvalcı H and Baş H 2004 *Tribol. Int.* **37** 433
- Dawson D 1998 *History of tribology* (London: Profes. Eng. Pub.), p. 768
- Enomoto Y and Yamamoto T 1998 *Trib. Lett.* **5** 13
- Eyre T S 1991 *Surf. Eng.* **7** 143
- Gronostajski J, Chmura W and Gronostajski Z 2002 *J. Mater. Proc. Technol.* **125–126** 483
- Hanna M D, Carter J T and Rashid M S 1997 *Wear* **203–204** 11
- Haque M M and Sharif A 2001 *J. Mater. Proc. Technol.* **118** 69
- Harmsen M, Laufer E and Masounave J 1996 *Wear* **192** 128
- Lepper K, James M, Chashechkina M J and Rigney D A 1997 *Wear* **203–204** 46
- Liu Y L, Kang S B and Kim H W 1999 *Mater. Lett.* **41** 267
- Niinomi M, Fukunaga K and Takeda J 1997 *Mater. Sci. Forum* **331–337** 1519
- Paulo D 2000 *J. Mater. Proc. Technol.* **100** 273
- Prasad B K 1997 *Metal. Trans.* **28** 809
- Prasad S V and Rohatgi P K 1987 *J. Metals* **22**
- Pratt G C 1973 *Inter. Metall. Rev.* **18** 23
- Pürçek G 1994 *Investigation of tribological properties Zn–Al based journal bearings*, Master thesis, Karadeniz Technical University, Trabzon, Turkey (in Turkish)
- Pürçek G, Küçükömeroğlu T and Savaşkan T 1999 *Eng. and Mach.* **443** 35
- Rapoport L, Leshchinsky V, Lvovsky M, Labsker I, Volovik Y and Tenne R 2002 *Tribol. Int.* **35** 47
- Savaşkan T, Pürçek G and Murphy S 2002 *Wear* **252** 693
- Schatt W and Wieters K P 1997 *Powder metallurgy, Proc. mater. EPMA* (Shrewsbury, UK) p. 492

- Schmidt R F and Schmidt D G 1993 *Selection and application of copper alloy castings, ASM handbook II*, pp 3446–3557
- Sharma S C, Girish B M, Kamath R and Satish B M 1998 *Wear* **219** 162
- Türk A, Kurnaz C and Şevik H 2007 *Mater. Design* **28** 1889
- Ünlü B S 2004 *Determination of usability of boronized ferrous based materials as bearing and tribological properties in journal bearings*, PhD thesis, Celal Bayar University, Manisa, Turkey (in Turkish)
- Ünlü B S and Atik E 2007 *Mater. Des.* **28** 973
- Upadhyaya A N, Mishra S and Ojha S N 1997 *J. Mater. Sci.* **32** 3227
- Zeren A 2007 *Mater. Des.* **28** 2344