

Nano-molecular Junctions on STM Tips

Chun Huang*, Jianshu Yang

[+Show more](#)


Nano-Micro Letters, March 2011, Volume 3, Issue 1, pp 1-5

Publication Date (Web): March 31, 2011 (Article)

DOI:10.3786/nml.v3i1.p1-5

 *Corresponding author. E-mail: huangchun0713@hotmail.com
[Abstract](#)
[Full Text Html](#)
[PDF w/ Links](#)
[Export Citation](#)
[Figures](#)
[SHARE](#)

Abstract

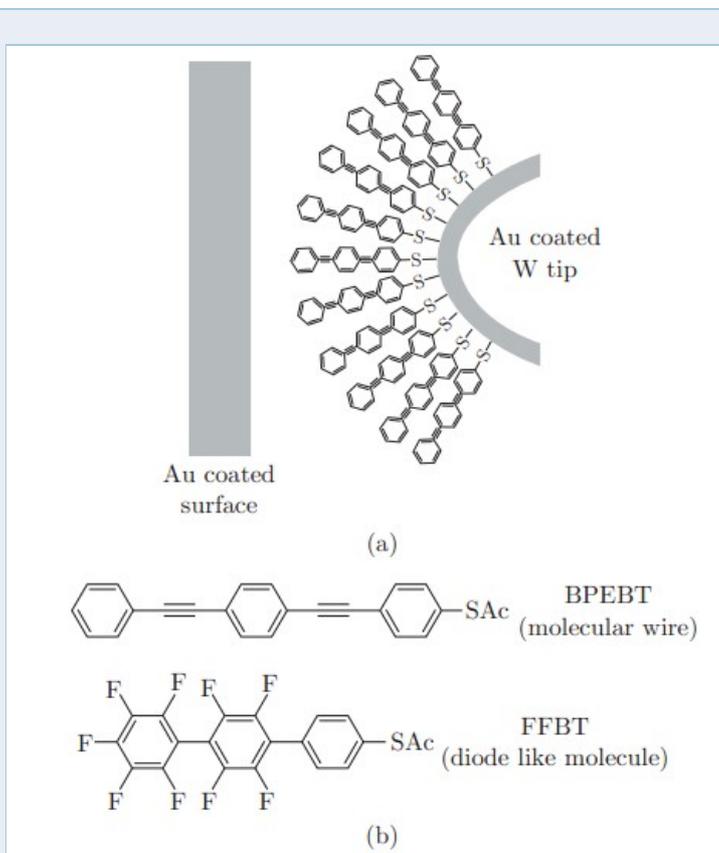

We present a technique for metal-organic-metal junctions, which contain ten or fewer conjugated molecules between each of such junction, and the investigation of the I-V response of these junctions. The junctions are made by self assembling thiolated molecules onto gold coated tips for use in scanning tunneling microscopy. We show that this easy technique probes the qualitative properties of the molecules. Current-voltage characteristics of a Tour wire and a new molecular rectifier are presented.

Keywords

STM; Junction; I-V response; Molecules; Tour wire

[Full Text Html](#) [References](#) [Citation Information](#) [History](#)

Introduction

Since the use of molecules for electronics was first described theoretically in the 1970s [1], numerous experiments have been conducted with scanning tunneling microscopy (STM), [2] conducting atomic force microscopy (AFM) [3] and the break junction [4] to probe their electronic properties. Molecules, connected to two metallic electrodes, can act as diodes, configurable

Browse By Issue

 Choose a Volume
[List of Issues](#)

Key topics

I-V response

Junction

Molecules

STM

Tour wire

Search articles by

 Chun Huang

 Jianshu Yang

Articles from this Issue

- Volume 3 Issue 1
- Efficient CNTFET-based Ternary Full Adder Cells for Nanoelectronics
- Synthesis and electrical properties of TiO₂ nanoparticles embedded in polyamide-6 nanofibers via electrospinning
- Thermodynamic and kinetic analysis of low-temperature thermal reduction of graphene oxide
- High-performance Li-ion batteries and supercapacitors base on Prospective 1-D nanomaterials
- Shape-controlled Synthesis of Porous SnO₂ Nanostructures via Morphological Conserved Transformation from SnC₂O₄ Precursor Approach
- Synthesis and photocatalytic activity of Fe-doped TiO₂ supported on hollow glass microbeads
- Synthesis and photocatalytic activity of one-dimensional CdS@TiO₂ core-shell heterostructures
- Synthesis and Thermal Behavior of Metallic Cobalt Micro and Nanostructures
- Hydrothermal Synthesis and Characterization of PEG-Mn₃O₄

memory devices, single-molecule rectifiers, transistors, or show negative differential resistance [5].

Electron transport through the molecular junction is determined not only by the intrinsic electronic structure of the molecule but also the metal-molecule contacts [6-9]. A good electrical contact between a molecule and a conducting substrate is a chemical bond, usually achieved with sulfur or selenium bound to gold [10]. In principle it is easy to take advantage of this concept to self assemble molecules at one electrode and make molecular junctions with a scanning probe tip. For instance, transport through single or at most a few molecules on a gold surface is observed with STM [11] using the tip as a counter electrode. Cui et al. [12] used thiol groups to bond to a gold base electrode and a gold nanoparticle top electrode. Reichert et al. [13] introduced small molecules between the electrodes in a mechanically controllable break junction. Zhitenev et al. [14] made contact to the molecule with a gold-coated AFM tip, so that the molecule is covalently bonded to gold at both ends.

In this work, we investigated an easy technique for fabricating and studying molecular nanojunctions using an STM. Compared to conventional molecule junctions realized in STM measurements, we adopt inverse junction geometry by assembling molecules onto a gold-coated tungsten STM tip, which allowed us to investigate the I-V curves at room temperature. This is actually challenge for normal methods [2, 3]. The tip is brought into contact with a clean gold surface and the current-voltage (I-V) characteristics measured. A schematic of this configuration is shown in Figure 1(a). We present results on I-V characteristics of two different molecules, shown in Figure 1(b), namely 4,4'-bis(phenylethynyl)-benzenethiolate (BPEBT) and 4-nonafluorobiphenyl-benzenethiolate (FFBT). Here, BPEBT could be considered as a molecular wire while FFBT is a diode-like molecule due to the electron withdrawing effect of fluorine atoms.




Figure 1 (a) Schematic of the junction geometry used. Molecules self assembled onto a gold coated STM tip are brought up to a Au(111) surface. (b) Schematic structures of the molecules investigated. BPEBT is a molecular wire. FFBT is a molecular diode.

Experimental

As shown below, reproducible I-V curves for the BPEBT wire and asymmetric I-V indicating rectifying behavior for FFBT were obtained at room temperature. This shows the utility of the inverse molecule junction technique for scanning tunneling spectroscopy (STS) measurement of organic molecules, in which the local measurement of the tunneling current versus tip-sample bias (I-V) curve were performed with a certain tip to substrate distance. We found the I-V characteristics, obtained by probing a self assembled monolayer of the same molecules on a gold substrate by a bare STM tip had the same form as the data shown below, but exhibited significantly higher noise. It should be emphasized at the outset that the method is only suited to qualitative assessment of the molecule I-V characteristics because the number of molecules in the junction and the pressures acting on the molecules [15] are not known. We therefore consider this technique as a quick method for testing the general I-V behavior of a number of molecules.

The experiments were carried out in an Omicron MULTIPROBE S ultrahigh vacuum (UHV) STM system with a base pressure better than 8×10^{-9} Pa. The substrate used was gold (111) film deposited by thermal evaporation onto freshly cleaved mica. Prior to deposition the mica was degassed for 6 h at 450°C in vacuum. The gold deposition rate was 0.1 nm/s and the thickness of gold film is typically 70nm. After the film deposition, the sample was kept in the vacuum chamber for another 30 min at 500 °C for annealing of the surface.

The STM tip was made by chemical etching of a 0.25mm diameter tungsten wire in 2 M NaOH. Freshly etched tungsten tips were coated with gold using the same methodology described above. The two types of molecule (BPEBT and FFBT) were then chemically bonded to the tips. All molecules consist of a rigid backbone with thiol groups on one end to form stable covalent bonds to gold electrodes. The length of the molecules is around 2 nm. Self-assembled films on the tip were obtained by immersing the gold-coated tips in 1mM BPEBT or FFBT in tetrahydrofuran (THF) solution, with a drop of ammonium hydroxide added to displace the acetyl group [16]. The tips were left in solution for around 21 hours, after which they were thoroughly rinsed with THF and then ethanol to remove any physisorbed material. The prepared tips were immediately introduced into the UHV STM chamber. An atomically flat area of the sample without defects and steps was chosen for experimentation.

Results and Discussions

Figure 2 shows IV curves obtained in UHV at room temperature for the Tour wire. The I-V curves are consistent with the published literature, with the current at 0.5 V being 10pA, the approximate value reported in the literature for a Tour wire [17]. Therefore, we can be confident that very few molecules are being probed. Since the HOMO and LUMO for BPEBT are 5.06 and 2.72 eV respectively, and the work function of Au is 5.1 eV, there is good alignment of the Fermi level with the HOMO of the molecule. Therefore the BPEBT molecule should act as a simple wire and exhibit no strong IV asymmetry [18-21]. A slight

Nanocomposite

- Nano-molecular Junctions on STM Tips

Related Articles

Browse

Abstract

Keywords

Introduction

Experimental

Results and Discussions

Conclusion

References

To Bottom

asymmetry in the data of Figure 2 is attributable to the small asymmetry in the barriers at the two ends of the molecule, i.e. one end is thiolated and bonded to the gold coated STM tip and the other (un-thiolated) end is in proximity to the gold substrate. A question naturally arises as to whether a vacuum tunneling gap exists between the molecule and the gold substrate. Current-distance (*I*-*Z*) curves show that the molecule is in contact with the gold substrate, as discussed below for FFBT.




Figure 2 I-V characteristics of the Tour wire BPEBT, taken at STM conditions of sample bias $V_s=3.0V$ and tunnel current $I_t=0.6nA$. The data shows 19 superimposed IV curves with the spread in data being around 0.05nA at +2V. The voltage axis is the sample bias.

Data for the FFBT molecule is shown in Figures 3 and 4. Figure 3a shows the most common current – distance (*I*-*Z*) curves observed for FFBT with an exponential dependence of the current on the tip sample separation. Less common were quasi-linear *I*-*Z* curves (e.g. Figure 3b) in which abrupt changes in current are observed, presumably arising from changing tip conditions. The abrupt changes may reflect a cross over to mechanical contact but this cannot be verified. In both cases a large displacement is needed (1 to 2nm) to change the current from 0.2 to 30nA. Given that the molecules are ~2nm in length one expects that if the indentation is too large then the molecules will be grossly influenced by the applied pressures. This is supported by the *I*-*V* data which shows considerable variability if the tunnel current control value (I_t) is set larger than $I_t \sim 10nA$.




Figure 3 Current versus relative tip-sample distance (*I*-*Z* curve) for the FFBT molecule. The STM control condition, which equates to the relative distance of $Z=0nm$, is sample bias $V_s=2.6V$ and tunnel current $I_t=0.2 nA$. The current amplifier saturates at 33nA.

We conclude from studying series of *I*-*V* and *I*-*Z* data that for consistent IV data the *I*-*Z* curve should be reproducible (no abrupt changes) to ensure a reproducible tip condition and the *I*-*V* should be taken at only moderate indentation to ensure a good mechanical contact with no vacuum gap and minimal tip damage. The best indentation will depend on the molecule under test. For the FFBT and BPEBT molecules the preferred indentation for *I*-*V* measurement appears to be $I_t \sim 5 nA$, whereas at control currents $I_t = 0$ to $\sim 2nA$ there is a vacuum barrier or weak mechanical contact (as discussed below for the IV data) and for $I_t > 10nA$ the mechanical contact is excessive.

Figure 4 shows three sets of *I*-*V* curves of the molecule FFBT which is expected to exhibit diode properties [21-24] in the absence of conformation change. The spectra are taken at different tip-sample separations on the corresponding *I*-*Z* curve of Figure 3. We first discuss Figures 4a and 4b which show strong rectification. The *I*-*V* shown in Figures 4a and 4b fit the exponential functional form expected for a vacuum tunnel barrier and we conclude that a vacuum tunnel gap is present. The asymmetric *I*-*V* nature in this case arises because the charge injection barrier will be different for either positive or negative sample polarity. In addition, there is a vacuum tunneling barrier at one end of the molecule.




Figure 4 (a)-(c) *I*-*V* curves for the FFBT molecule taken at different STM control current ($I_t = 0.4, 1.6, 4.4 nA$) with sample bias $V_s = 2.6V$. The STM control conditions correspond to different tip-sample separation (see Figure 3). The voltage axis is the sample bias.

In contrast, we find that the *I*-*V* for FFBT in Figure 4c is non-linear and a power-law dependence on the voltage provides a best fit. The power law dependence of the current on the voltage in the *I*-*V* and the *I*-*Z* data of Figure 3 suggest that the molecule is in good contact with the gold substrate. The *I*-*V* data again shows rectification, although with a smaller rectification ratio than in Figures 4a and 4b. Since the electrical contact appears good the rectification may arise from the different charge injection barriers for positive or negative sample polarity (as above) or from asymmetric alignment of energy levels across the molecule. To elaborate, we follow the discussion of Williams and co-workers [24] who outline a simple model of molecular rectification, where a single electroactive unit is positioned asymmetrically with respect to electrodes and the HOMO and LUMO are positioned asymmetrically with respect to the Fermi level. In FFBT, the required conditions for rectification by an asymmetric barrier and asymmetric arrangement of the electrode Fermi energy with respect to the HOMO and LUMO are well

met, since the HOMO and LUMO are 5.75 and 2.84 eV respectively, and the Au work function is 5.1 eV. The experimental geometry clearly yields asymmetric injection barriers at the two ends of the molecule. The tip coated with molecules acts as one electrode since the molecules are attached by chemical bonding. The other end of the molecule is not chemically bound to the gold substrate and such an arrangement gives an asymmetric injection barrier at the two ends of the molecule. All the requisite conditions for molecular rectification [24] are thus met. Our demonstration of rectification by the FFBT molecules is a confirmation of this effect.

We finally estimate the number of molecules in the junction with the tip and surface in contact. The self assembled films form compact molecular layers. The Tour wire in particular is a short and rigid molecule and the self-assembled film is expected to be mechanically stiff. Given the above we assume an elastic contact at the junction. For a rounded tip of curvature ~ 10 nm the radius of the tip-sample interaction area will be ~ 1 nm for an elastic contact [25]. The spacing between molecules in the self assembled films is ~ 0.5 nm and thus of order ~ 10 molecules or less would exist in the contact zone and contribute to the measured current.

Conclusion

In conclusion, we present a simple technique to investigate nanojunctions with a finite number of molecules, by self-assembling them on a gold coated STM tip. The STS measurements were conducted at room temperature which was a challenge for traditional methods [2, 3] that used STM tips to locate the molecules self-assembled on gold surface. Results are presented for a Tour wire and a new molecule (FFBT) exhibiting rectification. The results demonstrate that the technique indeed measures the I-V properties of the molecules provided one ensures good mechanical contact by appropriate setting of the tip-sample separation. The method should be considered as a qualitative approach only.

References

- [1] Aviram and M. A. Ratner, Chem. Phys. Lett. 29, 277 (1974). [http://dx.doi.org/10.1016/0009-2614\(74\)85031-1](http://dx.doi.org/10.1016/0009-2614(74)85031-1)
- [2] C. Joachim, J. K. Gimzewski and A. Aviram, Nature 408, 541 (2000). <http://dx.doi.org/10.1038/35046000>
- [3] J. Chen, M. A. Reed, A. M. Rawlett and J. M. Tour, Science 286, 1550 (1999). <http://dx.doi.org/10.1126/science.286.5444.1550>
- [4] C. M. Fisher, M. Burghard, S. Roth and K. Klitzing, Appl. Phys. Lett. 66, 3331 (1995). <http://dx.doi.org/10.1063/1.113747>
- [5] S. P. Collier, E. W. Wong, M. Belohradsky, F. M. Raymo, J. F. Stoddart, P. J. Kuekes, R. S. Williams and J. R. Heath, Science 285, 391 (1999). <http://dx.doi.org/10.1126/science.285.5426.391>
- [6] M. A. Reed, J. Chen, A. M. Rawlett, D. W. Price and J. M. Tour, Appl. Phys. Lett. 78, 3735 (2001). <http://dx.doi.org/10.1063/1.1377042>
- [7] A. Vilam, J. Ghabboun and D. Cahen, J. Phys. Chem. B 107, 6360 (2003). <http://dx.doi.org/10.1021/jp026779b>
- [8] A. Vilan, C. Pejoux and D. Cahen, Adv. Funct. Mater. 17, 795 (2002). <http://dx.doi.org/10.1002/adfm.200290009>
- [9] L. Jones and J. M. Tour, Polym. Prepr. 36, 233 (1995).
- [10] S. Datta, W. D. Tian, S. H. Hong, R. Reifenberger, J. I. Henderson and C. P. Kubiak, Phys. Rev. Lett. 79, 2530 (1997). <http://dx.doi.org/10.1103/PhysRevLett.79.2530>
- [11] K. W. Hipps, Science 294, 536 (2001). <http://dx.doi.org/10.1126/science.1065708>
- [12] X. D. Cui, A. Primak, X. Zarate, J. Tomfohr, O. F. Sankey, A. L. Moore, T. A. Moore, D. Gust, G. Harris and S. M. Lindsay, Science 294, 571 (2001). <http://dx.doi.org/10.1126/science.1064354>
- [13] J. Reichert, R. Ochs, D. Beckmann, H. B. Weber, M. Mayor and H. V. Löhneysen, Phys. Rev. Lett. 88, 176804 (2002). <http://dx.doi.org/10.1103/PhysRevLett.88.176804>
- [14] N. B. Zhitenev, A. Erbe and Z. Bao, Phys. Rev. Lett. 92, 186805 (2004). <http://dx.doi.org/10.1103/PhysRevLett.92.186805>
- [15] U. Durig, O. Zuger, B. Michel, L. Haussling and H. Ringsdorf, Phys. Rev. B 48, 1711 (1993). <http://dx.doi.org/10.1103/PhysRevB.48.1711>
- [16] J. M. Tour, L. Jones, D. L. Pearson, J. J. S. Lamba, T. P. Burgin, G. M. Whitesides, D. L. Allara, A. N. Parikh and S. V. Atre, J. Am. Chem. Soc. 117, 9529 (1995).

More in this Volume: [Synthesis and photocatalytic activity of one-dimensional CdS@TiO₂ core-shell heterostructures »](#)

[back to top](#)