

Lithium and magnesium isotopes fractionation by zone melting

D V Akimov, N B Egorov, A N Dyachenko, M P Pustovalova, I R Podoinikov

National Research Tomsk Polytechnic University, Tomsk, Russia

E-mail: egorov@tpu.ru

Abstract. The process of changing isotopic composition of the lithium and magnesium salts was studied by using the process of zone melting. It was founded in the paper that the process of separation of the lithium isotopes is more effective than for magnesium isotopes when the conditions of process were the same. The coefficients of isotopes separation were calculated and have the next value: $\alpha = 1.006$ for ^{26}Mg isotope and $\alpha = 1.0022$ for ^6Li isotope.

1. Introduction

Naturally occurring lithium is composed of two stable isotopes ^6Li (7.589 %) and ^7Li (92.411 %) [1]. Each of them is very important for nuclear energetics. The isotope of ^7Li is used as additive in the coolant of the first loop pressurized water reactor and also for production chemical reagents for nuclear energetics [2].

Naturally occurring magnesium is composed of three stable isotopes ^{24}Mg (78.992 %), ^{25}Mg (10.003 %) and ^{26}Mg (11.005 %) [3]. The isotope of ^{24}Mg is used for production radioisotope ^{22}Na [4]. Other isotopes ^{25}Mg and ^{26}Mg are used for biological labeling during the process of study the absorption and metabolism of magnesium in the human body.

Isotopes of lithium and magnesium are nonvolatile compounds. For this reason for separation of these isotopes we use the next methods: electromagnetic [5-6], crown ethers extraction [7-11], ion exchange [12-14], vacuum distillation [15], amalgam-lithium and amalgam-magnesium systems [16, 17] during precipitation from aqueous solutions [18, 19].

The process of zone melting is widely used for deep cleaning the different substances and for their production in single crystal form [20-23]. Also, this process can be used for separation isotopes such as H_2O and D_2O [24-26], the isotopes of boron, zinc, magnesium, lead and tin [27-32].

The purpose of this work is to investigate the process of changing isotope composition of lithium and magnesium during the process of zone melting of their salts.

2. Experimental part

2.1. Reagents

$\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ (analytical grade), $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$ and LiClO_4 were used. $\text{LiOH} \cdot \text{H}_2\text{O}$ (pure) and HClO_4 (pure) were used for synthesis $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$. The anhydrous lithium perchlorate LiClO_4 was obtained by dehydration of the $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$ at 200 °C for 3 hours. According to the results of X-ray diffraction analysis, the obtained salts were correspond to $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$ (PDF 00-008-0156) and LiClO_4 (PDF 30-0751).



2.2. Instrumentation

Investigations were conducted on samples with a length of 100 mm and a diameter of 3 mm. For preparing samples $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$, $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$ or LiClO_4 were heated until salt melted. After that a part of the melt was placed into a glass tube which was sealed at one end. When the process of zone melting was done, the glass tube was cut into samples, 10 mm in length. Then the samples were removed and dissolved in distilled water. After this, in the obtained solutions the isotope composition of the lithium or magnesium was determined. The analysis of isotope compositions was carried out on the mass spectrometer MX-1301T.

2.3. The process of zone melting

All experiments were carried out on the installation, which has five heating elements and five cooling elements (Figure 1). The main part of the installation was a platform with the heating elements placed at equal distance in the form of a ring, the inner diameter of which corresponds to the outer diameter of the glass tube. Power supply GW INSTEK PSH -10100 was used for regulating the temperature of the heating elements. Temperature was measured by using a chromel-alumel thermocouple. The cooling elements were installed between the heating elements.

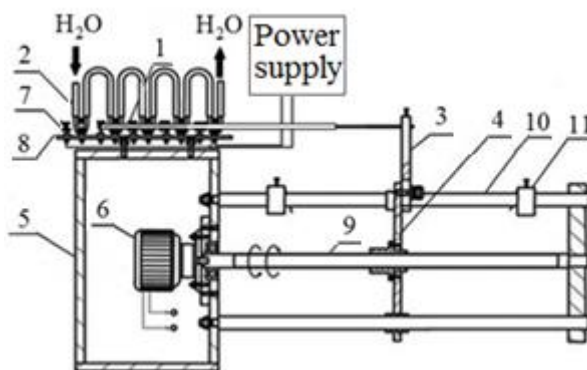


Figure 1. Installation for zone recrystallization
(1 – mixture of REEs; 2 – cooling element;
3 – rod; 4 – carriage; 5 – housing; 6 – stepper
motor; 7 – heating element; 8 – platform; 9 – shaft;
10 – guides; 11 – sensor).

Nichrome wire was used as the heating element. In Table 1 the temperatures of the heating elements for different work substances are presented. The length of the melt of the ingot was from 7 to 8 mm.

Table 1. The melting point of the work substances.

The work substance	The melting point, °C	Temperature of the heating elements, °C
LiClO_4	236	285 ± 15
$\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$	95	115 ± 5
$\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$	120	140 ± 5

3. Results and discussions

In the experiments with lithium the parameters of the process of zone melting were the following: the speed of the tube was 3 cm/h, the number of zone processes was equal to 30. The results of isotopic

analysis show that the isotopic composition of lithium in the work substances has change. The process of isotopes fractionation is more effective if we use $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$ as the work substance. The results of isotopic analysis of the lithium isotopes after the process of zone melting are shown in the Table 2. The coefficients of separation of the lithium isotopes are shown in Table 3.

Table 2. The isotopic composition of $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ in the initial zone of crystallization.

The work substances	The isotope content, %			
	^6Li		^7Li	
	the original composition	after the process of zone melting	the original composition	after the process of zone melting
LiClO_4	6.950 ± 0.01	7.32 ± 0.03	93.045 ± 0.01	92.68 ± 0.04
$\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$	6.955 ± 0.01	7.15 ± 0.02	93.050 ± 0.02	92.85 ± 0.03

Table 3. The coefficients of separation of the lithium isotopes.

The work substances	The coefficients of separation	
	$\alpha(^6\text{Li})$	$\alpha(^7\text{Li})$
LiClO_4	1.0019	0.9981
$\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$	1.0022	0.9978

The parameters of the process of zone melting of $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ were the same. The results of isotopic analysis of the magnesium isotopes after the process of zone melting are shown in the Table 4.

Table 4. The isotopic composition of $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ in the initial zone of crystallization.

The isotope content, %					
^{24}Mg		^{25}Mg		^{26}Mg	
the original composition	after the process of zone melting	the original composition	after the process of zone melting	the original composition	after the process of zone melting
79.58 ± 0.03	79.35 ± 0.04	9.8 ± 0.02	9.87 ± 0.04	10.62 ± 0.02	10.78 ± 0.04

The data obtained from the Table 4 shows that the isotopes ^{25}Mg and ^{26}Mg concentrate in the initial zone of crystallization and, also, the isotope ^{24}Mg moves with the melt zone and concentrates in the end of zone crystallization. The coefficients of separation of the magnesium isotopes are presented in Table 5.

Table 5. The coefficients of separation of the magnesium isotopes.

The coefficients of separation		
$\alpha(^{24}\text{Mg})$	$\alpha(^{25}\text{Mg})$	$\alpha(^{26}\text{Mg})$
0.9995	1.0002	1.0006

These results can be explained as follows. Burton, Prim and Slichter obtained the formula for the effective distribution coefficient [33]:

$$K = \frac{1}{1 + \left[\left(\frac{1}{K_0} \right) - 1 \right] e^{-f\delta/D}}, \quad (1)$$

where K_0 – the equilibrium distribution coefficient, f – the crystal growth rate, δ – the thickness of the diffusion layer in front of the crystallization front, D – the diffusion coefficient.

From this equation we can conclude that differences between the effective distribution coefficient K and the equilibrium distribution coefficient K_0 will be more significant if the value of the diffusion coefficient D is higher and the thickness of the diffusion layer in front of the crystallization front is smaller.

4. Conclusion

The distribution of lithium and magnesium isotopes was studied during the process of zone melting of their salts. During the process of zone melting the isotopes ^{25}Mg and ^{26}Mg concentrate in the initial zone of crystallization and, also, the isotope ^{24}Mg moves with the melt zone and concentrates in the end of zone crystallization. The coefficients of isotopes separation were calculated and have the next value: $\alpha = 1.006$ for ^{26}Mg isotope and $\alpha = 1.0022$ for ^6Li isotope. In the next work effectiveness of separation isotopes during the process of zone melting can be changed by using the other work substances, such as $\text{LiClO}_4 \cdot \text{H}_2\text{O}$ [34].

References

- [1] Qi H P, Tailor P D P, De Bievre P 1997 Calibrated Measurements of the Isotopic Composition and Atomic Weight of the Natural Li Isotopic Reference Material IRMM-016 *International Journal of Mass Spectrometry and Ion Processes* **171** 263–268
- [2] Report to the Ranking Member, Subcommittee on Oversight, Committee on Science, Space, and Technology, House of Representatives 2013 Stewardship of Lithium-7 Is Needed to Ensure a Stable Supply United States Government Accountability Office № GAO-13-716 31
- [3] Sabatier M, Arnaud M J, Kastenmayer P, Rytz A, Barclay D V 2002 Meal effect on magnesium bioavailability from mineral water in healthy women *Am. J. Clin. Nutr.* **75** 65–71
- [4] Wälti M K, Zimmermann M B, Walczyk T, Spinaz G A, Hurrell R F 2003 Measurement of magnesium absorption and retention in type 2 diabetic patients with the use of stable isotopes *Am. J. Clin. Nutr.* **78** 448–453
- [5] Gusev V M, Chkuaseli D V, Guseva M I 1957 Separation of germanium and magnesium isotopes in a small electromagnetic separator *The Soviet Journal of Atomic Energy* **3** 3 999–1005
- [6] Keim C P 1952 Electromagnetic separation of stable isotopes *Annu. Rev. Nucl. Sci.* **1** 263–292
- [7] Nishizawa K, Nishida T, Miki T, Yamamoto T, Hosoe M 1996 Extractive behavior of magnesium chloride and isotopic enrichment of magnesium by a crown ether *Separation Science and Technology* **31** 5 643–654
- [8] Kim D W 2001 Enrichment of magnesium isotopes by monoazacrown bonded merrifield peptide resin *Bull. Korean Chem. Soc.* **22** 6 570–574
- [9] Symons E A 1985 Lithium Isotope Separation: A Review of Possible Techniques *Separation Science and Technology* **20** 633–651
- [10] Kim D W, Kang B M 2001 Enrichment of magnesium isotopes by 2'-aminomethyl-15-crown-5 bonded Merrifield peptide resin *Journal of Radioanalytical and Nuclear Chemistry* **250** 291–294
- [11] Levkin A V, Basmanov V V, Demin S V, Tsivadze A Yu 1990 Segregation of magnesium isotopes at extraction with crown ethers *Russ. J. Phys. Chem.* **64** 5 1376–1377
- [12] Oi T, Yanase S, Kakihana H 1987 Magnesium Isotope Fractionation in Cation-Exchange Chromatography *Separation Science and Technology* **22** 11 2203–2215
- [13] Kim D W 2002 Separation of lithium and magnesium isotopes by hydrous manganese(IV) oxide *Journal of Radioanalytical and Nuclear Chemistry* **252** 3 559–563
- [14] Isupov V P, Mitrofanova R P, Chupahina L E 2001 Partition coefficients of lithium isotopes by chemical isotopic exchange *Chemistry for Sustainable Development* **9** 183–198
- [15] Pugachev Yu I, Rylov V S 1963 Segregation of magnesium isotopes at vacuum distillation

- Russ. J. Phys. Chem.* **37** 3 691–693
- [16] Allred V D, Cutler I B 1953 *Chemical methods for the separation of lithium isotopes* (Oak Ridge National Laboratory) 177
- [17] Chen D, Chang Z, Nomura M, Fujii T 1997 Isotope effects of magnesium in amalgam/organic solution systems *J. Chem. Soc. Faraday Trans.* **93** 14 2395–2398
- [18] Mavromatis V, Pearce C R, Shirokova L S, Bundelova I A, Pokrovsky O S, Benezeth P, Oelkers E H 2012 Magnesium isotope fractionation during hydrous magnesium carbonate precipitation with and without cyanobacteria *Geochimica et Cosmochimica Acta* **76** 161–174
- [19] Li W, Chakraborty S, Beard B L, Romanek C S, Johnson C M 2012 Magnesium isotope fractionation during precipitation of inorganic calcite under laboratory conditions *Earth and Planetary Science Letters* **333-334** 304–316
- [20] Yang G, Guan Y T, Jian F Y 2015 Zone Refinement of Germanium *Crystals Journal of Physics: Conference Series* **606** 012014
- [21] Sun D Y, He L W, Lian J Q 2015 Process for solar grade silicon production by molten salt electrolysis and zone melting *Journal of Materials Engineering* **43** 4 73–78
- [22] Yang G, Govani J, Mei H 2014 Investigation of influential factors on the purification of zone-refined germanium ingot *Crystal Research and Technology* **49** 4 269–275
- [23] Akimov D V, Egorov N B, Obmuch K V 2013 Separation of rare earth elements by zone recrystallization *Fundamental Research* **8** 3 529–533
- [24] Smith H A, Thomas C O 1959 The separation of mixtures of ordinary and heavy water by zone refining *J. Phys. Chem.* **63** 3 445–447
- [25] Herington E F G 1959 Zone melting with some comments on its analytical potentialities *Analyst* **84** 680–689
- [26] Kuhn W, Thürkauf M 1958 Isotopentrennung beim gefrieren von wasser und diffusionskonstanten von D und ^{18}O im Eis. Mit diskussion der möglichkeit einer multiplikation der beim gefrieren auftretenden Isotopentrennung in einer haarnadelgegenstromvorrichtung *Helvetica Chimica Acta* **41** 4 938–970
- [27] Makarov A V, Koreckay T V, Panchenkov G M 1962 About boron isotope separation zone melting *Russ. J. Phys. Chem.* **36** 391–393
- [28] Troitskii O A 1978 Fractionation of stable isotopes of metals by combined electric migration and zone melting *Phys. Stat. Sol. (a)* **48** 229–234
- [29] Troitskii O A, Spitsyn V I, Moiseenko M M, Tsiganov A D 1979 Fractionation of stable isotopes and impurities during zone recrystallization of metals and preparation of single crystals rich in individual isotopes *Phys. Stat. Sol. (a)* **54** 651–654
- [30] Akimov D V 2012 Preparation of isotopically enriched lead suitable for use in fast reactors *Russian Physics Journal* **55** 2/2 123–129
- [31] Egorov N B, Akimov D V, Gerin I I, Obmuch K V 2014 Fractionation of magnesium isotopes by using zone recrystallization *Russian Physics Journal* **57** 2/2 249–254
- [32] Andrienko O S, Egorov N B, Gerin I I 2007 Magnesium isotopes selection at recrystallization of $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ *Bulletin of the Tomsk Polytechnic University* **311** 3 67–69
- [33] Pfann V 1970 *Zone melting* (M: Mir)
- [34] Ivlev S I, Akimov D V, Egorov N B, Kraus F 2016 Synthesis and characterization of $\text{LiClO}_4 \cdot \text{H}_2\text{O}$ *Monatshfte fur Chemie* **147** 279–288