



LAWRENCE
LIVERMORE
NATIONAL
LABORATORY

Thermoelasticity at High Temperatures and Pressures for Ta

D. Orlikowski, P. Soderlind, J. A. Moriarty

December 13, 2004

Materials Multiscale Modeling II
Los Angeles, CA, United States
November 11, 2004 through November 15, 2004

Disclaimer

This document was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor the University of California nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or the University of California, and shall not be used for advertising or product endorsement purposes.

Thermoelasticity at High Temperatures and Pressures for Ta

Daniel Orlikowski, Per Söderlind and John A. Moriarty

Lawrence Livermore National Laboratory, University of California,

P.O. Box 808, Livermore, CA 94550, email: orlikowski1@llnl.gov

ABSTRACT

A new methodology for calculating high temperature and pressure elastic moduli in metals has been developed accounting for both the electron-thermal and ion-thermal contributions. Anharmonic and quasi-harmonic thermoelasticity for bcc tantalum have thereby been calculated and compared as a function of temperature ($<12,000$ K) and pressure (<10 Mbar). In this approach, the full potential linear muffin-tin orbital (FP-LMTO) method for the cold and electron-thermal contributions is closely coupled with ion-thermal contributions obtained via multi-ion, quantum-based interatomic potentials derived from model generalized pseudopotential theory (MGPT). For the later contributions two separate approaches are used. In one approach, the quasi-harmonic ion-thermal contribution is obtained through a Brillouin zone sum of the strain derivatives of the phonons, and in the other the anharmonic ion-thermal contribution is obtained directly through Monte Carlo (MC) canonical distribution averages of strain derivatives on the multi-ion potentials themselves. The resulting elastic moduli compare well in each method and to available ultrasonic measurements and diamond-anvil-cell compression experiments indicating minimal anharmonic effects in bcc tantalum over the considered pressure range.

Existing methods to calculate the thermoelastic moduli for a single crystal material include, for example, molecular dynamics[1] and Monte Carlo techniques[2] where only the ionic contribution is calculated, or the particle-in-a-cell method[3] where both electronic and ionic contributions (treated only approximately) are calculated. We present here a new methodology for calculating the high temperature and pressure elastic moduli that separates the Helmholtz free energy into cold, electronic and ionic contributions and makes a full calculation for each component. Two methods of calculating the ion-thermal contributions are presented and compared: one within the quasi-harmonic phonon approximation and the other being fully anharmonic. Both ion-thermal treatments produce similar results in the case of Ta indicating negligible anharmonic effects for the high pressure phase diagram for this metal.

For high temperatures ($300 \text{ K} \leq T \leq T_{melt}$) and pressures ($P < 10$ Mbar), we assume that the electron-phonon coupling is negligible for a metal and write the Helmholtz free energy as, $F(\Omega, T) = \Phi_o(\Omega, T = 0) + F_e(\Omega, T) + F_H(\Omega, T) + F_A(\Omega, T)$, where $\Phi_o(\Omega, T = 0)$ is the total energy of the electronic ground state, i.e. the frozen lattice, $F_e(\Omega, T)$ contains the electron-thermal contribution, $F_H(\Omega, T)$ holds the ion-thermal contribution, and $F_A(\Omega, T)$ has the anharmonic contributions. The specific volume Ω is the volume per atom. With this and through the definition of the isothermal elastic moduli $C_{ijkl}^T = \Omega^{-1} \partial^2 F / \partial \eta_{ij} \partial \eta_{kl} |_{T, \eta'}$, where η' indicates that all other strains are held fixed, the individual contributions to the elastic moduli are obtained, $C_{ijkl}^T = C_{ijkl}^o + C_{ijkl}^e + C_{ijkl}^{ion}$. For the C_{ijkl}^e term, temperature is incorporated into $F_e(\Omega, T) = U_e - TS_e$ through a broadening of the electron density of

states, $n(\epsilon, \Omega)$, via the Fermi-Dirac distribution, $f(\epsilon)$, and through the electronic entropy, $S_e(\Omega, T) = -k_B \int d\epsilon n(\epsilon, \Omega) \{f(\epsilon) \ln[f(\epsilon)] - (1 - f(\epsilon)) \ln[1 - f(\epsilon)]\}$. To calculate this term, the full-potential, linear muffin-tin orbital (FP-LMTO) electronic-structure method is used [4].

For the C_{ijkl}^{ion} contribution, we have implemented two different calculations to assess the anharmonic contribution: one within the quasi-harmonic (QH) approximation and one that is fully anharmonic (AH). Specifically for the QH method, following Wallace [5], the Helmholtz free energy for the lattice is written as a Brillouin zone and branch (κ) sum of the phonon frequencies ω_κ as $F_{ion} = \sum_\kappa 0.5 \hbar \omega_\kappa + \ln[1 - \exp(-\hbar \omega_\kappa / kT)]$. Therefore, to obtain C_{ijkl}^{ion} , strain derivatives of F_{ion} lead to a summation over the Brillouin zone of strain derivatives of the phonon frequencies. To compute the fully AH lattice contribution to the elastic moduli, we have extended previous MC work [2], where the strain derivatives of the partition function are taken while accounting for periodic boundary conditions. This leads to a canonical assemble average of these derivatives evaluated at thermodynamic equilibrium for a given Ω and T via a standard Metropolis, MC algorithm. Two to three runs for each Ω and T point were performed with a run lasting at least 1.5×10^6 MC-steps. In both ion-thermal methods, we have used a quantum derived, multi-ion potential for Ta from the model generalized pseudopotential theory (MGPT) [6].

We first compare the calculated adiabatic moduli C_{ijkl}^S obtained from $C_{ijkl}^T(\Omega, T)$ with electronic plus QH thermal contributions against experimental data, Figs. (1 and 2). We have found that it is necessary to include both the electron- and ion-thermal components of the C_{ijkl} , since each is of similar magnitude, roughly 0.1 Mbar at $T = 2500$ K and $P = 0$. Since the electron thermal plus QH ion-thermal calculation describe well the available experimental values, we now compare only the computation of $C_{ijkl}^{ion}(\Omega, T)$ by the QH and AH calculations. Overall

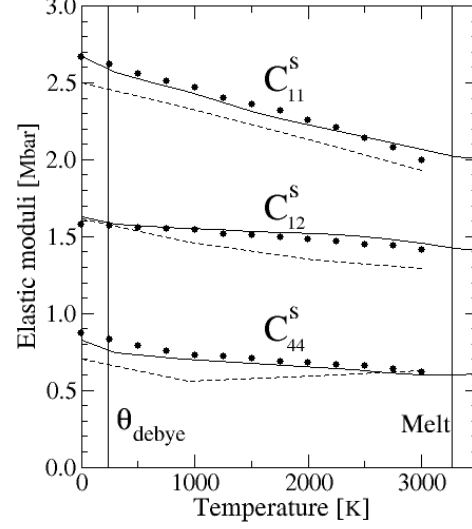


Fig. 1: The thermal dependence of the calculated C_{ijkl}^S (solid line) at ambient pressure up to $T_m = 3376$ K is compared to experiment [7] (circle). The dashed lines are from Gülseren and Cohen's work [3].

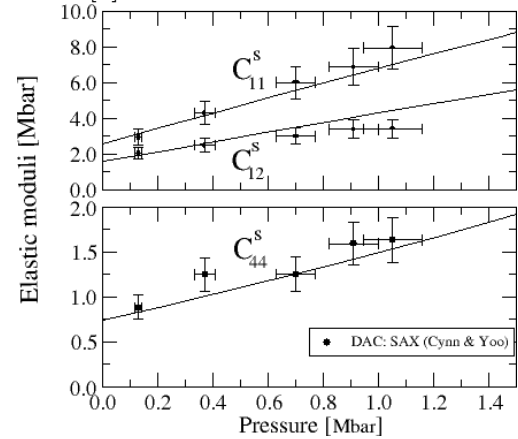


Fig. 2: The calculated C_{ijkl} (line) at $T = 300$ K captures the pressure dependence as compared to SAX-DAC data [8] (circle).

the AH calculation yields similar values compared to the QH calculation, especially below 1 Mbar and even near T_m . As the pressure increases, the AH calculated values deviate from the QH values at temperatures just below T_m (see Fig. 3). At pressures above 6 Mbar, the AH calculated values only begin to deviate from the QH calculation within 80% of the T_m . This indicates that Ta has negligible anharmonic effects (deviation from high temperature, linear dependence) over a broad range of pressure with temperature nearing T_m . This linear temperature dependence of the C_{ijkl}^T leads to linear dependence in Voigt averaged shear modulus, albeit the pressure dependence of the cold shear modulus is non-linear above 6 Mbar.

This work was performed under the auspices of the U.S. Department of Energy by the University of California Lawrence Livermore National Laboratory under contract W-7405-Eng-48.

*

References

- [1] R. J. Wolf, K. A. Mansour, M. W. Lee and J. R. Ray, *Temperature dependence of elastic constants of embedded-atom models of palladium*, Phys. Rev. B **46**, 8027 (1992).
- [2] C. W. Greeff and J. A. Moriarty, *Ab initio thermoelasticity of magnesium*, Phys. Rev. B **59**, 3427 (1999).
- [3] O. Gülseren and R. E. Cohen, *High-pressure thermoelasticity of body-centered-cubic tantalum*, Phys. Rev. B **65**, 064103 (2002).
- [4] P. Söderlind and J. A. Moriarty, *First-principles theory of Ta up to 10 Mbar pressure: Structural and mechanical properties*, Phys. Rev. B **57**, 10340 (1998).
- [5] D. C. Wallace, *Thermodynamics of crystals*, Dover: Mineola, NY (1998).
- [6] J. A. Moriarty, et al. *Quantum-based atomistic simulation of materials properties in transition metals*, J. Phys.: Cond. Mat. **14**, 2825 (2002).
- [7] E. Walker and P. Bujard, *Anomalous temperature behavior of the shear elastic constant C_{44} in tantalum*, Solid State Comm. **34**, 691 (1980).
- [8] H. Cynn and C.-S. Yoo, *Single crystal elastic constants of tantalum to 105 GPa*, LLNL internal document UCRL-JC-137930 (unpublished).

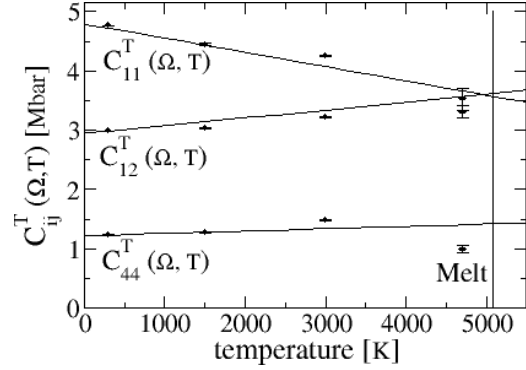


Fig. 3: The QH (line) and AH (circle) calculations of the $C_{ijkl}^{ion}(\Omega, T)$ term at $\Omega = 102.2$ a.u.³ for Ta. The pressure varies from 0.5 to 0.7 Mbar nearing $T_m = 5074$ K.