

Accepted Manuscript

Mineralization of organic pollutants by anodic oxidation using reactive electrochemical membrane synthesized from carbothermal reduction of TiO_2


Clément Trellu, Clémence Coetsier, Jean-Christophe Rouch, Roseline Esmilaire, Marc Cretin, Christel Causserand

PII: S0043-1354(17)31065-5

DOI: [10.1016/j.watres.2017.12.070](https://doi.org/10.1016/j.watres.2017.12.070)

Reference: WR 13468

To appear in: *Water Research*

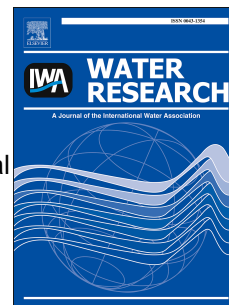

Please cite this article as: Clément Trellu, Clémence Coetsier, Jean-Christophe Rouch, Roseline Esmilaire, Marc Cretin, Christel Causserand, Mineralization of organic pollutants by anodic oxidation using reactive electrochemical membrane synthesized from carbothermal reduction of TiO_2 , *Water Research* (2017), doi: 10.1016/j.watres.2017.12.070

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.


Mineralization of organic pollutants by anodic oxidation using reactive electrochemical membrane synthesized from carbothermal reduction of TiO_2

Clément Trellu^{1,*}, Clémence Coetsier¹, Jean-Christophe Rouch¹, Roseline Esmilaire², Marc Cretin², Christel Causserand¹

1- Laboratoire de Génie Chimique, Université de Toulouse, CNRS, INPT, UPS, Toulouse, France

2- Institut Européen des Membranes, UMR 5635 (CNRS-ENSCM-UM), Montpellier, France

Graphical abstract

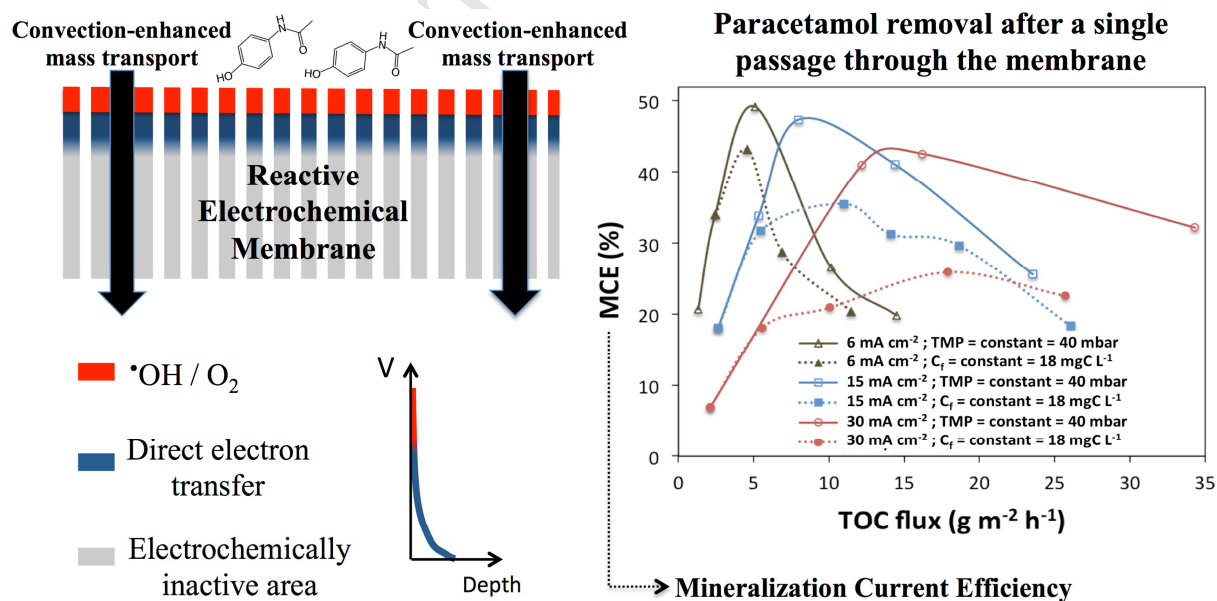

Mineralization of organic pollutants by anodic oxidation using reactive electrochemical membrane synthesized from carbothermal reduction of TiO₂

Clément Trellu^{1,*}, Clémence Coetsier¹, Jean-Christophe Rouch¹, Roseline Esmilaire², Marc Cretin², Christel Causserand¹

1- Laboratoire de Génie Chimique, Université de Toulouse, CNRS, INPT, UPS, Toulouse, France

2- Institut Européen des Membranes, UMR 5635 (CNRS-ENSCM-UM), Montpellier, France

Highlights

- Reactive electrochemical membranes are synthesized by carbothermal reduction of TiO₂
- Unprecedented high mineralization rates of various organic pollutants was achieved
- Ohmic drops within the REM influence electro-oxidation mechanisms and efficiency
- O₂ generation and O₂ bubbles sweeping at high permeate flux affect process efficiency
- Current density is the critical parameter for optimization of the process

**Mineralization of organic pollutants by anodic oxidation using
reactive electrochemical membrane synthesized from carbothermal
reduction of TiO₂**

Clément Trellu^{1,*}, Clémence Coetsier¹, Jean-Christophe Rouch¹, Roseline Esmilaire²,
Matthieu Rivallin², Marc Cretin², Christel Causserand¹

*1- Laboratoire de Génie Chimique, Université de Toulouse, CNRS, INPT, UPS, Toulouse,
France*

2- Institut Européen des Membranes, UMR 5635 (CNRS-ENSCM-UM), Montpellier, France

Manuscript submitted to Water Research for consideration

* Corresponding Author:

Email: cl.trellu@gmail.com

Phone: +33 (0)6 72 27 94 61

Abstract

Reactive Electrochemical Membrane (REM) prepared from carbothermal reduction of TiO_2 is used for the mineralization of biorefractory pollutants during filtration operation. The mixture of Ti_4O_7 and Ti_5O_9 Magnéli phases ensures the high reactivity of the membrane for organic compound oxidation through $\cdot\text{OH}$ mediated oxidation and direct electron transfer. In cross-flow filtration mode, convection-enhanced mass transport of pollutants can be achieved from the high membrane permeability ($3,300 \text{ LMH bar}^{-1}$). Mineralization efficiency of oxalic acid, paracetamol and phenol was assessed as regards to current density, transmembrane pressure and feed concentration. Unprecedented high removal rates of total organic carbon and mineralization current efficiency were achieved after a single passage through the REM, e.g. $47 \text{ g m}^{-2} \text{ h}^{-1}$ – 72% and $6.7 \text{ g m}^{-2} \text{ h}^{-1}$ – 47% for oxalic acid and paracetamol at 15 mA cm^{-2} , respectively. However, two mechanisms have to be considered for optimization of the process. When the TOC flux is too high with respect to the current density, aromatic compounds polymerize in the REM layer where only direct electron transfer occurs. This phenomenon decreases the oxidation efficiency and/or increases REM fouling. Besides, O_2 bubbles sweeping at high permeate flux promotes O_2 gas generation, with adverse effect on oxidation efficiency.

Keywords

Anodic oxidation; Electro-oxidation; Reactive Electrochemical Membrane; Organic pollutants; Sub-stoichiometric titanium oxide; Mineralization.

1. Introduction

Anodic oxidation (AO) is an electrochemical advanced oxidation process (EAOP) increasingly recognized as a promising next-generation technology for the treatment of contaminated effluents (Panizza and Cerisola, 2009; Chaplin, 2014; Radjenovic and Sedlak, 2015; Moreira et al., 2017). The process is based on both direct electron transfer (DET) from organic compounds (R) to the anode surface (eq. 1) and generation of hydroxyl radicals ($\cdot\text{OH}$) from water oxidation on the surface of electrodes (M) with high O_2 overvoltage (eq. 2) (Panizza and Cerisola, 2009). $\cdot\text{OH}$ is a very strong oxidant ($E^\circ = 2.8$ V vs SHE) (Latimer, 1952) allowing the degradation of a large range of bio-refractory organic compounds. Mineralization of various micropollutants and complex effluents has been achieved using AO (Özcan et al., 2008; Balci et al., 2009; Oturan et al., 2015; Martínez-Huitle et al., 2015; Brillas and Martínez-Huitle, 2015; Antonin et al., 2015; Trelu et al., 2016). However, several scientific challenges still need to be overcome in order to promote the application of AO for water treatment.



$\cdot\text{OH}$ are produced in a heterogeneous way in the electrochemical cell, therefore, new approaches are necessary in order to break the high cost bottleneck related to the limited mass transfer of organic pollutants from the bulk to the electrode surface (Yang et al., 2009; Chaplin, 2014; Radjenovic and Sedlak, 2015). Electro-oxidation is controlled by mass transport phenomenon when the concentration of organic compounds is too low by comparison to the electron transfer rate (current density). In the potential region of water discharge, secondary reactions such as oxygen evolution strongly decreases the current efficiency (Panizza et al., 2001; Panizza and Cerisola, 2009). Unfortunately, most

of anode materials used in AO can only be produced under the form of conventional plate electrodes (e.g. boron-doped diamond), for which mass transport is limited by surface diffusivity in the external film (Brillas and Martínez-Huitle, 2011). This technological constraint also limits the potential for scaling up. Implementation of flow-through porous electrodes is the most promising way to overcome mass transfer limitations (Zaky and Chaplin, 2013; Ganiyu et al., 2015; Radjenovic and Sedlak, 2015; Ronen et al., 2016).

Recently, carbon nanotube electrochemical filters have been developed for the removal of organic pollutants, however they are not active for $\cdot\text{OH}$ production (Tsierkezos and Ritter, 2012; Schnoor and Vecitis, 2013; Gao and Vecitis, 2013; Liu et al., 2015). Besides, research works from Guo et al. (2016) showed that a convection-enhanced rate constant for $\text{Fe}(\text{CN})_6^{4-}$ oxidation of $1.4 \cdot 10^{-4} \text{ m s}^{-1}$ – the highest reported in the literature, close to the kinetic limit – was reached by using porous sub-stoichiometric titanium oxide (TiO_x) reactive electrochemical membrane (REM) (Guo et al., 2016). The high membrane permeability ($3,200 \text{ L m}^{-2} \text{ h}^{-1} \text{ bar}^{-1}$) resulted in a strong increase of the convective mass transport of pollutants from the bulk solution to electron-transfer sites at the surface and in the porosity of the material. The reactivity of the material has been investigated by using probe molecules (oxalic acid, coumarin, terephthalic acid) showing that both DET and formation of $\cdot\text{OH}$ were involved in the oxidation of organic compounds (Zaky and Chaplin, 2013, 2014; Ganiyu et al., 2016). First studies on TiO_x REM used either commercial Ebonex[®] membranes (Walsh and Wills, 2010; Zaky and Chaplin, 2013) or TiO_2 ultrafiltration membranes reduced to Ti_4O_7 under 1 atm H_2 during 50 h at 1050°C (Guo et al., 2016). The latter showed the most promising results because of a higher permeability and predominance of the Ti_4O_7 phase but high production costs are associated to the synthesis method.

The focus of this study is on testing a novel TiO_x REM synthesized from carbothermal reduction of TiO_2 . The REM is characterized by scanning electron microscopy (SEM), X-ray diffraction (XRD), Hg porosimetry and water permeability. In cross-flow filtration mode, the effect of permeate flux, pollutant concentration and current density on mineralization efficiency of various organic compounds (oxalic acid (OA), paracetamol (PCT), phenol (PHE)) is assessed. A focus is given on phenomena limiting the efficiency of the REM during treatment of aromatic molecules at high concentration or high permeate flux. From the different behaviors observed, electro-oxidation mechanisms and potential of the REM to be applied for water treatment are highlighted.

2. Materials and methods

2.1. Chemicals

All chemicals were of reagent grade and purchased from Sigma Aldrich (Na_2SO_4 , PCT, OA) or Alfa Aesar (PHE). Solutions were prepared using ultrapure water (Purelab®, Elga LabWater, 18.2 $\text{M}\Omega\text{ cm}$).


2.2 REM synthesis and characterization

Porous Magneli phase was synthesized from carbothermal reduction of TiO_2 by using an extrusion die, based on the method developed by Saint-Gobain CREE. The extrusion paste contained 74.1% of anatase form of TiO_2 (Altichem, median particle diameter of 0.37 μm), 2.5% of carbon black (Thermax N990), 18.4% of water and 4.9% of organic binders used as extrusion adjuvant. Organic binders were removed during the debinding step under air atmosphere at 350 °C, 2 h. Finally, sintering and carbothermal reduction of TiO_2 to TiO_x was performed during 2 h under argon atmosphere at 1300 °C.

REM morphology was analyzed from images obtained by SEM at high resolution (Hitachi S4800) at 30 and 3000 magnification. Hg porosimetry analysis was performed on a AutoPore IV (Micrometrics) device. The nature of Magneli phases was characterized by powder XRD using X'Pert Pro (Pan Analytical) system with a Cu X-ray tube (40 kV and 20 mA). Scans were collected by Pan Alytical software and processed with Full Prof and Origin Pro software.

2.3 Cross-flow filtration and electro-oxidation setup

The REM (inner and outer diameter of 6 and 10 mm, active length of 9 cm) was used as anode in inside-outside cross-flow filtration mode. A 3 mm diameter stainless steel rod used as cathode was placed at the center of the REM. A recirculating pump and a pressurized reservoir tank ensured constant cross-flow rate (0.88 m s^{-1}) and transmembrane pressure (TMP, 40 – 1000 mbar). Experiments were performed with OA ($0.75 - 36 \text{ mM}$; $\text{TOC} = 18 - 870 \text{ mg L}^{-1}$), PCT ($0.1 - 2.3 \text{ mM}$; $\text{TOC} = 9 - 220 \text{ mg L}^{-1}$) or PHE ($0.25 - 2 \text{ mM}$; $\text{TOC} = 18 - 140 \text{ mg L}^{-1}$) as model organic compounds. Initial pH of the solution was not adjusted and the evolution of the pH in the permeate and retentate was monitored. Sodium sulfate (50 mM) was added as supporting electrolyte. Only the retentate was 100% recirculated, while the permeate was continuously sampled for analysis. Experiments were performed in galvanostatic mode, using a power supply from ELC (AL924A). Current density (j) was in the range $6 - 30 \text{ mA cm}^{-2}$. Potential difference in the electrochemical cell was in the range $4.0 - 6.5 \text{ V}$, according to current intensity. All experiments were performed with a constant volume of permeate collected (350 mL). A schematic view of the setup is provided in Figure 1.

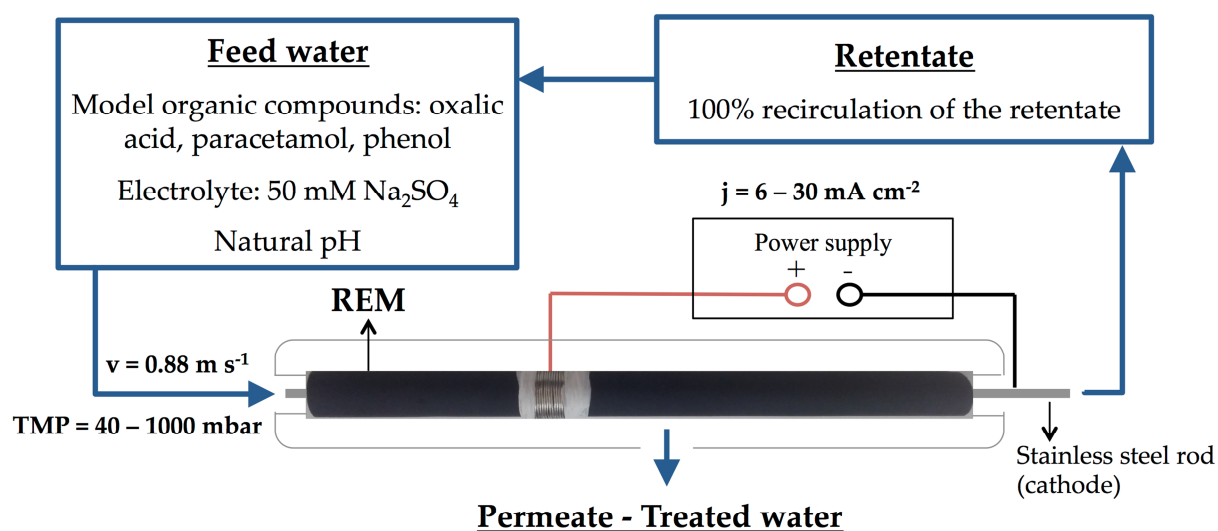Inside-out cross-flow filtration mode

0% recirculation of the permeate - Single passage through the membrane

Figure 1: Schematic view of the combined electro-oxidation/filtration setup

2.4 Analytical methods

Concentration of PCT was analyzed by HPLC (Agilent 1200) with a C18 column and a UV detector ($\lambda = 254 \text{ nm}$). The mobile phase was a mixture of water (with 0.1% formic acid) and acetonitrile (with 0.1% formic acid). HPLC was operated using a constant flow of 1.2 mL min^{-1} and gradient elution (0-3.5 min: 2.5% acetonitrile ; 6.5 min: 80% acetonitrile ; 7.5-10.5 min: 2.5% acetonitrile). The total organic carbon (TOC) was measured with a Shimadzu TOC-L analyzer using the 680°C combustion catalytic oxidation method. The relative standard deviation on TOC measurements is 2%.

2.4 Kinetic analysis and figures of merit

Different performance indicators were used for the determination of the oxidation efficiency. The TOC flux, percentage of removal (PR), removal rate (RR) and mineralization current efficiency (MCE, percentage of current directed towards the

128 mineralization of the substrate passing through the REM) of the substrate i (molecule or
 129 TOC) were calculated as follows (Brillas et al., 2009; Garcia-Segura and Brillas, 2011;
 130 Zaky and Chaplin, 2013):

$$TOC\ flux = TOC_f \times J \quad (1)$$

$$PR_i = \frac{(C_{f,i} - C_{p,i})}{C_{f,i}} \times 100 \quad (2)$$

$$RR_i = (C_{f,i} - C_{p,i}) \times J \quad (3)$$

$$MCE = \frac{n F J (TOC_f - TOC_p)}{4.32 \times 10^7 m j} \times 100 \quad (4)$$

131 where $C_{f,i}$ and $C_{p,i}$ are the concentration of the feed and permeate (g L^{-1}), J is the
 132 permeate flux ($\text{L h}^{-1} \text{ m}^{-2}$), n is the number of electrons consumed per molecule of
 133 substrate mineralized, F is the Faraday constant, 4.32×10^7 is a conversion factor ($3,600 \text{ s}$
 134 $\text{h}^{-1} \times 12,000 \text{ mg mol}^{-1}$), m is the number of carbon atoms of the substrate studied, j is the
 135 current density (A m^{-2}) and TOC_f and TOC_p are TOC of the feed and permeate (mg L^{-1}),
 136 respectively.

137 As explained in the results and discussion section, oxidation of the substrate in the feed
 138 stream was negligible.

139 One experiment was performed in quadruplicate in order to assess the reproducibility
 140 of experimental data.

141

142 3. Results and discussion

143 3.1 REM characterization

The REM was characterized in order to anticipate its suitability for the removal of organic pollutants from water. SEM images presented in Figure 2a and 2b show the uniform and interconnected structure of REM pores. Pore structure was further characterized by Hg porosimetry (Figure 2c and 2d). Differential and cumulative intrusion pore volume indicate a mono-modal pore size distribution ranging between 0.8 and 1.9 μm with median pore diameter of 1.4 μm . Hg porosimetry analysis also determined a porous volume of 41% and specific surface area of 0.40 $\text{m}^2 \text{g}^{-1}$. These characteristics correspond to microfiltration membranes allowing the separation of particles and bacteria, while dissolved species pass through the membrane. The porous structure of the REM is tailored for reaching high permeate flux. Water permeability was determined as 3,300 $\text{L m}^{-2} \text{h}^{-1} \text{bar}^{-1}$. This is 67-fold higher than commercial Ebonex[®] electrodes (Vector Corrosion Technologies, Inc.) consisting primarily of Ti_4O_7 , which present a bimodal pore size distribution. While micro-sized pores range between 1 and 6 μm , nano-sized pores (<10 nm) strongly increase pressure drop across Ebonex[®] membranes (Zaky and Chaplin, 2013). Similar flux (3,208 $\text{L m}^{-2} \text{h}^{-1} \text{bar}^{-1}$) was obtained by Guo et al. (2016) with TiO_2 membranes reduced to Ti_4O_7 using a thermal method at 1050°C under 1 atm H_2 during 50 h (Guo et al., 2016). The median pore size diameter of these membranes was 2.99 μm , however, the 70 μm thick active layer with smaller pores could not be characterized by Hg porosimetry. Detailed study on limiting mechanisms for electro-oxidation showed three different behaviors according to permeate flux through the membrane (Zaky and Chaplin, 2013; Guo et al., 2016). Mass transport rate is the key parameter since electro-oxidation reactions occur at the membrane/pore surface. At low permeate flux and convection rate, diffusion can limit organic compound oxidation, similarly to conventional plane configurations (parallel plate electrodes). Convection-enhanced mass transport of pollutants is observed at

higher permeate fluxes and the diffusion boundary layer is eliminated (Gao and Vecitis, 2012; Zaky and Chaplin, 2013). By continuously increasing the permeate flux, an ultimate limitation can finally arise from the electron transfer rate. This kinetic limitation depends on the nature of the substrate to oxidize, intrinsic kinetic reactivity of the REM and current supplied. From the comparison to values reported by Guo et al. (2016) with a similar configuration, it is anticipated that the high permeability of the REM used during this study avoid diffusion limitations during electro-oxidation of organic compounds, even at the lowest flux used ($\text{TMP} = 40 \text{ mbar}$; $J \approx 120 \text{ L h}^{-1} \text{ m}^{-2}$).

The electrochemical performance of REM also tightly depends on the nature of the Magnéli phase. Comparison of XRD data of the REM and TiO_x standards shows the presence of a mixture of Ti_4O_7 and Ti_5O_9 phases (Figure 2e, 2f and 2g). None studies focused on the electrochemical performance of Ti_5O_9 for organic compound oxidation but the most conductive Magnéli phase is known to be Ti_4O_7 and recent studies demonstrated that this phase is able to produce $\cdot\text{OH}$ from water oxidation (Guo et al., 2016; Ganiyu et al., 2016, 2017). Overall, physical characteristics of REM synthesized from carbothermal reduction of TiO_2 show that this material is tailored for water treatment applications, particularly for oxidation of organic pollutants. Moreover, this innovative synthesis method has the great advantage to reduce thermal treatment times and to avoid H_2 consumption.

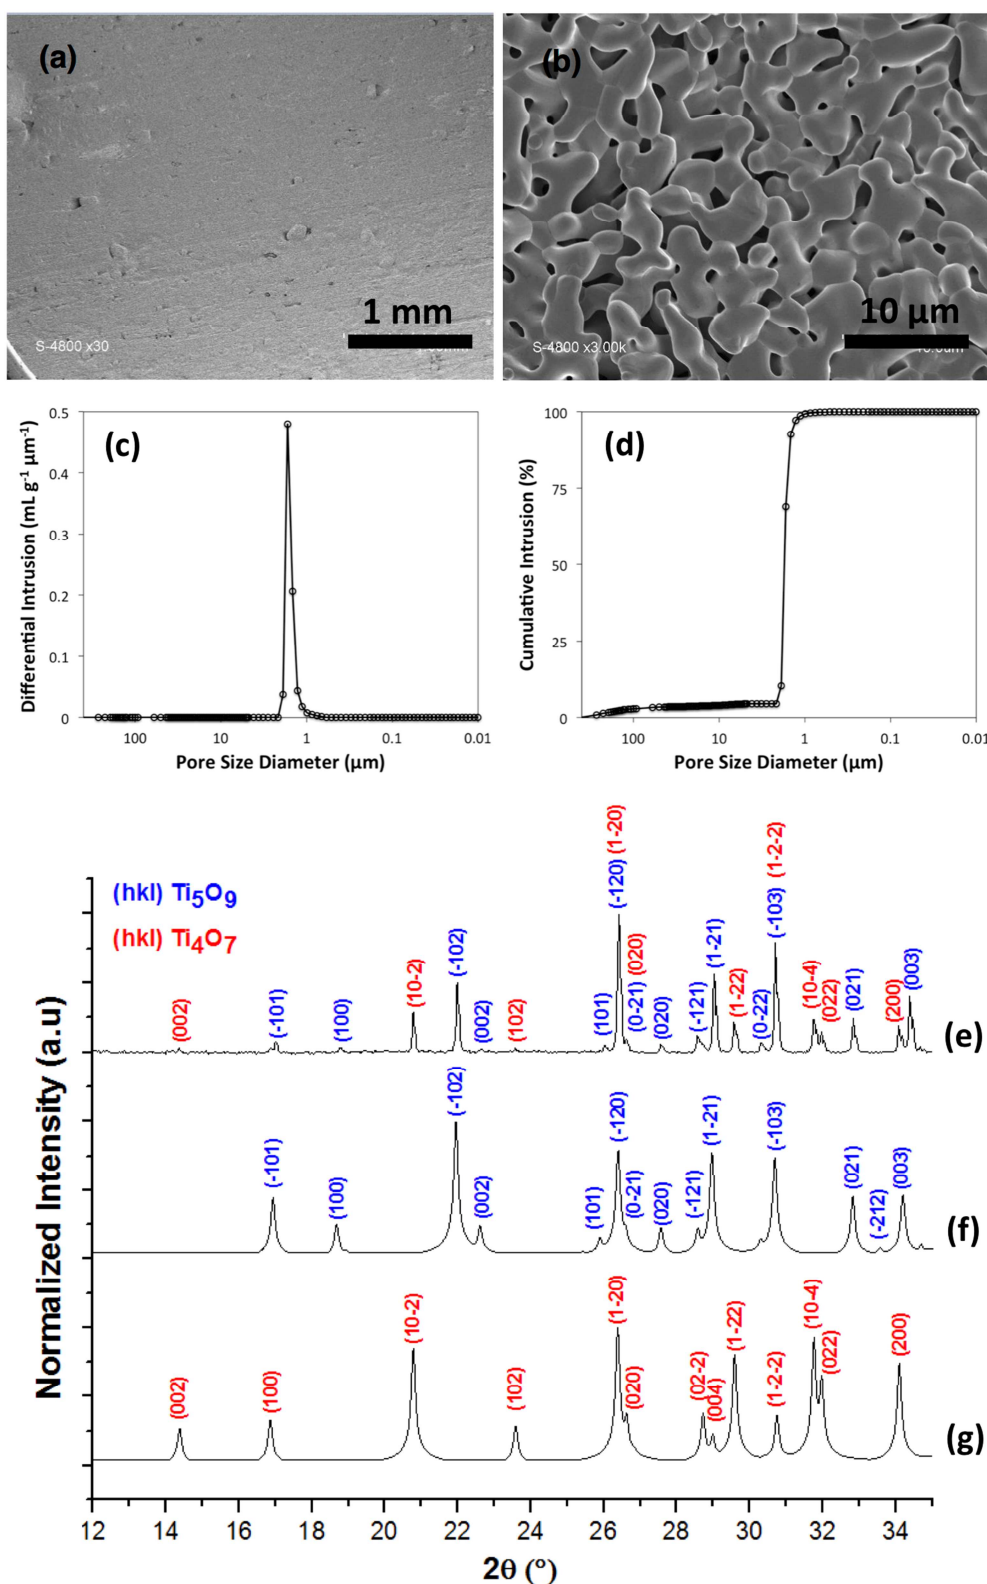


Figure 2: Physico-chemical characteristics of the reactive electrochemical membrane (REM) Scanning electron microscopy of inner surface: (a) x 30, (b) x3000. Data of Hg intrusion porosimetry analysis: (c) differential pore volume, (d) cumulative pore volume. X-ray diffraction data: (e) REM, (f) Ti₅O₉ (from Hodeau and Marezio (1979), (g) Ti₄O₇ (from Andersson and Jahnberg (1963)).

3.2 Electrochemical oxidation of organic compounds

The efficiency of the REM for mineralization of organic molecules was assessed using various model compounds involving different electro-oxidation mechanisms. Hydroxyl radicals generated at the surface of a BDD anode are able to participate to the oxidation of OA (Martínez-Huitle et al., 2004; Garcia-Segura and Brillas, 2011). However, based on the very low absolute rate constant for the reaction of $\cdot\text{OH}$ with OA - $1.4 \times 10^6 \text{ M}^{-1} \text{ s}^{-1}$ (Weiss et al., 2007; Ferro et al., 2010) – Guo et al. (2016) considered that OA could be used as a direct oxidation probe. As regards to PHE and PCT, both DET and $\cdot\text{OH}$ mediated oxidation can participate to the mineralization (rate constant of $1.4 \times 10^{10} \text{ L mol}^{-1} \text{ s}^{-1}$ for oxidation of PCT by $\cdot\text{OH}$ (Land and Ebert, 1967); rate constant of $9.8 \times 10^9 \text{ L mol}^{-1} \text{ s}^{-1}$ for oxidation of PHE by $\cdot\text{OH}$ (Bisby and Tabassum, 1988)). Besides, poisoning effect or anode fouling from electro-polymerization is often observed during electro-oxidation of PHE at the surface of anode materials with low O_2 overpotential, *i.e.* when oxidation mainly occurs by DET (Belhadj Tahar and Savall, 2009a, 2009b; Panizza and Cerisola, 2009).

Preliminary studies without current supply showed the absence of adsorption of these organic compounds in membrane pores and other parts of the pilot. It was also observed that oxidation mainly resulted from convection through the REM. Results from an electro-oxidation experiment at 30 mA cm^{-2} and $\text{TMP} = 40 \text{ mbar}$ during 90 min showed that >98% degradation and mineralization of 0.18 mM ($\text{TOC} = 18 \text{ mg L}^{-1}$) of PCT was achieved in the permeate all along the experiment, while PCT and TOC concentration in the feed stream only decreased by 9% and <5% (after 90 min), respectively. Molecules oxidized at the outer surface of the REM are not accumulated in the retentate because back diffusion is low compared to forward convection (Gao and Vecitis, 2012). Thus,

reaction in the feed stream was neglected, compared to the reaction through the REM. A quasi-permanent steady-state of both feed and permeate flux/concentration was reached few minutes after anodic polarization of the REM. Permeate was sampled until the same volume of solution was filtered (350 mL) for all experiments. Therefore, each data point reported in Figure 3, 4 and 7b refers to a single experiment. The efficiency was calculated by comparing the concentration in the collected permeate and in the feed stream (considered as constant).

One experiment (TMP = 100 mbar; [PCT] = 0.33 mM; TOC = 32 mg L⁻¹; j = 15 mA cm⁻²) was performed in quadruplicate in order to assess the reproducibility of experimental data. Low standard deviations were obtained for TOC flux (11.9 ± 0.4 g m⁻² h⁻¹), percentage of TOC removal (60 ± 3%), TOC removal rate (7.1 ± 0.3 g m⁻² h⁻¹) and MCE (49 ± 1%).

3.2.1 Oxidation of oxalic acid

Figure 3 shows results obtained for the two-electron oxidation of OA to CO₂ and H₂O at 15 mA cm⁻². For example, 75% of TOC removal from a solution containing 354 mgC L⁻¹ was achieved after a single passage through the membrane with a permeate flux of 139 L h⁻¹ m² (TOC flux = 49 g h⁻¹ m⁻²). Results from increasing concentrations of oxalic acid (TMP = constant = 40 mbar) are compared with results from increasing TMP (C_f = constant = 18 mgC L⁻¹). An ultimate current limitation was drawn according to the maximum amount of electron that can be used for oxidation of OA (black solid lines in Figure 3). This depends on the amount of electron supplied to the system (current density) and on the amount of OA available for oxidation (TOC flux).

Both OA concentration and permeate flux influences the TOC flux through the REM. When experiments were performed at the same TMP (40 mbar) and increasing OA concentrations ($C_f = 18 - 800 \text{ mgC L}^{-1}$), TOC removal rate and MCE reached a plateau around $47 \text{ g m}^{-2} \text{ h}^{-1}$ and 72%, respectively, indicating that a kinetic limitation was reached. At relatively low OA flux ($<30 \text{ g m}^{-2} \text{ h}^{-1}$), almost full mineralization of OA was achieved and the removal efficiency was close to the current limitation. However, at the highest OA flux, the kinetic limitation observed for OA oxidation could not reach the ultimate current limitation (MCE = 100%). In fact, a portion of electrons is also consumed in oxygen evolution reactions *i.e* the generation of O_2 and $\cdot\text{OH}$ that do not react or react slowly with OA. Maximum TOC removal rate of OA was 4.9-fold higher than the maximum reported in the literature using REM at a constant anodic potential of 2.94 V ($47 \text{ vs } 9.6 \text{ g m}^{-2} \text{ h}^{-1}$), most probably because of the higher current density used in this study leading to an increase of the kinetic limit (Guo et al., 2016).

Different behavior was observed when experiments were performed at constant OA concentration ($C_f = 18 \text{ mgC L}^{-1}$) and increasing TMP (*i.e.* increasing permeate flux). TOC removal rate and MCE of OA followed a bell curve with maximum of $14 \text{ g m}^{-2} \text{ h}^{-1}$ and 21% achieved for a TOC flux of $29 \text{ g m}^{-2} \text{ h}^{-1}$ ($J = 1,650 \text{ L m}^{-2} \text{ h}^{-1}$). Similarly to the behavior observed with increasing OA concentration, OA oxidation also reached a kinetic limit when increasing the permeate flux. The difference actually lies in the increase of oxygen evolution reactions. High permeate fluxes increased O_2 gas bubbles sweeping from the REM surface, thus resulting in the promotion of the competitive reaction of oxygen evolution. Guo et al. (2016) reported the same behavior in a cross-flow filtration configuration using TiO_x REM from thermal reduction of TiO_2 under H_2 . Lower TOC removal rate ($9.6 \text{ g m}^{-2} \text{ h}^{-1}$) but higher MCE (84%) was achieved for an optimal value of OA flux of $13.5 \text{ g m}^{-2} \text{ h}^{-1}$ ($J = 561 \text{ L m}^{-2} \text{ h}^{-1}$). Lower TOC removal rate and optimal value of

permeate flux is ascribed to the lower current density (lower electron transfer rate). However, higher maximum MCE was reached because O_2 gas bubbles generation and sweeping was reduced because of the lower current density and lower optimal value of permeate flux, respectively.

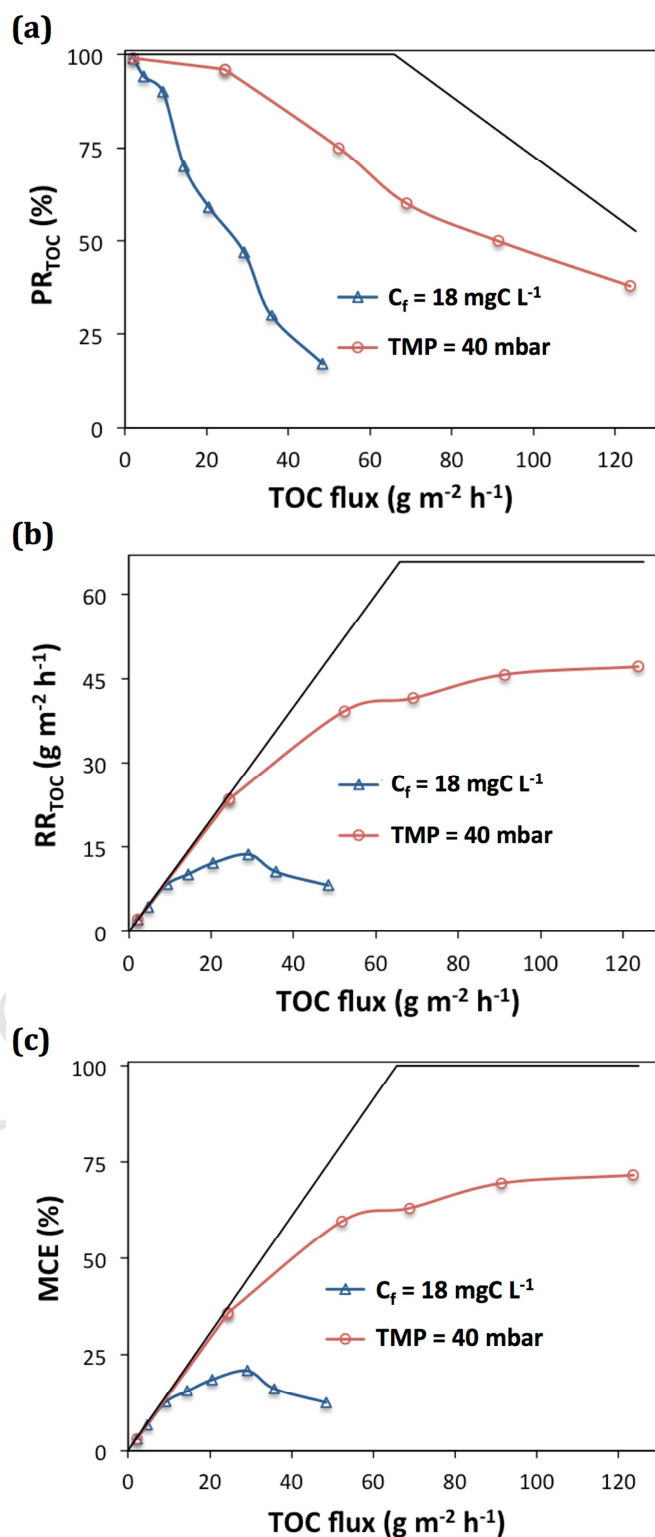


Figure 3. Efficiency of oxalic acid removal from water by anodic oxidation on reactive electrochemical membrane as a function of total organic carbon (TOC) flux through the membrane: (a) percentage of TOC removal (PR_{TOC}), (b) TOC removal rate (RR_{TOC}), (c) mineralization current efficiency (MCE). Results from increasing concentrations of oxalic acid (TMP = constant = 40 mbar) are compared with results from increasing TMP (C_f = constant = 18 mgC L⁻¹). j = 15 mA cm⁻²; [Na₂SO₄] = 50 mM. Solid lines represent piece-wise interpolation and are included for easier reading of the figure. Black solid lines represent the ultimate current limitation, based on the maximum amount of electron that can be consumed for oxidation of OA.

3.2.2 Oxidation of paracetamol

PCT is an interesting model organic pollutant because both DET and $\cdot OH$ mediated oxidation is required in order to achieve efficient mineralization of the molecule. On one hand, PCT presents a high rate constant for oxidation by $\cdot OH$ (9.8×10^9 L mol⁻¹ s⁻¹) and the well-known degradation by-product 1,4-benzoquinone is strongly refractory to DET (Brillas et al., 2005). On the other hand, OA and other short-chain carboxylic acids generated as ultimate organic intermediates (e.g. OA) have lower oxidation rate by $\cdot OH$ and faster mineralization rate can be achieved by DET (Weiss et al., 2007).

The efficiency of PCT degradation and mineralization by the REM is shown in Figure 4. Very high degradation rate of PCT was obtained, *e.g.* >99.9% degradation of PCT was reported until TOC flux reach 7, 14 and 20 g m⁻² h⁻¹ at 6, 15 and 30 mA cm⁻², respectively. However, higher efficiency was observed at high concentration/low TMP compared to experiments conducted at low concentration/high TMP. There is actually a competition between the reaction of free $\cdot OH$ with each other and with organic compounds (Kapałka et al., 2008). The dimerization reaction of $\cdot OH$ decreases mineralization efficiency through the consumption of $\cdot OH$ in non-organic events (scavenging reactions). Particularly, $\cdot OH$ dimerization has been observed to form hydrogen peroxide, and subsequently O₂ (Kapałka et al., 2009). Therefore, the increase of O₂ gas bubble

sweeping at high permeate flux might lead to a shift of the equilibrium of these reactions and could promote the scavenging reactions of $\cdot\text{OH}$ dimerization.

Using PCT as model compound, the ultimate current limitation for TOC removal (by assuming $\text{MCE} = 100\%$) is 5.7, 14.2 and 28.3 $\text{g m}^{-2} \text{ h}^{-1}$ at 6, 15 and 30 mA cm^{-2} , respectively. Compared to experiments with OA at the same current density (ultimate current limitation for TOC removal was 65.8 $\text{g m}^{-2} \text{ h}^{-1}$ at 15 mA cm^{-2}), a lower amount of TOC can be removed because more electrons are required to mineralize 1 mole of carbon (4.6 moles of e^- per mole of C for PCT and 1 mole of e^- per mole of C for OA).

When experiments were performed at the same TMP (40 mbar) and increasing PCT concentrations ($C_f = 18 - 220 \text{ mgC L}^{-1}$), TOC removal rate and MCE did not reached a plateau; bell curves were observed and maximum MCE were reached for TOC flux around 5 (MCE = 49%), 8 (MCE = 47%) and 16 $\text{g m}^{-2} \text{ h}^{-1}$ (MCE = 43%) at 6, 15 and 30 mA cm^{-2} , respectively. Much higher MCE was obtained compared to a previous study using boron-doped diamond plate electrode (Brillas et al., 2005). The highest maximum TOC removal rate was obtained at high current density (12 $\text{g m}^{-2} \text{ h}^{-1}$ at 30 mA cm^{-2}) because of the increase of the electron transfer rate. However, the different bell curves obtained for the MCE at different current density clearly overlapped, meaning that the current density has to be adapted to the concentration of PCT in order to achieve maximum MCE. A dark-orange color was also observed in the permeate for experiments performed with operating conditions corresponding to the downward phase of the bell curve. The decrease of oxidation efficiency at high PCT concentration can be explained by taking into consideration the different oxidation mechanisms occurring in the REM according to the depth into the porous electrode. Jing et al. (2016) provided an approximation of the potential distribution in an ultrafiltration TiO_x REM, based on the analytical solution

developed by Lasia (2008). The resistance of the electrode material and the concentration polarization of electroactive species were neglected. The main parameters influencing the calculation were pore radius, specific solution resistance, exchange current density and overpotential. The simulation showed that the potential dramatically drops in a cylindrical pore and reach a value below the one required for $\cdot\text{OH}$ production at the depth of 0.023 μm . Below this potential, DET mainly occur. Deeper into the membrane, the surface of the REM is not even anymore electro-active. DET is not able to achieve efficient mineralization of PCT. Production of soluble dark-orange polymers was observed during the electro-oxidation of PCT on Pt anode (active anode with low production of $\cdot\text{OH}$) (Brillas et al., 2005) and PCT by-products identified in previous studies (Almeida et al., 2011; Feng et al., 2013) such as 1,4-benzoquinone can be strongly refractory to DET. At high PCT concentration, $\cdot\text{OH}$ generated in the top layer of the REM are not sufficient to degrade all PCT molecules. Thus, the MCE decreases due to electro-polymerization of PCT and presence of organic compounds recalcitrant to DET in the deeper REM layer where only DET occurs. On the contrary, maximum MCE is reached when PCT molecules are degraded by $\cdot\text{OH}$ to intermediate products highly reactive to DET, e.g. short-chain carboxylic acids such as OA.

When experiments were performed at the same PCT concentration ($C_f = 18 \text{ mgC L}^{-1}$) and increasing TMP (40 – 470 mbar), similar phenomenon occurred. Thus, the results presented in this study show that the increase of the current density is required for maintaining elevated MCE during the treatment of high pollutant concentration or permeate flux because it allows avoiding the presence of organic compounds recalcitrant to DET in the layer where only DET occurs. Besides, lower oxidation efficiency was obtained during experiments conducted at high TMP compared to experiments at low TMP because of the enhancement of adverse effects coming from O_2

gas bubble sweeping, as described previously. This behavior is strongly enhanced at high current density because the optimal value of TOC flux is reached at higher permeate flux due to the increase of the electron transfer rate.

A schematic view of the main phenomena involved in the electro-oxidation of organic pollutants is provided in Figure 6.

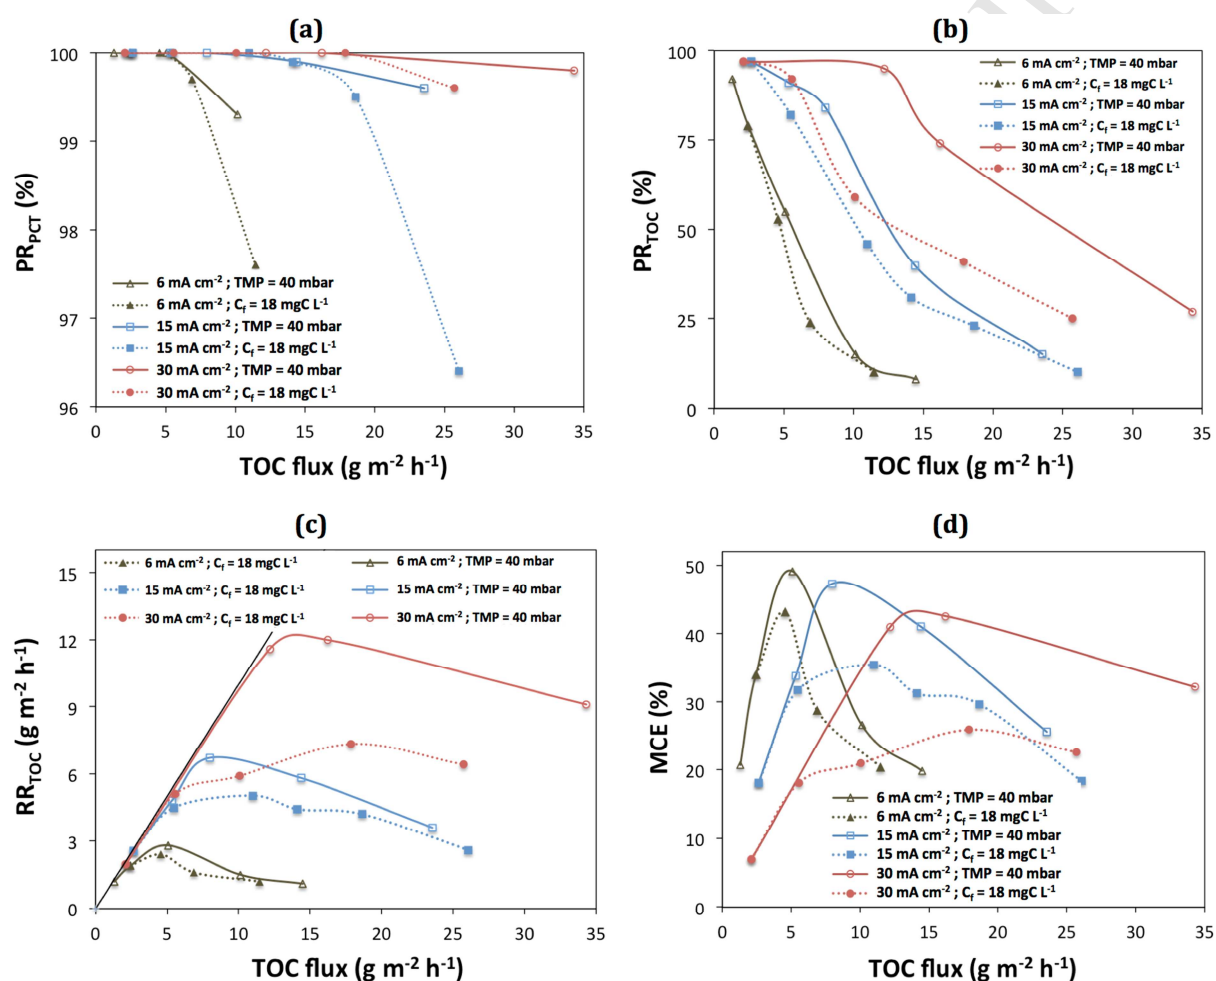


Figure 4. Efficiency of paracetamol (PCT) removal from water by anodic oxidation on reactive electrochemical membrane as a function of total organic carbon (TOC) flux through the membrane and current density: (a) percentage of PCT removal (PR_{PCT}), (b) percentage of TOC removal (PR_{TOC}), (c) TOC removal rate (RR_{TOC}), (d) mineralization current efficiency (MCE). Results from increasing concentrations of PCT (TMP = constant = 40 mbar) are compared with results from increasing transmembrane pressure (TMP) (C_f = constant = 18 mgC L^{-1}). $[\text{Na}_2\text{SO}_4] = 50 \text{ mM}$. Solid and dotted lines represent piece-wise interpolation and are included for easier reading of the figure.

A particular attention was also given to the evolution of the permeate flux during experiments performed at 30 mA cm⁻² (Figure 5). Using only the supporting electrolyte, permeate flux was observed to increase during the first 3-5 minutes of filtration due to the electro-osmotic flow. The electric field results in enhanced bulk liquid motion due to the net surplus of ions in the diffuse part of the electrical double layer formed at the surface of charged pores (Bowen and Clark, 1984; Huisman et al., 1998). This effect decreases at lower current density. Then, the permeate flux dropped around 65% of the initial water flux, followed by a period of stabilization (or slight decrease) between 10 and 90 minutes. The release of O₂ bubbles in the bulk from oxygen evolution at the anode reduces the liquid bulk volume active for filtration. In filtration mode, O₂ gas bubbles are continuously swept from the anode surface and a steady state is reached between the amount of O₂ produced and flushed out from the REM. When current was not anymore supplied, the permeate flux was restored to its initial value in 20 minutes, once all O₂ gas bubbles were flushed out. Very similar behavior was observed using low concentration of PCT. The permeate flux was restored to its initial value and none permeability loss was observed even after several successive experiments. At high concentration of PCT, the drop of the permeate flux was slower and stabilized around 80% of the initial flux, indicating a lower production rate of O₂ gas bubbles. In fact, the increase of the concentration of PCT favors the reaction of [•]OH with organic compounds and hinders the reaction of [•]OH dimerization as well as subsequent reactions leading to the formation of O₂ (Figure 6). Besides, PCT may also increase the overpotential of oxygen evolution, which inhibited the reaction of oxygen evolution. Further electrochemical characterizations would be required in order to clarify the explanation of this phenomenon. The evolution of the permeate flux was also observed to depend on the current density (data not shown). The higher the current density, the higher the

drop of the permeate flux because of the increase of oxygen evolution and generation of a greater amount of O₂ bubbles.

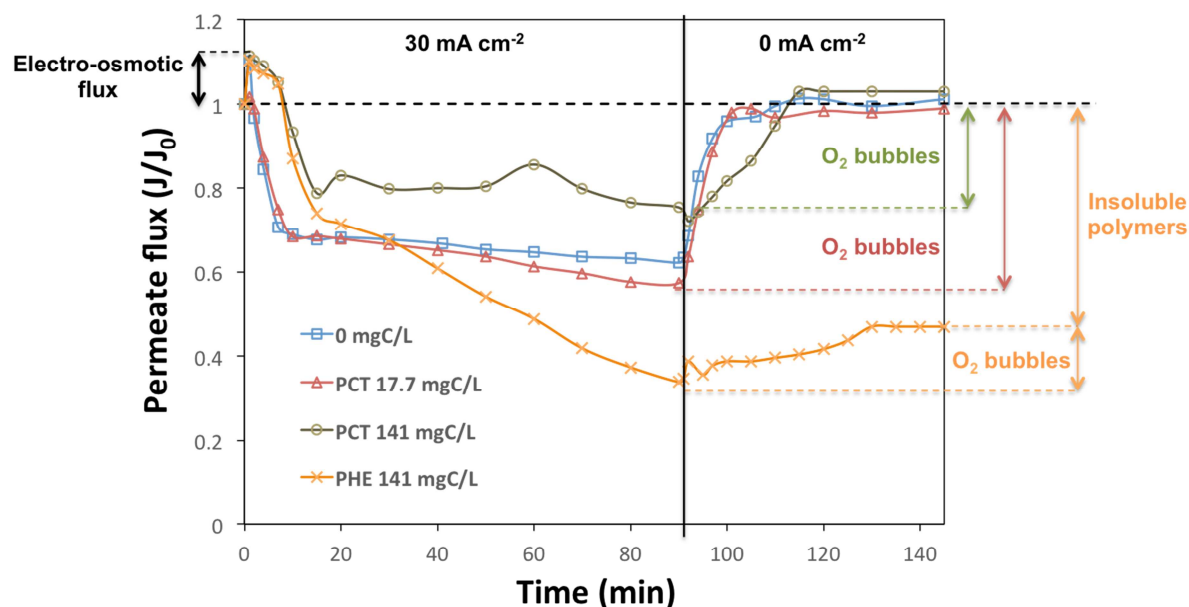


Figure 5. Evolution of the permeate flux during the treatment of paracetamol (PCT) at 17.7 mgC L⁻¹ or 141 mgC L⁻¹, phenol (PHE) at 141 mgC L⁻¹ and in the absence of organic compound. Current density is set at 30 mA cm⁻² during 90 min, then, none current was supplied during 50 min. [Na₂SO₄] = 50 mM. Solid lines represent piece-wise interpolation and are included for easier reading of the figure.

3.2.3 Phenol electro-oxidation

Different results were observed during electro-oxidation of PHE. Permeate flux continuously decreased during the whole experiment and could not be restored to its initial value when current was not anymore supplied. Permeability loss of the REM after 90 min of electro-oxidation is reported in Table 1, according to PHE concentration and current density. REM fouling observed during the treatment of PHE with a high ratio between the PHE concentration and the current density can be explained by taking into account similar electro-oxidation mechanisms than those reported in this study for PCT.

When the concentration of PHE is too high with respect to the current supplied, $\cdot\text{OH}$ produced in the top layer of the REM are not sufficient to oxidize all PHE molecules. Therefore PHE and degradation by-products can react in the deeper reactive layer by DET (Figure 6). While such reaction has been observed to form soluble polymers with PCT (Brillas et al., 2005), it has been widely reported that direct oxidation of PHE at the anode surface lead to the formation of insoluble polymers strongly interacting with the anode surface (Belhadj Tahar and Savall, 2009a; Gao and Vecitis, 2013). Thus, adsorption of polymers led to high percentage of TOC removal and high TOC removal rate of PHE, because large amounts of organic compounds (polymers) were physically retained within the membrane. However, these polymeric films cannot be mineralized. The adsorption of these polymers is responsible of pore blocking or pore size reduction (Figure 6), which results in the irreversible decrease of the REM permeability. At both high current density and high PHE concentration, permeability loss reached its highest level because a greater amount of DET reactions occurred between the pore surface of the deep reactive layer and non- or hardly degraded PHE molecules. However, it was observed that it is possible to avoid REM fouling when performing experiments with a sufficiently high current density with respect to the concentration of PHE (Table 1). The aim is to reach a high mineralization degree and rate of PHE in the top layer of the REM where $\cdot\text{OH}$ are produced in order to avoid direct oxidation of PHE and other aromatic by-products in the deep reactive layer where only DET occurs.

Table 1. Summary and comparison of results obtained for the treatment of paracetamol (PCT) and phenol (PHE) at different concentration and current density. Percentage of TOC removal (PR_{TOC}) of organic pollutants and permeability loss after the experiment have been assessed. All experiments have been performed during 90 min at $\text{TMP} = 40$ mbar.

Pollutant	C (mgC L ⁻¹)	j (mA cm ⁻²)	PR _{TOC} (%)	Permeability loss (%)
PCT	17.7	6	79	<3
PCT	141	30	74	<3
PHE	17.7	6	94	9
PHE	35.5	6	76	13
PHE	141	6	38	17
PHE	17.7	30	>98	<3
PHE	35.5	30	>98	<3
PHE	141	30	95	53


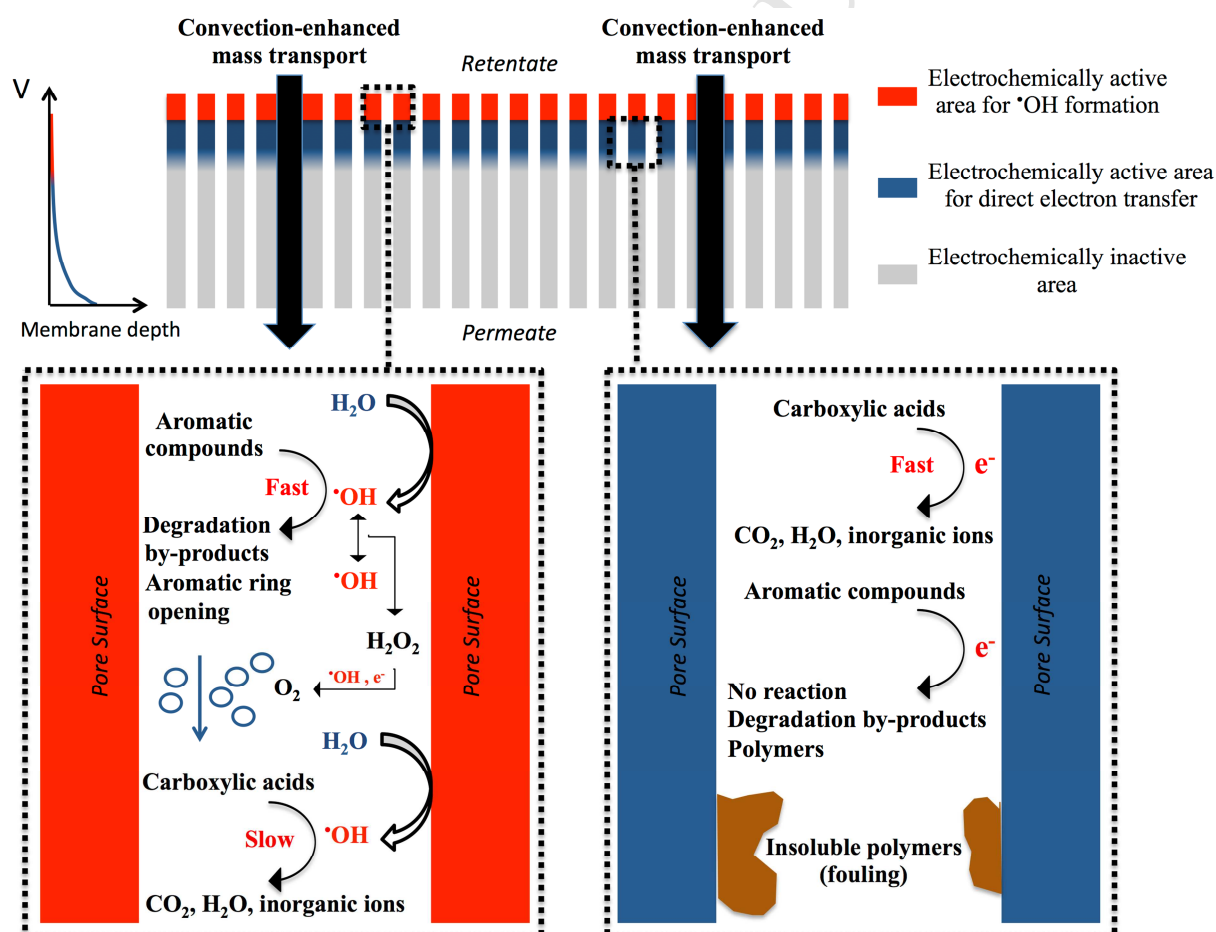


Figure 6. Recapitulative scheme of the main electro-oxidation mechanisms of organic compounds in the reactive electrochemical membrane.

3.2.4 Evolution of the pH

The evolution of the pH was monitored both in the permeate and in the retentate (Figure 7a). During an experiment at 30 mA cm^{-2} and $[\text{PCT}] = 0.18 \text{ mM}$, it was observed a rapid increase of the pH in the retentate (11.1 at $t = 10 \text{ min}$; 11.8 at $t = 30 \text{ min}$), followed by a period of slow increase (12.2 at $t = 90 \text{ min}$). In the permeate, pH rapidly reached a stable value around 1.8. When the feed water is passing through the membrane, H^+ generated from water oxidation at the anode (eq. 2) are accumulated in the permeate due to the convective mass transport. On the contrary, OH^- generated at the cathode (stainless steel rod) are accumulated in the retentate. Stabilized values of pH observed in the permeate according to operating conditions are plotted in Figure 7b. pH was mainly affected by current density and permeate flux. During experiments with PCT as model organic compounds, pH in the permeate ranged between 1.8 and 3.2 according to operating conditions. Lowest pH was observed at high current density (high amount of H^+ generated) and low permeate flux (low dilution of generated H^+). Further investigations would be required in order to emphasize the influence of this pH gradient on electro-oxidation mechanisms and efficiency.

(a)

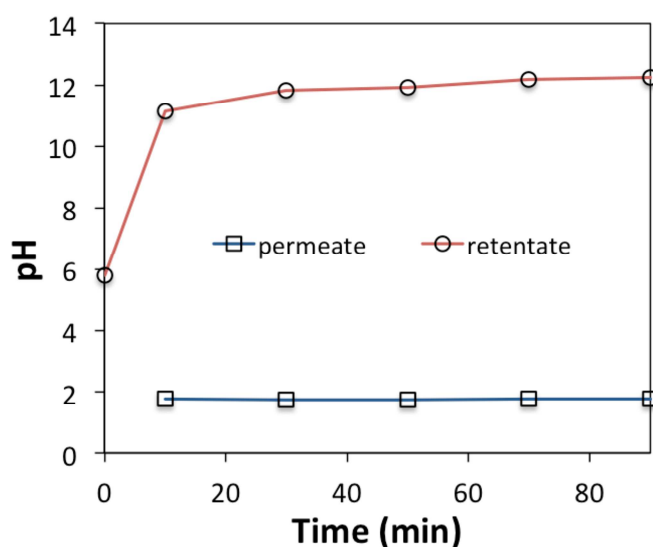

(b)

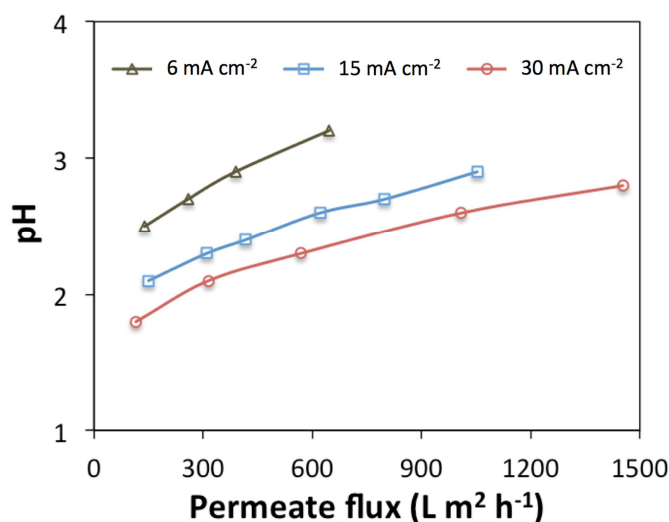


Figure 7. (a) Evolution of the pH in the permeate and in the retentate during the treatment of paracetamol (PCT) at 0.18 mM ($j = 30 \text{ mA cm}^{-2}$; $J = 110 \text{ L h}^{-1} \text{ m}^{-2}$). (b) Stabilized value of pH in the permeate according to current density and permeate flux ([PCT] = 0.18 mM).

3. Conclusion

Unprecedented high efficiency of mineralization of organic compounds is presented in this study by using an innovative REM synthesized from carbothermal reduction of TiO_2 . The homogeneous pore structure (median pore size = $1.4 \mu\text{m}$) and suitable Magnéli

phase synthesized (mixture of Ti_4O_7 and Ti_5O_9) resulted in high permeability ($3,300 \text{ L h}^{-1} \text{ m}^{-2}$), high convection-enhanced mass transfer and excellent reactivity of the REM. From the high TOC removal rates ($6.7 \text{ g m}^{-2} \text{ h}^{-1}$ and $47 \text{ g m}^{-2} \text{ h}^{-1}$ for PCT and OA, respectively, at 15 mA cm^{-2}) and mineralization current efficiency (72% and 47% for PCT and OA, respectively, at 15 mA cm^{-2}) achieved, the great promise of this new water treatment technology has been emphasized. Two limitations have been also highlighted. A decrease of the process efficiency has been observed at high TOC flux due to the effect of ohmic drops within the REM. Hydroxyl radicals can be only generated in the top layer of the REM. Therefore, adverse effects arises from the presence of refractory organic compounds and electro-polymerization in the layer where only DET occurs. In the case of PHE, interaction of electro-generated polymers with the pore surface strongly reduced the membrane permeability (fouling). Besides, at high permeate flux, a decrease of the electro-oxidation efficiency was observed due to enhanced O_2 bubble sweeping from the anode surface, which promotes oxygen evolution reactions. Whatever the organic compound studied, current density appeared as the crucial parameter for limiting these adverse effects. Fortunately, the advantage of electro-oxidation is the possibility to easily tune current intensity in order to adapt the process to effluent concentration and/or permeate flux. While the efficiency of the REM was observed to be constant during this study, the assessment of the long-term lifetime of these electrodes is the focus of ongoing research in order to confirm the suitability of this process for water treatment. Then, the use of REM for the treatment of real effluents will be investigated since particles and colloids in real water matrix may affect the efficiency of the process.

Acknowledgment

We gratefully acknowledge the National French Agency of Research ‘ANR’ for funding the project ECOTS/CELECTRON. Clément Trellu particularly thanks the agency for post-doctoral fellowship. Authors are also grateful to Saint Gobain CREE for supplying reactive electrochemical membranes in the framework of the ANR program.

References

- Almeida, L.C., Garcia-Segura, S., Bocchi, N., Brillas, E., 2011. Solar photoelectro-Fenton degradation of paracetamol using a flow plant with a Pt/air-diffusion cell coupled with a compound parabolic collector: Process optimization by response surface methodology. *Appl. Catal. B Environ.* 103, 21–30. <https://doi.org/10.1016/j.apcatb.2011.01.003>
- Andersson, S., Jahnberg, L., 1963. Crystal structure studies on the homologous series TiO_{2n-1} , VnO_{2n-1} , $\text{Ti}_{n-2}\text{Cr}_{202n-1}$. *Ark. Foer Kemi* 21, 423–426.
- Antonin, V.S., Santos, M.C., Garcia-Segura, S., Brillas, E., 2015. Electrochemical incineration of the antibiotic ciprofloxacin in sulfate medium and synthetic urine matrix. *Water Res.* 83, 31–41. <https://doi.org/10.1016/j.watres.2015.05.066>
- Balci, B., Oturan, N., Cherrier, R., Oturan, M.A., 2009. Degradation of atrazine in aqueous medium by electrocatalytically generated hydroxyl radicals. A kinetic and mechanistic study. *Water Res.* 43, 1924–1934. <https://doi.org/10.1016/j.watres.2009.01.021>
- Belhadj Tahar, N., Savall, A., 2009a. Electrochemical removal of phenol in alkaline solution. Contribution of the anodic polymerization on different electrode materials. *Electrochimica Acta* 54, 4809–4816. <https://doi.org/10.1016/j.electacta.2009.03.086>
- Belhadj Tahar, N., Savall, A., 2009b. Electropolymerization of phenol on a vitreous carbon electrode in alkaline aqueous solution at different temperatures. *Electrochimica Acta*, ELECTROCHEMISTRY WITH SPATIAL AND TEMPORAL RESOLUTION Selection of papers from the 4th Gerischer Symposium 25-27 June 2008, Berlin, Germany 55, 465–469. <https://doi.org/10.1016/j.electacta.2009.08.040>
- Bisby, R.H., Tabassum, N., 1988. Properties of the radicals formed by one-electron oxidation of acetaminophen—A pulse radiolysis study. *Biochem. Pharmacol.* 37, 2731–2738. [https://doi.org/10.1016/0006-2952\(88\)90035-4](https://doi.org/10.1016/0006-2952(88)90035-4)
- Bowen, W.R., Clark, R.A., 1984. Electro-osmosis at microporous membranes and the determination of zeta-potential. *J. Colloid Interface Sci.* 97, 401–409.

- 523 [https://doi.org/10.1016/0021-9797\(84\)90311-4](https://doi.org/10.1016/0021-9797(84)90311-4)
- 524 Brillas, E., Martínez-Huitle, C.A., 2015. Decontamination of wastewaters containing
525 synthetic organic dyes by electrochemical methods. An updated review. *Appl. Catal. B*
526 *Environ.* 166–167, 603–643. <https://doi.org/10.1016/j.apcatb.2014.11.016>
- 527 Brillas, E., Martínez-Huitle, C.A. (Eds.), 2011. *Synthetic Diamond Films: Preparation,*
528 *Electrochemistry, Characterization, and Applications.* John Wiley & Sons, Inc., Hoboken,
529 NJ, USA.
- 530 Brillas, E., Sirés, I., Arias, C., Cabot, P.L., Centellas, F., Rodríguez, R.M., Garrido, J.A., 2005.
531 Mineralization of paracetamol in aqueous medium by anodic oxidation with a boron-
532 doped diamond electrode. *Chemosphere* 58, 399–406.
533 <https://doi.org/10.1016/j.chemosphere.2004.09.028>
- 534 Brillas, E., Sirés, I., Oturan, M.A., 2009. Electro-Fenton process and related
535 electrochemical technologies based on Fenton's reaction chemistry. *Chem. Rev.* 109,
536 6570–6631. <https://doi.org/10.1021/cr900136g>
- 537 Chaplin, B.P., 2014. Critical review of electrochemical advanced oxidation processes for
538 water treatment applications. *Environ. Sci. Process. Impacts.*
539 <https://doi.org/10.1039/C3EM00679D>
- 540 Feng, L., van Hullebusch, E.D., Rodrigo, M.A., Esposito, G., Oturan, M.A., 2013. Removal of
541 residual anti-inflammatory and analgesic pharmaceuticals from aqueous systems by
542 electrochemical advanced oxidation processes. A review. *Chem. Eng. J.* 228, 944–964.
543 <https://doi.org/10.1016/j.cej.2013.05.061>
- 544 Ferro, S., Martínez-Huitle, C.A., Battisti, A.D., 2010. Electrooxidation of oxalic acid at
545 different electrode materials. *J. Appl. Electrochem.* 40, 1779–1787.
546 <https://doi.org/10.1007/s10800-010-0113-y>
- 547 Ganiyu, S.O., Oturan, N., Raffy, S., Cretin, M., Esmilaire, R., van Hullebusch, E., Esposito, G.,
548 Oturan, M.A., 2016. Sub-stoichiometric titanium oxide (Ti4O7) as a suitable ceramic
549 anode for electrooxidation of organic pollutants: A case study of kinetics, mineralization
550 and toxicity assessment of amoxicillin. *Water Res.* 106, 171–182.
551 <https://doi.org/10.1016/j.watres.2016.09.056>
- 552 Ganiyu, S.O., Oturan, N., Raffy, S., Esposito, G., van Hullebusch, E.D., Cretin, M., Oturan,
553 M.A., 2017. Use of Sub-stoichiometric Titanium Oxide as a Ceramic Electrode in Anodic
554 Oxidation and Electro-Fenton Degradation of the Beta-blocker Propranolol: Degradation
555 Kinetics and Mineralization Pathway. *Electrochimica Acta* 242, 344–354.
556 <https://doi.org/10.1016/j.electacta.2017.05.047>
- 557 Ganiyu, S.O., van Hullebusch, E.D., Cretin, M., Esposito, G., Oturan, M.A., 2015. Coupling of
558 membrane filtration and advanced oxidation processes for removal of pharmaceutical
559 residues: A critical review. *Sep. Purif. Technol., Environmental Nanotechnology and*
560 *Sustainability in Water Treatment in honor of Professor Chin-Pao Huang, Ph.D, Harvard*
561 *University, Donald C. Philips, Professor Civil and Environmental Engineering, University*
562 *of Delaware, USA* 156, Part 3, 891–914. <https://doi.org/10.1016/j.seppur.2015.09.059>
- 563 Gao, G., Vecitis, C.D., 2013. Electrocatalysis aqueous phenol with carbon nanotubes

- networks as anodes: Electrodes passivation and regeneration and prevention.
Electrochimica Acta 98, 131–138. <https://doi.org/10.1016/j.electacta.2013.02.127>
- Gao, G., Vecitis, C.D., 2012. Reactive Depth and Performance of an Electrochemical Carbon Nanotube Network as a Function of Mass Transport. ACS Appl. Mater. Interfaces 4, 6096–6103. <https://doi.org/10.1021/am301724n>
- Garcia-Segura, S., Brillas, E., 2011. Mineralization of the recalcitrant oxalic and oxamic acids by electrochemical advanced oxidation processes using a boron-doped diamond anode. Water Res. 45, 2975–2984. <https://doi.org/10.1016/j.watres.2011.03.017>
- Guo, L., Jing, Y., Chaplin, B.P., 2016. Development and Characterization of Ultrafiltration TiO₂ Magnéli Phase Reactive Electrochemical Membranes. Environ. Sci. Technol. 50, 1428–1436. <https://doi.org/10.1021/acs.est.5b04366>
- Hodeau, J.L., Marezio, M., 1979. Structural aspects of the metal-insulator transitions in (Ti_{0.9975}V_{0.0025})₄O₇. J. Solid State Chem. 29, 47–62. [https://doi.org/10.1016/0022-4596\(79\)90208-1](https://doi.org/10.1016/0022-4596(79)90208-1)
- Huisman, I.H., Trägårdh, G., Trägårdh, C., Pihlajamäki, A., 1998. Determining the zeta-potential of ceramic microfiltration membranes using the electroviscous effect. J. Membr. Sci. 147, 187–194. [https://doi.org/10.1016/S0376-7388\(98\)00135-5](https://doi.org/10.1016/S0376-7388(98)00135-5)
- Jing, Y., Guo, L., Chaplin, B.P., 2016. Electrochemical impedance spectroscopy study of membrane fouling and electrochemical regeneration at a sub-stoichiometric TiO₂ reactive electrochemical membrane. J. Membr. Sci. 510, 510–523. <https://doi.org/10.1016/j.memsci.2016.03.029>
- Kapałka, A., Fóti, G., Comninellis, C., 2009. The importance of electrode material in environmental electrochemistry: Formation and reactivity of free hydroxyl radicals on boron-doped diamond electrodes. Electrochimica Acta, ELECTROCHEMISTRY FOR A HEALTHY PLANET ENVIRONMENTAL ANALYTICAL AND ENGINEERING ASPECTS Selection of papers from the 6th ISE Spring Meeting 16-19 March 2008, Foz do Iguaçu, Brazil 54, 2018–2023. <https://doi.org/10.1016/j.electacta.2008.06.045>
- Kapałka, A., Fóti, G., Comninellis, C., 2008. Kinetic modelling of the electrochemical mineralization of organic pollutants for wastewater treatment. J. Appl. Electrochem. 38, 7–16. <https://doi.org/10.1007/s10800-007-9365-6>
- Land, E.J., Ebert, M., 1967. Pulse radiolysis studies of aqueous phenol. Water elimination from dihydroxycyclohexadienyl radicals to form phenoxyl. Trans. Faraday Soc. 63, 1181–1190. <https://doi.org/10.1039/TF9676301181>
- Lasia, A., 2008. Modeling of Impedance of Porous Electrodes, in: Modeling and Numerical Simulations, Modern Aspects of Electrochemistry. Springer New York, pp. 67–137. https://doi.org/10.1007/978-0-387-49582-8_3
- Latimer, W.M., 1952. Oxidation Potentials. Prentice-Hall.
- Liu, Y., Liu, H., Zhou, Z., Wang, T., Ong, C.N., Vecitis, C.D., 2015. Degradation of the Common Aqueous Antibiotic Tetracycline using a Carbon Nanotube Electrochemical Filter. Environ. Sci. Technol. 49, 7974–7980. <https://doi.org/10.1021/acs.est.5b00870>

- 604 Martínez-Huitle, C.A., Rodrigo, M.A., Sirés, I., Scialdone, O., 2015. Single and Coupled
 605 Electrochemical Processes and Reactors for the Abatement of Organic Water Pollutants:
 606 A Critical Review. *Chem. Rev.* 115, 13362–13407.
 607 <https://doi.org/10.1021/acs.chemrev.5b00361>
- 608 Martínez-Huitle, C.A., Ferro, S., De Battisti, A., 2004. Electrochemical incineration of
 609 oxalic acid: Role of electrode material. *Electrochimica Acta*, The role of electrochemistry
 610 in the sustained development of modern societies 49, 4027–4034.
 611 <https://doi.org/10.1016/j.electacta.2004.01.083>
- 612 Moreira, F.C., Boaventura, R.A.R., Brillas, E., Vilar, V.J.P., 2017. Electrochemical advanced
 613 oxidation processes: A review on their application to synthetic and real wastewaters.
 614 *Appl. Catal. B Environ.* 202, 217–261. <https://doi.org/10.1016/j.apcatb.2016.08.037>
- 615 Oturan, N., van Hullebusch, E.D., Zhang, H., Mazeas, L., Budzinski, H., Le Menach, K.,
 616 Oturan, M.A., 2015. Occurrence and Removal of Organic Micropollutants in Landfill
 617 Leachates Treated by Electrochemical Advanced Oxidation Processes. *Environ. Sci.*
 618 *Technol.* 49, 12187–12196. <https://doi.org/10.1021/acs.est.5b02809>
- 619 Özcan, A., Sahin, Y., Koparal, A.S., Oturan, M.A., 2008. Prophan mineralization in aqueous
 620 medium by anodic oxidation using boron-doped diamond anode: Influence of
 621 experimental parameters on degradation kinetics and mineralization efficiency. *Water*
 622 *Res.* 42, 2889–2898. <https://doi.org/10.1016/j.watres.2008.02.027>
- 623 Panizza, M., Cerisola, G., 2009. Direct and mediated anodic oxidation of organic
 624 pollutants. *Chem. Rev.* 109, 6541–6569. <https://doi.org/10.1021/cr9001319>
- 625 Panizza, M., Michaud, P.A., Cerisola, G., Comninellis, C., 2001. Anodic oxidation of 2-
 626 naphthol at boron-doped diamond electrodes. *J. Electroanal. Chem.* 507, 206–214.
 627 [https://doi.org/10.1016/S0022-0728\(01\)00398-9](https://doi.org/10.1016/S0022-0728(01)00398-9)
- 628 Radjenovic, J., Sedlak, D.L., 2015. Challenges and Opportunities for Electrochemical
 629 Processes as Next-Generation Technologies for the Treatment of Contaminated Water.
 630 *Environ. Sci. Technol.* 49, 11292–11302. <https://doi.org/10.1021/acs.est.5b02414>
- 631 Ronen, A., Walker, S.L., Jassby, D., 2016. Electroconductive and electroresponsive
 632 membranes for water treatment. *Rev. Chem. Eng.* 32. [https://doi.org/10.1515/revce-](https://doi.org/10.1515/revce-2015-0060)
 633 2015-0060
- 634 Schnoor, M.H., Vecitis, C.D., 2013. Quantitative Examination of Aqueous Ferrocyanide
 635 Oxidation in a Carbon Nanotube Electrochemical Filter: Effects of Flow Rate, Ionic
 636 Strength, and Cathode Material. *J. Phys. Chem. C* 117, 2855–2867.
 637 <https://doi.org/10.1021/jp3112099>
- 638 Trellu, C., Péchaud, Y., Oturan, N., Mousset, E., Huguenot, D., Hullebusch, E.D. van,
 639 Esposito, G., Oturan, M.A., 2016. Comparative study on the removal of humic acids from
 640 drinking water by anodic oxidation and electro-Fenton processes: Mineralization
 641 efficiency and modelling. *Appl. Catal. B Environ.* 194, 32–41.
 642 <https://doi.org/10.1016/j.apcatb.2016.04.039>
- 643 Tsierkezos, N.G., Ritter, U., 2012. Electrochemical and thermodynamic properties of
 644 hexacyanoferrate(II)/(III) redox system on multi-walled carbon nanotubes. *J. Chem.*

- 645 Thermodyn. 54, 35–40. <https://doi.org/10.1016/j.jct.2012.03.018>
- 646 Walsh, F.C., Wills, R.G.A., 2010. The continuing development of Magnéli phase titanium
647 sub-oxides and Ebonex® electrodes. *Electrochimica Acta* 55, 6342–6351.
648 <https://doi.org/10.1016/j.electacta.2010.05.011>
- 649 Weiss, E., Groenen-Serrano, K., Savall, A., Comninellis, C., 2007. A kinetic study of the
650 electrochemical oxidation of maleic acid on boron doped diamond. *J. Appl. Electrochem.*
651 37, 41–47. <https://doi.org/10.1007/s10800-006-9212-1>
- 652 Yang, J., Wang, J., Jia, J., 2009. Improvement of Electrochemical Wastewater Treatment
653 through Mass Transfer in a Seepage Carbon Nanotube Electrode Reactor. *Environ. Sci.*
654 *Technol.* 43, 3796–3802. <https://doi.org/10.1021/es8034285>
- 655 Zaky, A.M., Chaplin, B.P., 2014. Mechanism of p-Substituted Phenol Oxidation at a Ti407
656 Reactive Electrochemical Membrane. *Environ. Sci. Technol.* 48, 5857–5867.
657 <https://doi.org/10.1021/es5010472>
- 658 Zaky, A.M., Chaplin, B.P., 2013. Porous Substoichiometric TiO₂ Anodes as Reactive
659 Electrochemical Membranes for Water Treatment. *Environ. Sci. Technol.* 47, 6554–6563.
660 <https://doi.org/10.1021/es401287e>

661