



Short communication

Organic dispersion of polyaniline and single-walled carbon nanotubes and polyblends with poly(methyl methacrylate)

Thomas Farrell ^a, Kan Wang ^a, Cheng-Wei Lin ^a, Richard B. Kaner ^{a, b, *}^a Department of Chemistry and Biochemistry and California NanoSystems Institute, University of California, Los Angeles, Los Angeles, CA, 90095, USA^b Department of Materials Science and Engineering, University of California, Los Angeles, Los Angeles, CA, 90095, USA

ARTICLE INFO

Article history:

Received 27 June 2017

Received in revised form

11 September 2017

Accepted 14 September 2017

Available online 17 September 2017

Keywords:

Polyaniline

Composites

Dispersions

ABSTRACT

Traditionally, *in situ* polymerization has been used to make polymer-carbon nanotube composites. Here, we report a simple method of mixing polyaniline with single-walled carbon nanotubes in a variety of organic solvents via ultrasonication. The maximum loading fraction of SWCNTs in the composites is determined by the conformation of the polyaniline chains. The type of solvent used has the greatest influence on the conformation of the polyaniline chains. Furthermore, the composites can be easily blended with poly(methyl methacrylate) (PMMA), to form polyblends. The electrical conductivities and transparencies of the polyblend films are reported.

© 2017 Elsevier Ltd. All rights reserved.

1. Introduction

Since its rediscovery, polyaniline (PANI) has been one of the most studied conducting polymers due to its excellent chemical stability, relatively high conductivity and low cost. Conducting PANI solutions can be prepared in select organic solvents including toluene, m-cresol and chloroform, with the use of a compatible protonic acid, such as dodecylbenzene sulfonic acid (DBSA) or camphorsulfonic acid (CSA) [1]. This counter-ion induced processability enables the creation of solution processable conductive polyblends of PANI and the desired insulating bulk polymer. However, the conductivity of PANI is lower than most metals, and its low strength may also hinder the mechanical properties of the polyblends [2,3]. A good alternative to PANI as a conductive filler is carbon nanotubes (CNTs), a lightweight nanomaterial, which exhibits high electrical conductivities and excellent mechanical properties [2,4–6]. Unfortunately poor processability limits the applications of CNTs. Although the use of non-conductive surfactants [7] or the introduction of functional groups [8] can improve the solubility of CNTs in a variety of solvents, the conductivity will inevitably be diminished due to the insulating nature of the

surfactants [9] and the destruction of long range π conjugation [10]. On the other hand, several studies [11,12] indicate that PANI and CNTs can interact strongly through π - π interactions between the conjugated polymer chains and the carbon nanotube walls. Thus, it seems logical that a dispersible PANI-CNT composite could overcome the limitations of each component. Progress has been made in recent years to prepare PANI/CNT composites dispersed in either aqueous or organic media [13–18]. Yet most syntheses have focused on a single solvent and adopted an *in situ* polymerization method [19–21], which makes control over CNT loading difficult. Moreover, there are rare reports on PANI-CNT composite dispersions in polyblends with other bulk polymers [22]. Here, we report a facile method to prepare well-dispersed polyaniline and single-walled carbon nanotube (PANI-SWCNT) composites in a variety of organic solvent systems via simple ultrasonication. The PANI-SWCNT dispersions can be further mixed with other co-soluble polymers, such as PMMA at various ratios to obtain conductive polyblend solutions (see ESI† experimental section and Scheme S1 for details).

2. Results and discussion

In a typical synthesis, a desired loading of SWCNTs (relative to the content of PANI base) is added to a ~2% PANI/DBSA chloroform solution. The mixture is placed under ultrasonication overnight to obtain a dark homogeneous dispersion. The dispersion can be either centrifuged or filtered through glass wool to remove any

* Corresponding author. Department of Chemistry and Biochemistry and California NanoSystems Institute, University of California, Los Angeles, Los Angeles, CA, 90095, USA.

E-mail address: kaner@chem.ucla.edu (R.B. Kaner).

possible minor insoluble solids. Actually, only the sample with 100% SWCNT loading showed an appreciable amount of precipitate when centrifuged at 4500 rpm for 10 min. The dispersion with 10% SWCNT loading is named PANI/0.1SWCNT and so forth.

The as-prepared PANI-SWCNT composites form very stable dispersions in chloroform (Fig. 1a). No visible precipitate shows up for months in dispersions with up to 50% SWCNT loading. The composite with 100% SWCNT loading, however, begins to precipitate within days, which indicates that the SWCNTs are not fully wrapped by the PANI chains (Fig. 1b). Scanning electron microscopy (SEM) and transmission electron microscopy (TEM) images (Fig. 1c and d) reveal that SWCNTs in the composites are well dispersed with an average diameter of 20–30 nm for each bundle. The SWCNTs form well-connected conductive pathways throughout the composite. Metal catalysts from the synthesis of the SWCNTs are also observed as randomly distributed nanoparticles. Interestingly, it is difficult to observe the SWCNTs in the spin-coated films under SEM at first glance because they are so well hidden in the polymer matrix. As the same sample area is exposed to the electron beam for an extended time, the polymer is gradually burned away, revealing the SWCNT network underneath (see ESI† Fig. S1).

UV-vis spectra were collected for dilute PANI and PANI-SWCNT dispersions (see ESI† Fig. S2). Due to the high doping level, the π to π^* transition at ~ 360 nm and the polaron to π^* transition at ~ 430 nm are combined into one single distorted peak [23]. The peak observed at ~ 800 nm corresponds to the π to polaron transition [24]. As the SWCNT loading increases, the spectra gradually approach that of pure carbon nanotubes.

FT-IR spectra of all PANI and PANI-SWCNT samples show characteristic peaks for pristine polyaniline (see ESI† Fig. S3). The peaks at 1560 cm^{-1} , 1485 cm^{-1} , 1307 cm^{-1} , 1226 cm^{-1} , and 1147 cm^{-1} are assigned to PANI's quinoid C=C stretching, benzenoid C=C stretching, C-N stretching of secondary aromatic amines on the

PANI backbone, the C-N⁺ stretching vibration in the polaron structure, and the vibrational mode of the -NH⁺ = structure (electronic-like band), respectively [25]. In contrast to some PANI-CNT composites fabricated by *in situ* polymerization [11,14,15], the quinoid/benzenoid ratio (I_{1560}/I_{1485}) does not show a significant change as the loading of SWCNTs increase.

The PANI-SWCNT composite dispersions were spin-coated into transparent thin films (see ESI† Fig. S5). Not surprisingly, the presence of SWCNTs greatly enhances the conductivities of the composites, while maintaining relatively high transmittances (see ESI† Table S1). The films with 0%, 10%, 25%, 50% and 100% SWCNT loadings have conductivities of 1.0 S/cm, 7.2 S/cm, 19.2 S/cm, 33.4 S/cm and 36.9 S/cm, respectively. At the same time the corrected transmittance at 580 nm only decreases from 88.5% to 79.9%. The transmittance was measured at 580 nm, and corrected to that of a 100 nm thick film. The conductivity increases sharply even with a 10% loading, indicating the formation of a well-connected conductive SWCNT network in the composite film.

The PANI-SWCNT composite dispersions can be further mixed with PMMA dissolved in chloroform to create homogeneous polyblend solutions without any visible particles. Highly transparent thin films are fabricated out of the polyblend solutions by spin-coating (Fig. 2a). The microscopic images (Fig. 2b and c) show that the existence of SWCNTs effectively reinforces the film due to its excellent mechanical strength, therefore the number of cracks in the film caused by the surface tension upon drying is reduced. The SEM image (Fig. 2d) also reveals that SWCNTs are randomly dispersed and well bridged in the polymer matrix. Due to the high aspect ratio of the SWCNTs [26], the conductivity percolation threshold of the polyblends is exceeded at a loading of less than 5 wt% PANI-SWCNT (Fig. 2e, ESI† Table S2), while the resistance of the film without SWCNTs goes beyond the instrument's limit even at higher loading percentages.

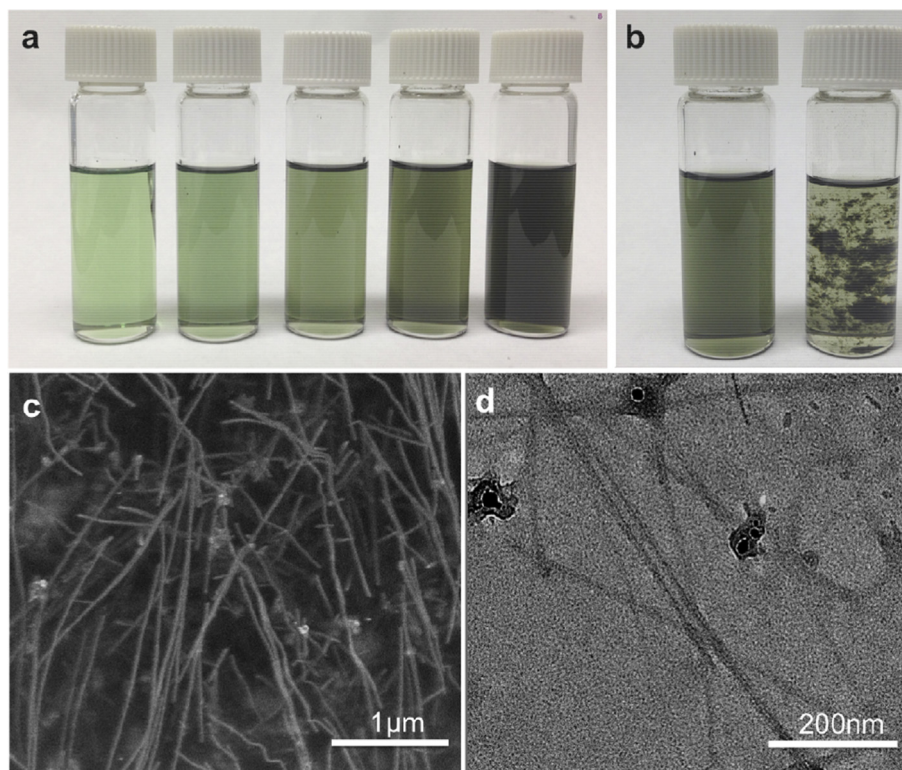


Fig. 1. (a) From left to right: diluted PANI/DBSA chloroform solutions with 0%, 10%, 25%, 50% and 100% SWCNT loadings, respectively; (b) PANI/0.5SWCNT dispersion (left) and PANI/1.0SWCNT dispersion (right) after one month; (c) SEM and (d) TEM images of diluted PANI/0.5SWCNT dispersion from the DBSA/ CHCl_3 system.

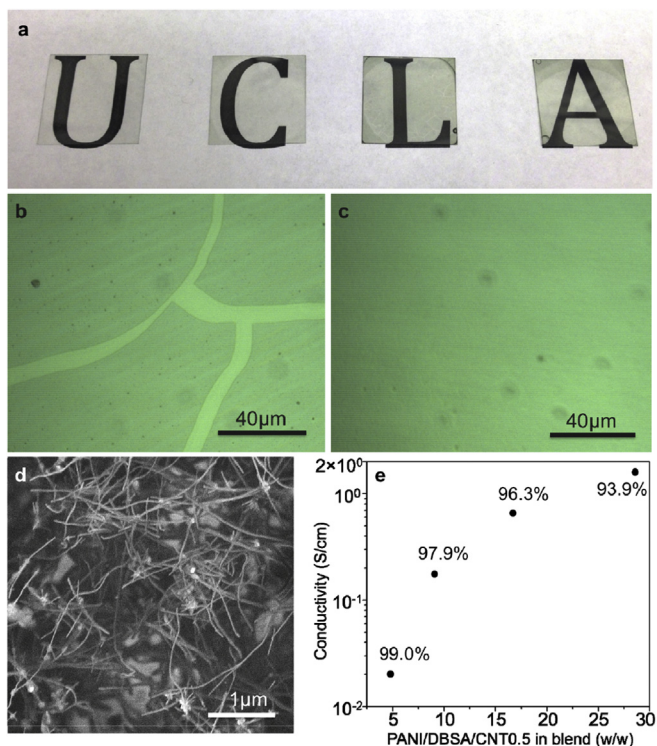


Fig. 2. (a) Spin-coated films of PANI/0.5SWCNT and PMMA polyblends from the DBSA/ CHCl_3 system; the loading fractions of conductive filler are 4.8 wt%, 9.1 wt%, 16.7 wt% and 28.6 wt% from left to right, respectively; the high transparencies of the spin-coated films on glass squares offer clear views of UCLA printed on the paper underneath; microscopic image of (b) PANI and PMMA polyblend film, (c) PANI/0.5SWCNT and PMMA polyblend film, both with 9.1 wt% of conductive filler; (d) a close-up SEM image of film (c); (e) the conductivity and transmittance (at 580 nm) for films in (a), the transmittance is corrected based on a 100 nm thickness.

Dispersions of PANI-SWCNT composites can also be prepared in a variety of other common dopant/solvent systems. However, the

maximum loading of SWCNTs varies greatly in each system. For example, SWCNTs disperse poorly in the HCOOH/HCOOH and CSA/chloroform systems, while it exhibits a much better dispersibility in the DBSA/toluene, DBSA/chloroform and CSA/m-cresol systems (see ESI† Table S3). SEM images (Fig. 3a, b) reveal quite different morphologies of PANI-SWCNT composites in a poor system (CSA/ CHCl_3) and a good system (CSA/m-cresol). In the former one, polymer chains tend to agglomerate with each other instead of wrapping the carbon nanotubes, resulting in a very limited loading of SWCNTs. In the latter system, however, no agglomeration of PANI is observed and the SWCNTs are well dispersed in the polymer matrix, which serves as a good surfactant. This morphology difference is also confirmed by UV-vis-NIR spectra (ESI† Fig. S4). PANI and PANI-SWCNT films cast out of good systems exhibit a steadily increasing free carrier tail commencing at ~ 1000 nm, indicative of polymer chains in an “expanded coil” conformation [27,28]. However, the spectra from poor systems show localized polaron absorption rather than the free carrier tail, indicating a “compact coil” conformation of polymer chains due to little solvation. It is obvious that a more expanded conformation can wrap carbon nanotubes more effectively through π - π interactions (Fig. 3c). Interestingly, this “expanded coil” conformation increases not only the loading of SWCNTs, but also the conductivity of PANI itself due to the reduction of π defects caused by ring twisting.

3. Conclusions

In summary, we report a facile method to produce stable PANI-SWCNT composite dispersions in a variety of organic solvent systems by simple ultrasonication. The type of solvent used determines the conformation of polyaniline chains. The existence of SWCNTs greatly enhances the conductivity of the composites. The composites can be readily processed into transparent thin films in polyblends with desired bulk polymers such as PMMA. The maximum loading fraction of SWCNTs in different organic systems is determined by the conformation of the PANI chains in the solvent.

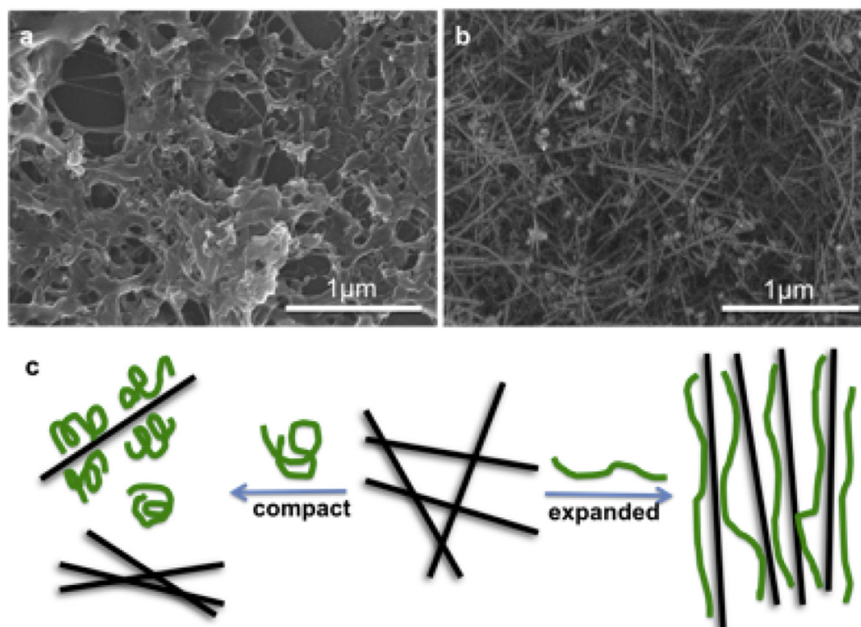


Fig. 3. SEM images of PANI/0.25SWCNT in the system of (a) CSA/ CHCl_3 and (b) CSA/m-cresol; (c) a more “expanded coil” conformation of PANI acts as a good surfactant while the “compact coil” form does not.

Acknowledgements

We thank Dr. Wanmei Sun for scanning electron microscopy, and Pengyu Sun for the profilometry measurements and the National Science Foundation CBET Grant 1337065 for financial support.

Appendix A. Supplementary data

Supplementary data related to this article can be found at <https://doi.org/10.1016/j.polymer.2017.09.032>.

References

- [1] Y. Cao, P. Smith, A.J. Heeger, Counterion induced processability of conducting polyaniline and of conducting polyblends of polyaniline in bulk polymers, *Synth. Met.* 48 (1) (1992) 91–97.
- [2] M. in het Panhuis, Carbon nanotubes: enhancing the polymer building blocks for intelligent materials, *J. Mater. Chem.* 16 (2006) 3598–3605.
- [3] C. Oueiny, S. Berlioz, F.-X. Perrin, Carbon nanotube-polyaniline composites, *Prog. Polym. Sci.* 39 (4) (2014) 707–748.
- [4] W. Zhao, Y. Li, S. Wu, D. Wang, X. Zhao, F. Xu, M. Zou, H. Zhang, X. He, A. Cao, Highly stable carbon nanotube/polyaniline porous network for multifunctional applications, *ACS Appl. Mater. Interfaces* 8 (49) (2016) 34027–34033.
- [5] S. Ghoshal, P.-H. Wang, P. Gulgunje, N. Verghese, S. Kumar, High impact strength polypropylene containing carbon nanotubes, *Polymer* 100 (2016) 259–274.
- [6] P.-H. Wang, S. Ghoshal, P. Gulgunje, S. Kumar, Polypropylene nanocomposites with polymer coated multiwall carbon nanotubes, *Polymer* 100 (2016) 244–258.
- [7] V.C. Moore, M.S. Strano, E.H. Haroz, R.H. Hauge, R.E. Smalley, J. Schmidt, Y. Talmon, Individually suspended single-walled carbon nanotubes in various surfactants, *Nano Lett.* 3 (10) (2003) 1379–1382.
- [8] H. Hu, B. Zhao, M.E. Itkis, R.C. Haddon, Nitric acid purification of single-walled carbon nanotubes, *J. Phys. Chem. B* 107 (50) (2003) 13838–13842.
- [9] H.-Z. Geng, K.K. Kim, K.P. So, Y.S. Lee, Y. Chang, Y.H. Lee, Effect of acid treatment on carbon nanotube-based flexible transparent conducting films, *J. Am. Chem. Soc.* 129 (25) (2007) 7758–7759.
- [10] X. Zhang, T.V. Sreekumar, T. Liu, S. Kumar, Properties and structure of nitric acid oxidized single wall carbon nanotube films, *J. Phys. Chem. B* 108 (42) (2004) 16435–16440.
- [11] H. Zengin, W. Zhou, J. Jin, R. Czerw, D.W. Smith, L. Echegoyen, D.L. Carroll, S.H. Foulger, J. Ballato, Carbon nanotube doped polyaniline, *Adv. Mater.* 14 (20) (2002) 1480–1483.
- [12] M. Cochet, W.K. Maser, A.M. Benito, M.A. Callejas, M.T. Martinez, J.-M. Benoit, J. Schreiber, O. Chauvet, Synthesis of a new polyaniline/nanotube composite: “in-situ” polymerization and charge transfer through site-selective interaction, *Chem. Comm.* (2001) 1450–1451.
- [13] E. Zelikman, M. Narkis, A. Siegmann, L. Valentini, J.M. Kenny, Polyaniline/multiwalled carbon nanotube systems: dispersion of CNT and CNT/PANI interaction, *Polym. Eng. Sci.* 48 (10) (2008) 1872–1877.
- [14] R. Sainz, W.R. Small, N.A. Young, C. Vallés, A.M. Benito, W.K. Maser, M. in het Panhuis, Synthesis and properties of optically active polyaniline carbon nanotube composites, *Macromolecules* 39 (21) (2006) 7324–7332.
- [15] Y. Liao, C. Zhang, Y. Zhang, V. Strong, J. Tang, X. Li, K. Kalantar-Zadeh, E.M. V Hoek, K.L. Wang, R.B. Kaner, Carbon nanotube/polyaniline composite nanofibers: facile synthesis and chemosensors, *Nano Lett.* 11 (3) (2011) 954–959.
- [16] S.G. Vaidya, S. Rastogi, A. Aguirre, Surfactant assisted processable organic nanocomposite dispersions of polyaniline-single wall carbon nanotubes, *Synth. Met.* 160 (1) (2010) 134–138.
- [17] E. Zelikman, R.Y. Suckeveriene, G. Mechrez, M. Narkis, Fabrication of composite polyaniline/CNT carbon nanofibers using an ultrasonically assisted dynamic inverse emulsion polymerization technique, *Polym. Adv. Technol.* 21 (2) (2010) 150–152.
- [18] R.Y. Suckeveriene, G. Mechrez, O. Hachamo Filiba, S. Mosheev, M. Narkis, Synthesis of hybrid polyaniline/carbon nanotubes nanocomposites in toluene by dynamic interfacial inverse emulsion polymerization under sonication, *J. Appl. Polym. Sci.* 128 (3) (2013) 2129–2135.
- [19] S.-Y. Lee, J.-I. Kim, S.-J. Park, Activated carbon nanotubes/polyaniline composites as supercapacitor electrodes, *Energy* 78 (2014) 298–303.
- [20] N. Gull, S.M. Khan, A. Islam, S. Zia, M. Shafiq, A. Sabir, M.A. Munawar, M.T.Z. Butt, T. Jamil, Effect of different oxidants on polyaniline/single wall carbon nanotubes composites synthesized via ultrasonically initiated in-situ chemical polymerization, *Mater. Chem. Phys.* 172 (2016) 39–46.
- [21] N.A. Ogurtsov, Y.V. Noskov, V.N. Bliznyuk, V.G. Ilyin, J.-L. Wojkiewicz, E.A. Fedorenko, A.A. Pud, Evolution and interdependence of structure and properties of nanocomposites of multiwall carbon nanotubes with polyaniline, *J. Phys. Chem. C* 120 (1) (2016) 230–242.
- [22] Q. Wang, X. Qian, S. Wang, W. Zhou, H. Guo, X. Wu, J. Li, X. Wang, Conductive polyaniline composite films from aqueous dispersions: performance enhancement by multi-walled carbon nanotube, *Synth. Met.* 199 (2015) 1–7.
- [23] S. Valiavalappil, S. Harinipriya, Electrically conducting nylon 6,6-polyaniline short composite fibers synthesised by the solvent coagulation method, *Synth. Met.* 162 (23) (2012) 2027–2032.
- [24] M.G. Han, S.K. Cho, S.G. Oh, S.S. Im, Preparation and characterization of polyaniline nanoparticles synthesized from DBSA micellar solution, *Synth. Met.* 126 (1) (2002) 53–60.
- [25] M. Trchová, J. Stejskal, Polyaniline: the infrared spectroscopy of conducting polymer nanotubes, *Pure Appl. Chem.* 83 (10) (2011) 1803–1817.
- [26] J. Li, P.C. Ma, W.S. Chow, C.K. To, B.Z. Tang, J.-K. Kim, Correlations between percolation threshold, dispersion state, and aspect ratio of carbon nanotubes, *Adv. Funct. Mater.* 17 (16) (2007) 3207–3215.
- [27] A. MacDiarmid, A.J. Epstein, The concept of secondary doping as applied to polyaniline, *Synth. Met.* 65 (2–3) (1994) 103–116.
- [28] A.G. MacDiarmid, A.J. Epstein, Secondary doping in polyaniline, *Synth. Met.* 69 (1–3) (1995) 85–92.