



Double-shot inkjet printing for high-conductivity polymer electrode



Sejeong Yoon^{a,1}, Sunyoung Sohn^{b,1}, Jimin Kwon^b, Ju An Park^b, Sungjune Jung^{a,b}

^a The School of Interdisciplinary Bioscience and Bioengineering, Pohang University of Science and Technology, Pohang 37673, South Korea

^b Department of Creative IT Engineering, Pohang University of Science and Technology, Pohang 37673, South Korea

ARTICLE INFO

Article history:

Received 13 January 2016

Received in revised form 25 March 2016

Accepted 31 March 2016

Available online 4 April 2016

Keywords:

Inkjet-printing

PEDOT:PSS

Conductivity

Polymer electrode

ABSTRACT

This paper presents a printing method to form a high-conductivity patterned poly(3,4-ethylenedioxythiophene):poly(styrenesulfonate) (PEDOT:PSS) film. A modified PEDOT:PSS ink containing a secondary dopant (dimethyl sulfoxide) and fluorosurfactant (Zonyl FS-300) was inkjet-printed to form a uniform conducting layer, and the dimethyl sulfoxide, conductivity enhancer, was over-printed onto it to further enhance its conductivity. We achieved high-conductivity greater than 1000 S cm^{-1} by only using inkjet-printing technique. The mechanism of conductivity enhancement was investigated with X-ray photoelectron spectroscopy and atomic force microscopy analyses. The printing process for high-conductivity PEDOT:PSS was applied to pattern a transparent anode for the fabrication of an organic light emitting diode.

© 2016 Elsevier B.V. All rights reserved.

1. Introduction

Poly(3,4-ethylenedioxythiophene):poly(styrenesulfonate) (PEDOT:PSS) has been considered as one of the promising soft electrode materials for emerging flexible and printed electronic devices such as organic light emitting diodes (OLEDs) [1,2], organic solar cells [3,4] and organic electronic circuits [5–8]. Although a pristine PEDOT:PSS film shows very low conductivity below 1 S cm^{-1} , with the addition of a secondary dopant such as dimethyl sulfoxide (DMSO) and ethylene glycol (EG) the conductivity can be improved by 2–3 orders of magnitude, typically $600\text{--}700 \text{ S cm}^{-1}$ for spin-coated films [9–11]. But, this value does not meet the requirement for the electronic applications, and several post-treatment methods have been devised in order to further increase its conductivity to over 1000 S cm^{-1} . Chou et al. dropped a small amount of DMSO directly onto a spin-coated PEDOT:PSS film to increase its conductivity up to $\sim 1000 \text{ S cm}^{-1}$ [12]. More recently, Alemu et al. combined both methods (dropping & dipping of Methanol) and had the conductivity of a spin-coated PEDOT:PSS film enhanced to over 1300 S cm^{-1} [13]. Higher conductivity of $\sim 1400 \text{ S cm}^{-1}$ was achieved by dipping spin-coated samples into an EG bath for 30 min [14]. Although these post-treatments are simple and can be easily used in laboratories, they may not be applicable to roll-to-roll manufacturing of patterned flexible and transparent electrodes with high-conductivity.

This paper presents a printing method to form a high-conductivity patterned PEDOT:PSS film. We used inkjet printing technology with high positional accuracy, high speed and roll-to-roll processability. The optimized printing condition was examined to form a uniform and

smooth PEDOT:PSS film, and the film was then post-processed with the same inkjet nozzle to achieve higher conductivity. We discuss the effect of printing a secondary dopant on the film with X-ray photoelectron spectroscopy (XPS) and atomic force microscopy (AFM). Finally, the suggested printing method was applied to fabricate an OLEDs.

2. Experimental details

Conducting PEDOT:PSS dissolved in water was used in this work (Clevios PH 1000, Heraeus). The solid content of the PH 1000 solution was 1–1.3% and had a PEDOT to PSS ratio of 1:2.5 by weight. 5 wt% of DMSO (Sigma-Aldrich) was added into the PEDOT:PSS to enhance conductivity. The surface tension of the solution was modified by adding fluorosurfactant (Zonyl FS-300, Sigma-Aldrich). The equilibrium surface tension was measured at $23 \text{ }^\circ\text{C}$ with a bubble tensiometer (SITA pro line t15) and was significantly reduced from 72 m Nm^{-1} to 21 mN m^{-1} . The rheological property of the modified-PEDOT:PSS solution (m-PEDOT:PSS) can be found elsewhere [15].

The modified PEDOT:PSS ink, m-PEDOT:PSS, was deposited to form a conductive film onto a glass substrate (Eagle XG, Corning) using a high-resolution inkjet-printing system (Jetlab II, MicroFab) with a piezoelectric printhead (MJ-A, $40 \text{ }\mu\text{m}$ nozzle, MicroFab). The ink was filtered with a $0.45 \text{ }\mu\text{m}$ membrane filter before jetting. A square shaped unipolar control waveform with rise and fall times of $5 \text{ }\mu\text{s}$ and a dwell time of $25 \text{ }\mu\text{s}$ was sent to the printhead to eject a fine drop at the speed of $\sim 5 \text{ ms}^{-1}$ and at the frequency of 500 Hz. The temperature of the printing substrate was maintained at $40 \text{ }^\circ\text{C}$. The ejected conducting ink formed a single main drop within $230 \text{ }\mu\text{s}$ and no satellite drops were generated under the jetting condition. After being annealed at $120 \text{ }^\circ\text{C}$, the conductivity of the printed film was further enhanced by overprinting DMSO along its surface with the same nozzle. The

E-mail address: sjjung@postech.ac.kr (S. Jung).

¹ Equally contributed.

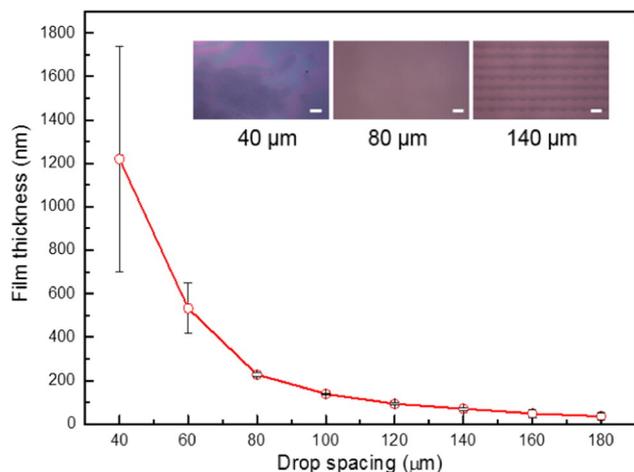


Fig. 1. Variation in film thickness against drop spacing for printed PEDOT:PSS.

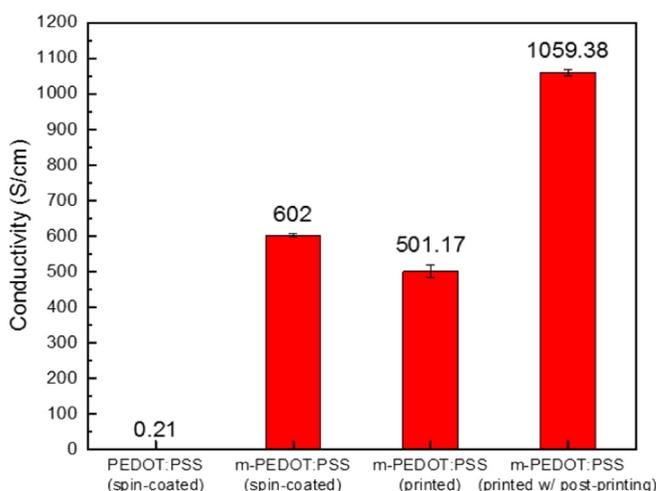


Fig. 2. Comparison of conductivities of various PEDOT:PSS films formed by different processes.

conductivity of the printed electrode was precisely measured with a four point probe resistivity meter (Loresta-AX, Mitsubishi Chemical). The mechanism of increase in conductivity was investigated by AFM (VEECO Dimension 3100 + Nanoscope V) and high-resolution XPS (HR-XPS, AXOS Nova, Kratos Analytical, Ltd) using a monochromatic Al-K α source (1486.6 eV photon energy). The printed m-PEDOT:PSS conducting electrode was used to fabricate an OLED with a structure of m-PEDOT:PSS/TPD/Alq₃/LiF/Al. On a patterned PEDOT:PSS film with a thickness of ~100 nm by inkjet printing, TPD (40 nm), Alq₃ (40 nm), LiF (1 nm) and Al (100 nm) were deposited using thermal evaporation system. The current density verse voltage (J - V) and luminance verse voltage (L - V) characteristics were measured by Keithley 236 and CS-1000 (Konica Minolta Co.) system.

3. Results and discussion

In order to find the optimized printing conditions for uniform and smooth films, the m-PEDOT:PSS ink was printed with varying drop spacing from 40 μ m to 180 μ m. As seen in Fig. 1, the change in drop spacing had an effect on film morphology. At small drop spacing (40 and 60 μ m) a non-uniform film was formed, and at large drop spacing resulted in a wavy film. From this result, the drop spacing of 100 μ m

was chosen to achieve high uniformity and smoothness of printed conducting films.

Fig. 2 shows the conductivity values of PEDOT:PSS films made by different methods and solutions. The pristine PEDOT:PSS film by spin-coating showed poor conductivity less than 1 S cm⁻¹. Conductivity has greatly increased up to ~600 S cm⁻¹ by adding DMSO and Zonyl surfactant into the aqueous solution. We obtained comparable high-conductivity from m-PEDOT:PSS films formed by inkjet-printing as described in the previous section. A post-treatment was carried out on the printed film by inkjet-printing as-received DMSO with the same nozzle. This additional printing process led to a significant increase in conductivity over 1000 S cm⁻¹. It is noteworthy that this high value was achieved simply by inkjet printing process performed in air. This value is comparable to the conductivity obtained from other post-treatments such as dipping or dropping which may not be applicable to roll-to-roll manufacturing.

It was found that the thickness of the printed film was slightly reduced after the post-printing process, and this gives an idea that the enhancement of conductivity by additional printing of highly dipolar DMSO might result from removal of non-conducting PSS molecules from the film surface. In order to investigate the effect of the post-printing on PSS molecules, the amount of PSS removed from the printed PEDOT:PSS film was evaluated with HR-XPS. As seen from Fig. 3, the S(2p) peaks observed at the binding energy of 168.7 eV corresponding to the sulfur signal from PSS and 164.2 and 165.3 eV corresponding to the sulfur signal from PEDOT. The calculated surface ratio of PSS to PEDOT for the film with and without post-printing process is 0.33:1 and 0.58:1, respectively, showing that the PSS content was significantly reduced by 43% resulting from the printing of DMSO. We believe that the removal of hydrophilic insulating PSS leads to the thickness reduction of the film and brings about reorientation of the hydrophobic conducting PEDOT polymer chains from a coiled to extended-coil structure, allowing closer inter-chain interaction between the conducting polymers [13].

We also investigated the correlation between conductivity and surface morphology of PEDOT:PSS films with and without DMSO treatment by AFM. As shown in Fig. 4, distinct structural change, weakly separated PEDOT-rich grains (bright) and PSS-rich grains (dark) were observed from a pristine PEDOT:PSS film, while well-separated grains with better connection of PEDOT-rich grains were found from a post-processed m-PEDOT:PSS film. We believe that inter-chain interactions between conducting PEDOT polymers with linear or extended-coil structure make charge hopping easier and thus lead to a significant increase in conductivity.

In order to prove this printing process, we have applied our printed high conductivity films to fabricate OLEDs. Fig. 5(a) shows the

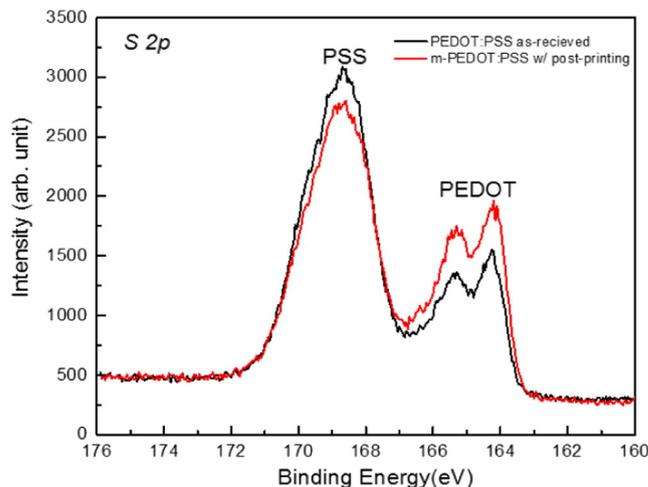


Fig. 3. XPS of pristine PEDOT:PSS and m-PEDOT:PSS with post-processing.

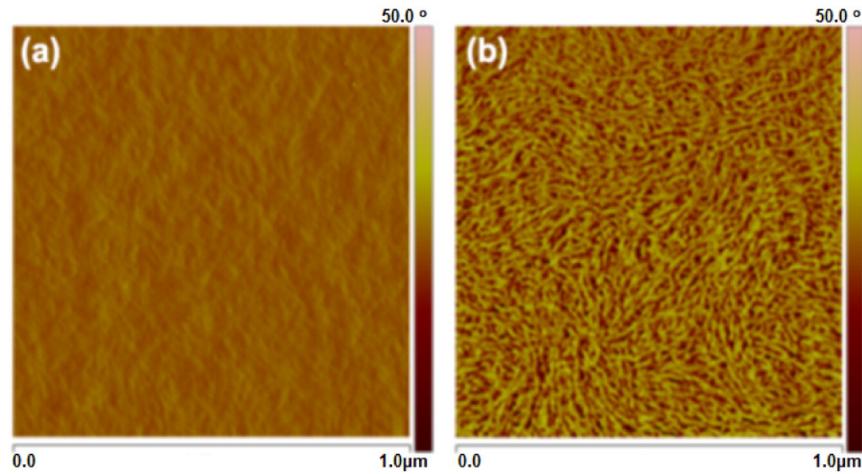


Fig. 4. AFM phase images of (a) pristine PEDOT:PSS (spin-coated) (b) m-PEDOT:PSS with post-processing (inkjet-printed).

characteristics of current density and luminance versus operating voltage of an OLED device with the structure printed m-PEDOT:PSS/TPD/Alq₃/LiF/Al. The device turned on at the voltage of 2.6 V (defined at 1 cd m⁻²) and its luminance reached 1863 cd m⁻² at 8.5 V. The emission image of a device is shown in Fig. 5(b).

4. Conclusion

In this study, we demonstrated an inkjet-printing process to pattern a high-conductivity polymer film. A secondary dopant, DMSO-containing PEDOT:PSS ink was first inkjet-printed to form a uniform conducting layer, and as-received DMSO was over-printed onto it to further enhance its conductivity greater than 1000 S cm⁻¹. This is among the highest values ever attained by printing technologies for this particular conducting polymer material. We believe that our proposal of post-printing treatment is ideally suited to roll-to-roll printing manufacturing process for low cost, large area organic electronic circuits and devices.

Acknowledgments

This work was supported by the Ministry of Science, ICT and Planning of South Korea under the “IT Consilience Creative Program”

(IITP-2015-R0346-15-1007) supervised by IITP (Institute for Information & Communications Technology Promotion) and by a grant (Code No. 2014M3A6A5060952) from the Center for Advanced Soft Electronics under the Global Frontier Research Program of the Ministry of Science, ICT and Planning of South Korea.

References

- [1] M. Ren, H. Gorter, J. Michels, R. Andriessen, Ink jet technology for large area organic light-emitting diode and organic photovoltaic applications, *J. Imaging Sci. Technol.* 55 (2011) 040301, <http://dx.doi.org/10.2352/J.ImagingSci.Technol.2011.55.4.040301>.
- [2] J. Ha, J. Park, J. Ha, D. Kim, S. Chung, C. Lee, Y. Hong, Selectively modulated inkjet printing of highly conductive and transparent foldable polymer electrodes for flexible polymer light-emitting diode applications, *Org. Electron.* 19 (2015) 147–156, <http://dx.doi.org/10.1016/j.orgel.2015.01.017>.
- [3] S. Jung, A. Sou, K. Banger, D.-H. Ko, P.C.Y. Chow, C.R. McNeill, H. Sirringhaus, All-inkjet-printed, all-air-processed organic solar cells, *Adv. Energy Mater.* 4 (2014) 1400432, <http://dx.doi.org/10.1002/aenm.201400432>.
- [4] C.N. Hoth, P. Schilinsky, S.A. Choulis, C.J. Brabec, Printing highly efficient organic solar cells, *Nano Lett.* 8 (2008) 2806–2813, <http://dx.doi.org/10.1021/nl801365k>.
- [5] A. Sou, S. Jung, E. Gili, V. Pecunia, J. Joimel, G. Fichet, H. Sirringhaus, Programmable logic circuits for functional integrated smart plastic systems, *Org. Electron.* 15 (2014) 3111–3119, <http://dx.doi.org/10.1016/j.orgel.2014.08.032>.
- [6] K.-J. Baeg, D. Khim, D.-Y. Kim, S.-W. Jung, J.B. Koo, I.-K. You, H. Yan, A. Facchetti, T.-Y. Noh, High speeds complementary integrated circuits fabricated with all-printed polymeric semiconductors, *J. Polym. Sci. B Polym. Phys.* 49 (2011) 62–67, <http://dx.doi.org/10.1002/polb.22148>.

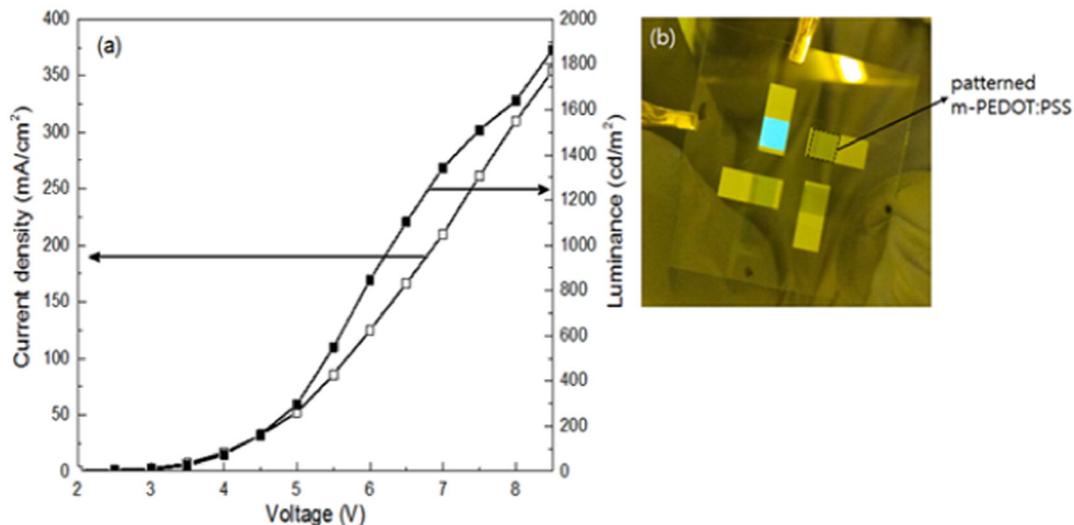


Fig. 5. (a) *J*–*V*–*L* performance of an inkjet-printed OLED device, (b) an image of the device. m-PEDOT:PSS anodes patterned by inkjet-printing are clearly seen from the image.

- [7] L. Basiricò, P. Cosseddu, B. Fraboni, A. Bonfiglio, Inkjet printing of transparent, flexible, organic transistors, *Thin Solid Films* 520 (2011) 1291–1294, <http://dx.doi.org/10.1016/j.tsf.2011.04.188>.
- [8] Y. Jang, J. Jo, Y. Choi, K. Woo, S. Kwon, K. Kim, Oxidation effects of poly(3,4-ethylenedioxythiophene)/poly(styrene sulfonate) electrodes on high-performance organic thin-film transistors, *Appl. Phys. Express* 8 (2015) 061601, <http://dx.doi.org/10.7567/APEX.8.061601>.
- [9] Y. Kim, S. Cook, S.M. Tuladhar, S.A. Choulis, J. Nelson, J.R. Durrant, D.D.C. Bradley, M. Giles, I. McCulloch, C.-S. Ha, M. Ree, A strong regioregularity effect in self-organizing conjugated polymer films and high-efficiency polythiophene: fullerene solar cells, *Nat. Mater.* 5 (2006) 197–203, <http://dx.doi.org/10.1038/nmat1574>.
- [10] S. Zhang, P. Kumar, A.S. Nouas, L. Fontaine, H. Tang, F. Cicoira, Solvent-induced changes in PEDOT:PSS films for organic electrochemical transistors, *Appl. Phys. Lett. Mater.* 3 (2015) 014911, <http://dx.doi.org/10.1063/1.4905154>.
- [11] Q. Wei, M. Mukaida, Y. Naitoh, T. Ishida, Morphological change and mobility enhancement in PEDOT:PSS by adding co-solvents, *Adv. Mater.* 25 (2013) 2831–2836, <http://dx.doi.org/10.1002/adma.201205158>.
- [12] T. Chou, S. Chen, Y. Chiang, Y. Lin, C. Chao, Highly conductive PEDOT:PSS films by post-treatment with dimethyl sulfoxide for ITO-free liquid crystal display, *J. Mater. Chem. C* 3 (2015) 3760–3766, <http://dx.doi.org/10.1039/C5TC00276A>.
- [13] D. Alemu, H.-Y. Wei, K.-C. Ho, C.-W. Chu, Highly conductive PEDOT:PSS electrode by simple film treatment with methanol for ITO-free polymer solar cells, *Energy Environ. Sci.* 5 (2012) 9662–9671, <http://dx.doi.org/10.1039/c2ee22595f>.
- [14] Y.H. Kim, C. Sachse, M.L. Machala, C. May, L. Müller-Meskamp, K. Leo, Highly conductive PEDOT:PSS electrode with optimized solvent and thermal post-treatment for ITO-free organic solar cells, *Adv. Funct. Mater.* 21 (2011) 1076–1081, <http://dx.doi.org/10.1002/adfm.201002290>.
- [15] S. Jung, A. Sou, E. Gili, H. Sirringhaus, Inkjet-printed resistors with a wide resistance range for printed read-only memory applications, *Org. Electron.* 14 (2013) 699–702, <http://dx.doi.org/10.1016/j.orgel.2012.12.034>.