



# Influence of non-magnetic and magnetic ions on the MagnetoCaloric properties of $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{M}_{0.1}\text{O}_3$ doped in the Mn sites by $\text{M}=\text{Cr}, \text{Sn}, \text{Ti}$



Brahim Arayedh<sup>a,\*</sup>, Sami Kallel<sup>a</sup>, Nabil Kallel<sup>a</sup>, Octavio Peña<sup>b</sup>

<sup>a</sup> Laboratoire Physico-chimie des Matériaux, Département de Physique, Faculté des Sciences de Monastir, Université de Monastir, 5019 Monastir, Tunisia

<sup>b</sup> Institut des Sciences Chimiques de Rennes, UMR 6226-CNRS, Université de Rennes 1, 35042 Rennes Cedex, France

## ARTICLE INFO

### Article history:

Received 9 November 2013

Received in revised form

18 February 2014

Available online 3 March 2014

### Keywords:

Perovskite manganite

Magnetic entropy

Magnetic refrigeration

## ABSTRACT

We have studied the MagnetoCaloric Effect (MCE) in  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{M}_{0.1}\text{O}_3$ ,  $\text{M}=\text{Cr}, \text{Sn}$  and  $\text{Ti}$ , prepared by a conventional solid state reaction. The temperature dependence of magnetization reveals that all compositions exhibit a ferromagnetic (FM) to paramagnetic (PM) transition at  $T_C$  temperatures of 369, 326, 228 and 210 K, respectively for  $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$  (LSMO),  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Cr}_{0.1}\text{O}_3$  (LSMO-Cr),  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Sn}_{0.1}\text{O}_3$  (LSMO-Sn), and  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Ti}_{0.1}\text{O}_3$  (LSMO-Ti). Using Arrott plots, the phase transition from FM to PM is found to be of second order. The maximum magnetic entropy change ( $-\Delta S_M$ ), at the applied magnetic field of 2 T, is found to be 1.27, 1.76, 0.47 and 1.45  $\text{J kg}^{-1} \text{K}^{-1}$ , respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. The relative cooling power (RCP) for LSMO-Cr, LSMO-Sn and LSMO-Ti is in the order of 50%, 26% and 71%, respectively, compared to gadolinium (Gd). As a result, the LSMO-Cr and LSMO-Ti compounds can be considered as promising materials in magnetic refrigeration technology.

© 2014 Elsevier B.V. All rights reserved.

## 1. Introduction

In recent years, magnetic refrigeration has received considerable attention because it is considered to be more energy-efficient and environmentally friendlier compared to the conventional refrigeration based on the compression–expansion of greenhouse gases, CFC (ChloroFluoroCarbons) and HCFC (Hydro-ChloroFluoroCarbons) [1,2]. The renewed interest in MagnetoCaloric materials is partly due to the discovery of a giant magnetic entropy change in  $\text{Gd}_5\text{Si}_2\text{Ge}_2$  and Gd alloys in the late 1990s and early 2000s [3–5]. The magnetic refrigeration is based on the MagnetoCaloric Effect (MCE) [6], which depends on the fact that the spin entropy of a magnetic material decreases upon application of an external magnetic field and this reduction in magnetic entropy is compensated by an increase in the lattice entropy resulting in an increase in the temperature of the sample. Conversely, when the magnetic field is removed adiabatically, magnetic spins tend to randomize which leads to an increase in the magnetic entropy and a decrease in the lattice entropy and hence lowering the temperature of the sample.

In this context, gadolinium (Gd) is the reference material for magnetic refrigeration at room temperature. This is the first material that has validated the principle of magnetic refrigeration

at room temperature, and it is still used to test prototypes with a Curie temperature ( $T_C=293 \text{ K}$ ) close to room temperature [7]. However, because of its very expensive price and limited resources, the studies on manganite-based materials have been accelerated these last years. Among these materials, perovskites of general formula  $\text{R}_{1-x}\text{A}_x\text{MnO}_3$  ( $\text{R}$  – rare-earth,  $\text{A}$  – alkali earth) have been studied in detail due to their interesting magnetic properties [8,9]. Among them,  $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$  compounds are given particular attention because of their interesting magnetic properties such as Colossal MagnetoResistance (CMR) and MCE [10,11]. In addition, the presence of  $\text{Mn}^{3+}$  and  $\text{Mn}^{4+}$  cations (promoted by the inclusion of divalent cations such as  $\text{Sr}^{2+}$ ) induces mobile holes in the  $e_g$  band near the Fermi energy, which affect the electronic conduction and the SuperExchange (SE) interaction. The SE interaction causes antiferromagnetic (AFM) coupling between magnetic moments in manganites and thus, moderate-to-low values for the magnetic moment per unit formula. This AFM ordering can be progressively suppressed by the increment of the number of  $\text{Mn}^{3+}-\text{Mn}^{4+}$  pairs, which favors the Double Exchange (DE) interaction and hence, the enhancement of the magnetic moment and Curie temperature ( $T_C$ ). On the other hand, doping at the Mn-site is of great importance in modifying the DE strength between  $\text{Mn}^{3+}$  and  $\text{Mn}^{4+}$  via oxygen. This alters the magnetic and MagnetoCaloric behavior in doped manganites.

$\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$  (LSMO) is one of the extensively studied manganites which undergoes a paramagnetic (PM) to a ferromagnetic

\* Corresponding author. Tel.: +216 52 999 615; fax: +216 73 332 658.

E-mail address: [larayedh\\_brahim@yahoo.fr](mailto:larayedh_brahim@yahoo.fr) (B. Arayedh).

(FM) transition above room temperature. The ferromagnetic transition of this compound can be brought down to room temperature either by partial replacement of  $\text{La}^{3+}$ , of big ionic size, by  $\text{Pr}^{3+}$  or  $\text{Nd}^{3+}$ , of smaller size, or by partial substitution of Mn ions by other transition metals such as  $\text{M}=\text{Cr}$ ,  $\text{Ni}$ ,  $\text{Cu}$ ,  $\text{Fe}$ ,  $\text{Zn}$ ,  $\text{Co}$ ,  $\text{Al}$ , etc. [12–22]. The influence of substitution of magnetic and non-magnetic elements at Mn-site on the MCE has been reported in the literature [23–25].

In this work, we present the MCE of  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{M}_{0.1}\text{O}_3$  manganites substituted at the Mn site by  $\text{M}=\text{Cr}$ ,  $\text{Sn}$  and  $\text{Ti}$ . The Cr substitution deserves particular attention due to the magnetic nature of the Cr ion compared to non-magnetic Sn and Ti ions. It is noticed that both  $\text{Sn}^{4+}$  ( $[\text{Ar}]4d^{10}5s^05p^0$ ) and  $\text{Ti}^{4+}$  ( $[\text{Ar}]3d^04s^0$ ) are bigger than  $\text{Mn}^{4+}$  ( $r_{\text{Mn}^{4+}}^{\text{IV}}=0.530^\circ$ ,  $r_{\text{Sn}^{4+}}^{\text{IV}}=0.690^\circ$  and  $r_{\text{Ti}^{4+}}^{\text{IV}}=0.605^\circ$ ), whereas  $\text{Cr}^{3+}$  ( $3d^34s^0=t_{2g}^3e_g^0$ ) is smaller than  $\text{Mn}^{3+}$  ( $r_{\text{Mn}^{3+}}^{\text{III}}=0.650^\circ$  and  $r_{\text{Cr}^{3+}}^{\text{III}}=0.615^\circ$ ).

## 2. Experimental

$\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{M}_{0.1}\text{O}_3$  ( $\text{M}=\text{Cr}$ ,  $\text{Sn}$  and  $\text{Ti}$ ) polycrystalline compounds were prepared by a conventional solid-state reaction method in air. Magnetization ( $M$ ) versus temperature ( $T$ ) and magnetization versus magnetic field ( $\mu_0H$ ) were measured using a Quantum Design MPMS-XL5 SQUID magnetometer. Isothermal  $M(\mu_0H)$  data were measured at different temperatures under an applied magnetic field varying from 0 to 5 T.

## 3. Results and discussion

### 3.1. Structural characteristics

Identification of the phase and structural analysis by X-ray diffraction technique are reported elsewhere [26–28]. These results show that the compounds  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{M}_{0.1}\text{O}_3$  ( $\text{M}=\text{Cr}$ ,  $\text{Sn}$ ,  $\text{Ti}$ ) crystallize in the rhombohedral system with the  $R\bar{3}C$  space group. Lattice parameters and unit cell volumes are listed in Table 1.

### 3.2. Magnetic properties

The temperature dependence of magnetization  $M(T)$  for  $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$  (LSMO),  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Cr}_{0.1}\text{O}_3$  (LSMO-Cr),  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Sn}_{0.1}\text{O}_3$  (LSMO-Sn) and  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Ti}_{0.1}\text{O}_3$  (LSMO-Ti) samples, measured under an applied magnetic field of 0.05 T, is shown in Fig. 1. All compositions exhibit a FM to PM transition at  $T_C$  temperatures of 369, 326, 228, and 210 K, respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. Curie temperature  $T_C$  is defined as the temperature corresponding to a minimum of the derivative  $dM(T)/dT$  of the  $M(T)$  curve. The  $T_C$  value decreases with Cr, Sn and Ti substitution. For LSMO-Cr, the decrease in  $T_C$  value can be explained by the fact that  $\text{Cr}^{3+}$  cations have the same electronic structure as that of  $\text{Mn}^{4+}$ , i.e.  $[\text{Ar}]3d^3$  with 3 electrons at the lower  $t_{2g}$  level and 0 electrons at the higher  $e_g$  level. So, the substitution of Mn by Cr implies a number of

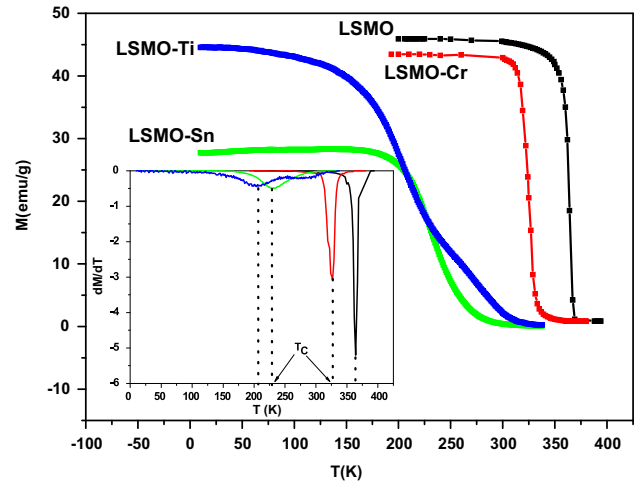


Fig. 1. The temperature dependence of the field-cooled magnetization  $M(T)$  under an applied magnetic field of  $\mu_0H=0.05$  T for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. The inset indicates the  $dM/dT$  curve used to determine  $T_C$ .

cations with the  $[\text{Ar}]3d^3(\text{Mn}^{4+})$  configuration which is equivalent to a reduction in the number of  $\text{Mn}^{3+}$  cations, and hence, a reduced number of  $\text{Mn}^{4+}-\text{Mn}^{3+}$  pairs (the  $\text{Mn}^{3+}/\text{Mn}^{4+}$  ratio decreases from 0.70/0.30 to 0.60/0.30 during the substitution). The reduction of these atoms pairs favors the SE interactions between  $\text{Cr}^{3+}-\text{O}-\text{Mn}^{4+}$ ,  $\text{Cr}^{3+}-\text{O}-\text{Cr}^{3+}$  and  $\text{Mn}^{4+}-\text{O}-\text{Mn}^{4+}$  cations, and thus, deteriorating the magnetic properties of the parent compound LSMO. The SE interaction being favored between ions with empty  $e_g$  orbitals in manganites was described in detail by Goodenough and Loeb [29]. The  $T_C$  value of the LSMO-Cr compound is close to room temperature. This value is similar to that found by Sun et al. [30] for the  $\text{La}_{0.67}\text{Sr}_{0.33}\text{Mn}_{0.9}\text{Cr}_{0.1}\text{O}_3$  compound.

From the remarkable variation of  $T_C$  (369 K for LSMO to 228 and 210 K for LSMO-Sn and LSMO-Ti), we conclude that the substitution of Mn by  $\text{Ti}^{4+}$  and  $\text{Sn}^{4+}$  causes a significant decrease in the FM ordering temperature of the undoped system.  $\text{Ti}^{4+}$  and  $\text{Sn}^{4+}$  are non-magnetic ions and do not possess any unpaired electrons; then, the substitution of Mn by Ti and Sn produces a sudden break in the FM  $\text{Mn}^{3+}-\text{O}-\text{Mn}^{4+}$  interactions. The important role of the magnetic nature of dopants in the manganites properties was demonstrated by Song et al. [31].

Fig. 2 shows an example of the magnetization versus the applied magnetic field measured at different temperatures, from 0 to 5 T, for the LSMO-Cr sample. Below  $T_C$ , the magnetization  $M$  increases sharply with the applied magnetic field up to 1 T and then saturates. Above  $T_C$ , the magnetization  $M$  increases more smoothly, as typical in paramagnetic materials. This decrease is mainly due to the thermal agitation which tends to disorder the magnetic moments. This variation indicates that there is a large magnetic entropy change associated with the FM–PM transition temperature occurring at  $T_C$ .

Near the Curie temperature, a ferromagnet undergoes a second-order phase transition in the presence of an external field ( $\mu_0H$ ). Thus, the magnetic energy  $M\mu_0H$  can be included in the expression of Gibbs's free energy, which can be written as a Landau power expansion of the magnetization  $M$ , neglecting higher-order parts [32–34]

$$G(M, T) = G_0 + \frac{1}{2}A(T)M^2 + \frac{1}{4}B(T)M^4 - M\mu_0H \quad (1)$$

where  $A$  and  $B$ , known as Landau coefficients, depend on the temperature  $T$ . The last term in Eq. (1) describes the energy of spins, which is expected to be slowly varying with temperature.

Table 1

Structural parameters and cell volume for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti.

	LSMO	LSMO-Cr	LSMO-Sn	LSMO-Ti
Space group	$R\bar{3}C$	$R\bar{3}C$	$R\bar{3}C$	$R\bar{3}C$
$a=b$ (Å)	5.5023	5.5018	5.5437	5.5255
$c$ (Å)	13.3569	13.3430	13.4259	13.3899
Volume ( $\text{\AA}^3$ )	350.210	349.80	357.340	354.040
$d_{(\text{Mn}, \text{M})-\text{O}}$ (Å)	1.955	1.952	1.970	1.961
(Mn, M)–O–(Mn, M) ( $^\circ$ )	165.60	166.470	164.960	166.360
$W$ (a.u.)	0.0958	0.0955	0.0923	0.0940

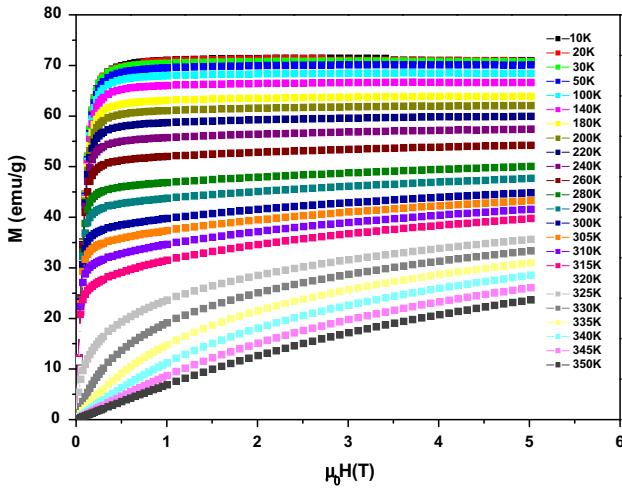


Fig. 2. Magnetization versus magnetic field  $M(H)$  at several temperatures for LSMO-Cr.

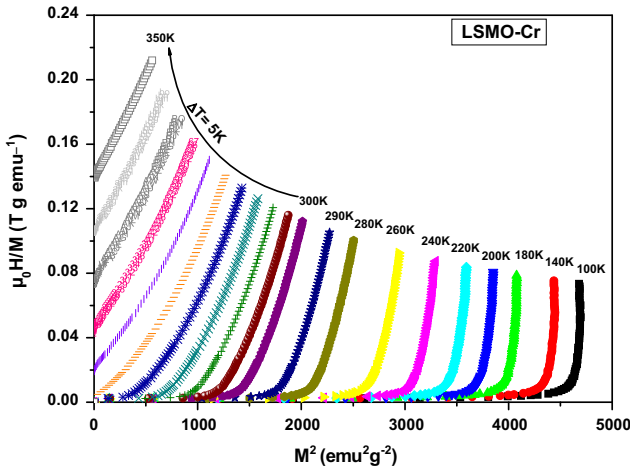


Fig. 3. Arrott plot isotherms of  $\mu_0 H/M$  versus  $M^2$  at different temperatures for LSMO-Cr.

From the condition of equilibrium at  $T_c$ ,  $(\partial G(M, T)/\partial M) = 0$ , we obtain

$$\frac{\mu_0 H}{M} = A(T) + B(T)M^2 \quad (2)$$

In order to get a deeper insight of the nature of magnetic phase transition, Arrott plots ( $\mu_0 H/M$  versus  $M^2$ ) are shown in Fig. 3 for the LSMO-Cr compound. According to Banerjee's criterion [35], a negative or positive sign of the slope of Arrott curves corresponds to a first-order or second-order magnetic phase transition, respectively. The results obtained from  $\mu_0 H/M$  versus  $M^2$  plots of all compounds studied in this work, LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti, show that a positive slope in all cases in the complete  $M^2$  range, confirming that a second-order FM to PM phase transition has occurred.

Thus, the temperature dependence of parameter  $A$ , Eq. (2), can be extracted from the linear region of Arrott plots (Fig. 3), as shown in Fig. 4. It is found that parameter  $A$  varies from negative to positive with increasing temperature. It is noticed that the temperature corresponding to the intercept (zero-value of parameter  $A$ ) correlates well with the value of the transition temperature  $T_c$ .

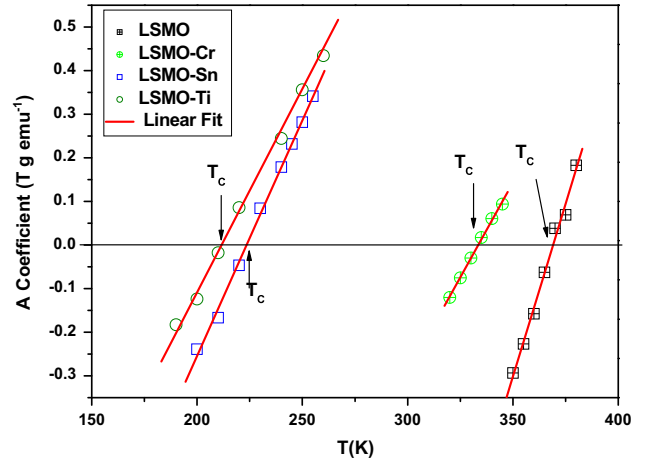


Fig. 4. Temperature dependence of coefficient  $A$  for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti deduced from the Arrott plots, using Eq. (2).

### 3.3. MagnetoCaloric Effect (MCE)

MCE is an intrinsic property of magnetic materials. It is the response of the material toward the application or removal of a magnetic field. This response is maximized when the material is near its magnetic ordering temperature (Curie temperature  $T_c$ ).

According to the thermodynamic Maxwell's relationship  $(\partial S/\partial H)_T = (\partial M/\partial T)_H$ , the magnetic entropy change  $\Delta S_M$  which results from spin ordering and which is induced by the variation  $\mu_0 \Delta H$  of the applied field from 0 to  $\mu_0 H$  is given by [36,37]

$$\Delta S_M(T, \mu_0 H) = S(T, \mu_0 H) - S(T, 0) = \int_0^{\mu_0 H} \left( \frac{\partial M}{\partial T} \right)_H \mu_0 dH \quad (3)$$


where  $\mu_0 H$  is the external magnetic field.

In order to evaluate the magnetic entropy change ( $\Delta S_M$ ), one needs to make a numerical approximation for the integral in Eq. (3). The method consists of using the magnetization curves at various temperatures. Then, for given intervals of temperature ( $\Delta T = T_2 - T_1$ ), the magnetization measurements at small discrete fields lead to a magnetic entropy change  $\Delta S_M$  approximated by

$$\Delta S_M \left( \frac{T_1 + T_2}{2} \right) = \frac{1}{T_2 - T_1} \left[ \int_0^{\mu_0 H} M(T_2, \mu_0 H) \mu_0 dH - \int_0^{\mu_0 H} M(T_1, \mu_0 H) \mu_0 dH \right] \quad (4)$$

Fig. 5 shows the temperature dependence of the magnetic entropy change ( $-\Delta S_M$ ) at various intervals of the applied field from  $\mu_0 \Delta H$  of 1 T to 5 T, for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. It is clear that the magnetic entropy change depends on the magnetic field interval; also the largest changes in magnetic entropy take place near  $T_c$ , which is a property of simple ferromagnets due to the efficient ordering of magnetic moments induced by the magnetic field at the ordering temperature. For each composition, the peak position is nearly unaffected because of the second-order nature of the FM-PM transition for these compounds. These peaks are situated at about 364 K, 325 K, 229 K and 212 K, respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. Under a variation in the applied magnetic field  $\mu_0 \Delta H$  of 2 T, the  $|\Delta S_M^{\max}|$  values are on the order of 1.27, 1.76, 0.47 and 1.45 J kg<sup>-1</sup> K<sup>-1</sup>, respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti.

In Table 1 we have compared the MCE of Cr, Sn and Ti with other B-site multi-element doping effect like Al, Co, Ni and Fe in La<sub>0.7</sub>Sr<sub>0.3</sub>Mn<sub>1-x</sub>M<sub>x</sub>O<sub>3</sub> system. Phan et al. [15] studied MCE in La<sub>0.7</sub>Sr<sub>0.3</sub>Mn<sub>0.98</sub>Ni<sub>0.02</sub>O<sub>3</sub> and found a maximum entropy change of

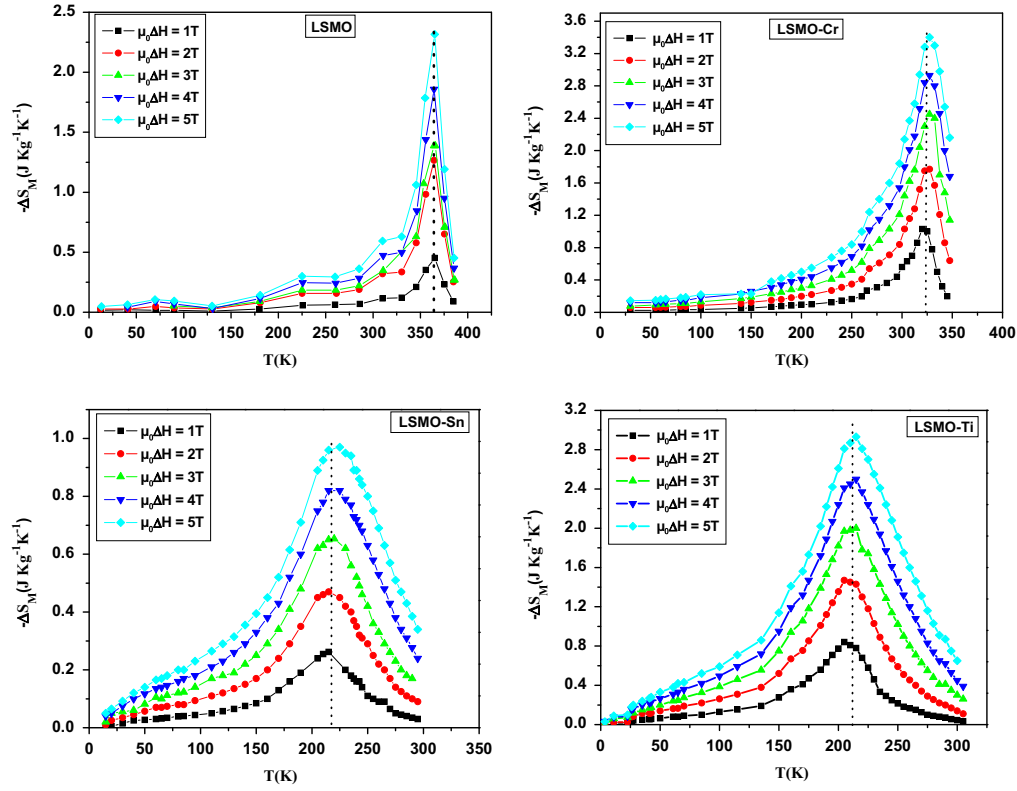

**Fig. 5.** Magnetic entropy change ( $-\Delta S_M$ ) as a function of temperature for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti under given variations of the applied magnetic field ( $\mu_0\Delta H$ ).

$2.25 \text{ J kg}^{-1} \text{ K}^{-1}$  under  $\mu_0\Delta H=1 \text{ T}$ . A large MCE ( $\Delta S_M=5.51 \text{ J kg}^{-1} \text{ K}^{-1}$  under  $\mu_0\Delta H=1.5 \text{ T}$ ) was found in  $\text{La}_{0.7}\text{Sr}_{0.3}\text{Mn}_{0.9}\text{Cu}_{0.1}\text{O}_3$  [17]. In the series  $\text{La}_{0.845}\text{Sr}_{0.155}\text{Mn}_{1-x}\text{M}_x\text{O}_3$  ( $M=\text{Mn}, \text{Cu}, \text{and Co}$ ) the largest MCE ( $\Delta S_M=2.67 \text{ J kg}^{-1} \text{ K}^{-1}$  under  $\mu_0\Delta H=1.35 \text{ T}$ ) was also found for  $x=0.1$  of Cu [20]. All these studies indicate that the large MCE in the perovskite manganites can originate from the spin–lattice coupling related to the magnetic ordering process [38,39]. This strong coupling is evidenced by the lattice changes accompanying the magnetic transitions in these manganites; the lattice structural change in (Mn, M)–O bond distances and (Mn, M)–O–(Mn, M) bond angles with temperature, which results in a variation of the volume, can cause an additional change in the magnetic properties of the material [40].

The influence of structural change on the magnetism and MCE in these systems is related to the electronic bandwidth  $W$  [41] (see Table 1). The decrease in the values of  $W$  with different elements doping reduces the double-exchange (DE) interaction. The empirical formula of bandwidth  $W$  for  $\text{ABO}_3$ -type perovskites using the tight binding approximation [42] is  $W \propto \cos \theta / d_{\text{Mn-O}}^{3.5}$ , where  $\theta = (1/2)(\pi - (\text{Mn-O-Mn}))$  and  $d_{\text{Mn-O}}$  is the Mn–O length. The decrease in bandwidth  $W$  reduces the overlap between the O 2p and the Mn 3d orbital, which in turn decreases the exchange coupling of  $\text{Mn}^{3+}$ – $\text{Mn}^{4+}$  resulting in a decrease in the magnetic ordering [43,44].

On the other hand, the oxygen deficiency could play an important role in the physical properties of this kind of materials, especially the structural transition that may appear in the magnetic, MCE and electrical properties [45,46].

The change of specific heat ( $\Delta C_P$ ) associated with a magnetic field variation from 0 to  $\mu_0 H$  is given by [47,48]

$$\Delta C_P(T, \mu_0 H) = C_P(T, \mu_0 H) - C_P(T, 0) = T \frac{\partial \Delta S_M(T, \mu_0 H)}{\partial T} \quad (5)$$

Using Eq. (5),  $\Delta C_P$  of all samples versus temperature under different variations of the applied magnetic field ( $\mu_0\Delta H$ ) is


displayed in Fig. 6. Here, we can see that  $\Delta C_P$  undergoes a sudden change of sign around  $T_C$  with a positive value above  $T_C$  and a negative value below  $T_C$ . In addition, the maximum/minimum values of  $\Delta C_P$  exhibit an increasing trend with the applied field and are observed at temperatures 385/350, 337/317, 242/169 and 230/190 K, respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. The values of  $\Delta C_P^{\text{max}}/\Delta C_P^{\text{min}}$  under the applied magnetic field of 2 T are listed in Table 2.

Generally, an important criterion for selecting magnetic refrigerants is the cooling power per unit volume, namely, the relative cooling power RCP [1,49,50], which corresponds to the amount of heat transferred between the cold and the hot sinks in the ideal refrigeration cycle. RCP has been defined as

$$\text{RCP} = |\Delta S_M^{\text{max}}| \times \delta T_{\text{FWHM}} \quad (6)$$

where  $|\Delta S_M^{\text{max}}|$  is the maximum entropy change at  $T_C$  and is equal to  $\delta T_{\text{FWHM}} = (T_2 - T_1)$ , the full-width temperature span of the ( $-\Delta S_M$ ) versus temperature plots at their half-maxima.

The magnetic field dependence of the RCP is shown in Fig. 7. RCP values increase linearly with the applied magnetic field ( $\mu_0 H$ ). RCP values under an applied field of 2 T are about 29, 74, 40 and  $113 \text{ J kg}^{-1}$ , respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti samples. To evaluate the applicability of LSMO-Cr, LSMO-Sn and LSMO-Ti compounds as magnetic refrigerants, the values of  $|\Delta S_M^{\text{max}}|$  and RCP obtained in our study were compared with those reported in the literature for several other magnetic materials (Table 2). For LSMO-Cr, LSMO-Sn and LSMO-Ti our values are in the order of 50%, 26% and 71% compared with gadolinium (Gd), while they are quite comparable to those reported for other manganites (Table 2). Hence, LSMO-Cr and LSMO-Ti compounds, in particular, are suitable candidates to be used in magnetic refrigeration; among these two, the value of RCP for LSMO-Ti is higher than the one for LSMO-Cr, the Curie temperature for the

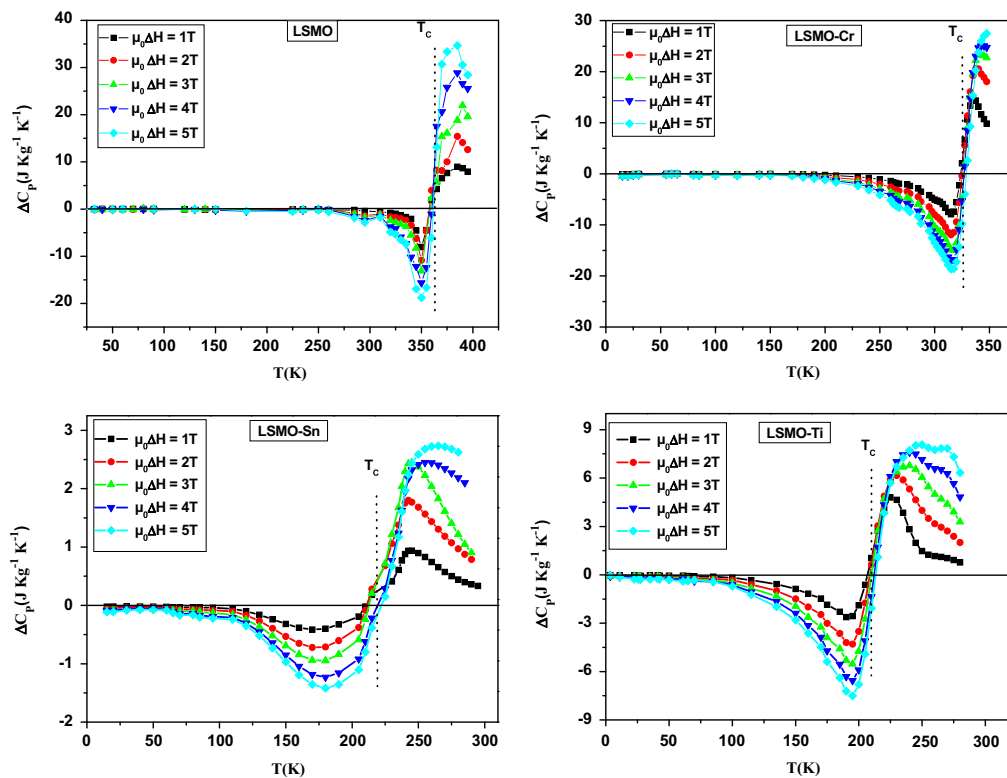

**Fig. 6.** Temperature dependence of the specific heat ( $\Delta C_p$ ) as evaluated from Eq. (5), under given variations of the applied magnetic field ( $\mu_0 \Delta H$ ) for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti.

**Table 2**

Summary of MagnetoCaloric properties of LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti, compared to other magnetic materials.

Sample	$T_C$ (K)	$ \Delta S_M^{\max} $ (J kg <sup>-1</sup> K <sup>-1</sup> )	$\Delta C_p^{\max}/\Delta C_p^{\min}$ (J kg <sup>-1</sup> K <sup>-1</sup> )	RCP (J kg <sup>-1</sup> )	$\mu_0 \Delta H$ (T)	Ref.
La <sub>0.7</sub> Sr <sub>0.3</sub> MnO <sub>3</sub> (LSMO)	369	1.27	15.4/–10.6	29	2	This work
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.9</sub> Cr <sub>0.1</sub> O <sub>3</sub> (LSMO-Cr)	326	1.76	21.5/–11.4	74	2	This work
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.9</sub> Sn <sub>0.1</sub> O <sub>3</sub> (LSMO-Sn)	228	0.47	1.82/–0.72	40	2	This work
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.9</sub> Ti <sub>0.1</sub> O <sub>3</sub> (LSMO-Ti)	210	1.45	6.2/–4.2	113	2	This work
La <sub>0.67</sub> Sr <sub>0.33</sub> MnO <sub>3</sub>	370	1.55	40.5/–18.7	42	1	[47]
La <sub>0.7</sub> Ca <sub>0.3</sub> MnO <sub>3</sub>	267	0.91	13.2/–5.2	35	1.10	[48]
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.95</sub> Ti <sub>0.05</sub> O <sub>3</sub>	308	2.2	–	90	2	[22]
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.9</sub> Al <sub>0.1</sub> O <sub>3</sub>	310	0.61	–	51	1	[22]
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.9</sub> Fe <sub>0.1</sub> O <sub>3</sub>	260	1.7	–	83	2	[21]
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.9</sub> Cu <sub>0.1</sub> O <sub>3</sub>	348	5.51	–	–	1.5	[17]
La <sub>0.67</sub> Sr <sub>0.33</sub> Mn <sub>0.9</sub> Cr <sub>0.1</sub> O <sub>3</sub>	328	5	–	–	5	[30]
La <sub>0.7</sub> Sr <sub>0.3</sub> Mn <sub>0.98</sub> Ni <sub>0.02</sub> O <sub>3</sub>	350	2.25	–	–	1	[15]
La <sub>0.845</sub> Sr <sub>0.155</sub> Mn <sub>0.98</sub> Co <sub>0.02</sub> O <sub>3</sub>	220	2.60	–	–	1.35	[20]
La <sub>0.845</sub> Sr <sub>0.155</sub> Mn <sub>0.9</sub> Cu <sub>0.1</sub> O <sub>3</sub>	267	2.67	–	–	1.35	[20]
Gd	293	5	–	153	2	[7]

later is closer to room temperature, making LSMO-Cr as the most favorable for magnetic refrigeration.

#### 3.4. Dependence of magnetic entropy change

Numerous works have been done concerning the field dependence of the magnetic entropy change ( $\Delta S_M$ ) of manganites at the FM–PM transition  $T_C$ . According to Oesterreicher et al. [51], the magnetic field dependence of the magnetic entropy change  $\Delta S_M$  at a temperature  $T$  for materials obeying a second-order phase transition follows an exponent power law of the type

$$\Delta S_M(H) = a(\mu_0 H)^n \quad (7)$$

where  $a$  is a constant and the  $n$  exponent depends on the magnetic state of the sample. In a mean field approach, the value of  $n$  at the

Curie temperature is predicted to be  $2/3$  [51]. It is well known that in manganites the exponent is roughly field-independent and approaches approximate values of 1 and 2, far below and above the transition temperature, respectively [52].

By fitting the data of  $\Delta S_M$  versus  $\mu_0 H$  to Eq. (7), we obtain the value of  $n$  as a function of temperature, as depicted on a log–log scale in Fig. 8. The  $n$  exponent is close to 1 in the FM regime and increases to 2 in the PM region. The  $n$  exponent exhibits a moderate decrease with increasing temperature, with a minimum value in the vicinity of the transition temperature, sharply increasing above  $T_C$ . The  $n$  values around  $T_C$  are 0.556, 0.654, 0.794, and 0.706, respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti. These values are similar to those obtained for soft magnetic alloys, gadolinium (Gd) and other magnetic materials containing rare earth metals [52–56].



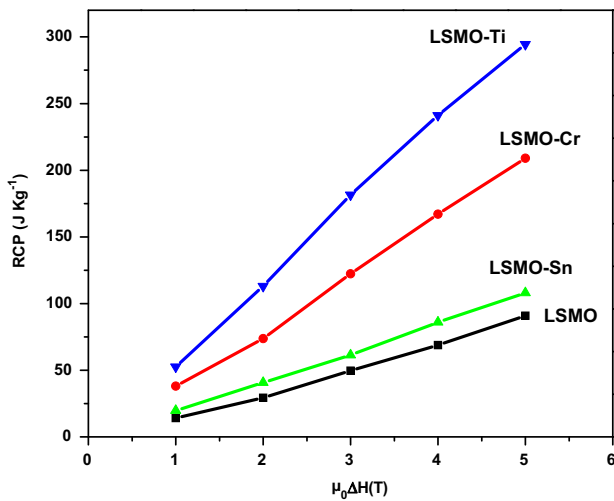


Fig. 7. Magnetic field ( $\mu_0\Delta H$ ) dependence of the relative cooling power RCP for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti.

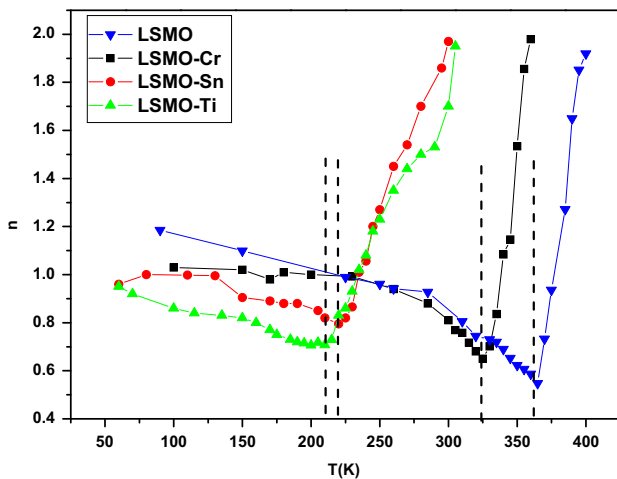


Fig. 8. Temperature dependence of the exponent  $n$  for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti samples.

#### 4. Conclusions

We have studied the MagnetoCaloric Effect (MCE) in  $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$  (LSMO) manganites partly substituted at the Mn site by 10 at% of Cr, Sn and Ti (LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti) prepared by standard solid-state reaction methods. Magnetic measurements show that all compounds exhibit a FM-PM second order transition. A large MCE is observed near  $T_C$ . The maximum of the magnetic entropy change ( $-\Delta S_M$ ) observed for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti is found to be 1.27, 1.76, 0.47 and  $1.45 \text{ J kg}^{-1} \text{ K}^{-1}$ , respectively, under a magnetic field change ( $\mu_0\Delta H$ ) of 2 T. The relative cooling power (RCP) for LSMO-Cr, LSMO-Sn and LSMO-Ti is on the order of 50%, 26% and 71%, respectively, compared to gadolinium (Gd). Our results indicate that both LSMO compounds substituted with Ti and Cr constitute potential candidates for magnetic refrigeration, with a relatively large change in entropy. The field dependence of the magnetic entropy variation shows a power law dependence ( $\Delta S_M \propto (\mu_0 H)^n$ ), with  $n=0.556$ , 0.654, 0.794 and 0.706, respectively for LSMO, LSMO-Cr, LSMO-Sn and LSMO-Ti.

#### References

- [1] K.A. Gschneidner, V.K. Pecharsky, A.O. Tsokol, Rep. Prog. Phys. 68 (2005) 1479.
- [2] M.A. Tishin, Magnetocaloric effect in the vicinity of phase transitions, in: K.H.J. Buschow (Ed.), Handbook on Magnetic Materials, 12, North-Holland, Amsterdam, 1999, pp. 395–524.
- [3] V.K. Pecharsky, K.A. Gschneidner, Phys. Rev. Lett. 78 (1997) 4494.
- [4] A.O. Pecharsky, K.A. Gschneidner, V.K. Pecharsky, J. Appl. Phys. 93 (2003) 8.
- [5] S. Yu. Dan'kov, A.M. Tishin, V.K. Pecharsky, K.A. Gschneidner, J. Phys. Rev. 57 (1998) 6.
- [6] E. Warburg, Ann. Phys. 13 (1881) 141.
- [7] E. Brück, O. Tegus, D.T.C. Thanh, K.H.J. Buschow, J. Magn. Magn. Mater. 310 (2007) 2793.
- [8] M. Pekala, V. Drozd, J. Alloys Compd. 456 (2008) 30.
- [9] Y. Sun, W. Tong, N. Liu, Y. Zhang, J. Magn. Magn. Mater. 238 (2002) 25.
- [10] Z.H. Wang, B.G. Shen, N. Tang, J.W. Cai, T.H. Ji, J.G. Zhao, W.S. Zhan, G.C. Che, S.Y. Dai, D.H.L. Ng, J. Appl. Phys. 85 (1999) 5399.
- [11] C. Autret, M. Gervais, F. Gervais, N. Raimboux, P. Simon, Solid State Sci. 6 (2004) 815.
- [12] M.A. Oumezzine, O. Peña, S. Kallel, M. Oumezzine, J. Alloys Compd. 539 (2012) 116.
- [13] N. Kallel, S. Kallel, A. Hagaza, M. Oumezzine, Physica B 404 (2009) 285.
- [14] S. Chatterjee, S. Giri, S. Majumdar, J. Appl. Phys. 107 (2010) 113909.
- [15] M.-H. Phan, N.-D. Tho, N. Chau, S.-C. Yu, M. Kurisu, J. Appl. Phys. 97 (2005) 103901.
- [16] Z.M. Wang, G. Ni, Q.Y. Xu, H. Sang, Y.W. Du, J. Appl. Phys. 90 (2001) 5689.
- [17] M.H. Phan, H.X. Peng, S.C. Yu, N.D. Tho, N. Chau, J. Magn. Magn. Mater. 285 (2005) 199.
- [18] Z. Wang, J. Huang, J. Alloys Compd. 576 (2013) 54.
- [19] T.S. Zhao, W.X. Xianyu, B.H. Li, Z.N. Qian, J. Alloys Compd. 459 (2008) 29.
- [20] M.-H. Phan, T.-L. Phan, S.-C. Yu, N.-D. Tho, N. Chau, Phys. Status Solidi B 241 (2004) 1744.
- [21] S.K. Barik, C. Krishnamoorthi, R. Mahendiran, J. Magn. Magn. Mater. 323 (2011) 1015.
- [22] D.N.H. Nam, N.V. Dai, L.V. Hong, N.X. Phuc, S.C. Yu, M. Tachibana, E.T. Muromachi, J. Appl. Phys. 103 (2008) 043905.
- [23] S.M. Yusuf, M. Sahana, K. Dörr, K.H. Müller, Appl. Phys. A 74 (2002) 622.
- [24] D. Cao, F. Bridges, M. Anderson, A.P. Ramirez, M. Olapinski, M.A. Subramanian, C.H. Booth, G.H. Kwei, Phys. Rev. B 64 (2001) 184409.
- [25] F. Damay, A. Maignan, C. Martin, B. Raveau, J. Appl. Phys. 82 (1997) 3.
- [26] N. Kallel, G. Dezanneau, J. Dhahri, M. Oumezzine, H. Vincent, J. Magn. Magn. Mater. 261 (2003) 56.
- [27] N. Kallel, J. Dhahri, S. Zemni, M. Oumezzine, M. Ghedira, H. Vincent, Phys. Status Solidi A 184 (2001) 319.
- [28] N. Kallel, K. Fröhlich, S. Pignard, M. Oumezzine, H. Vincent, J. Alloys Compd. 399 (2005) 20–26.
- [29] J.B. Goodenough, A.L. Loeb, Phys. Rev. 98 (2) (1955) 391.
- [30] Y. Sun, W. Tong, Y. Zhang, J. Magn. Magn. Mater. 232 (2001) 205.
- [31] H. Song, W. Kim, S.J. Kwon, J. Appl. Phys. 89 (2001) 3398.
- [32] S. Kallel, N. Kallel, O. Peña, M. Oumezzine, J. Mater. Lett. 64 (2010) 1045.
- [33] J. Fan, L. Pi, L. Zhang, W. Tong, L. Ling, B. Hong, Y. Shi, W. Zhang, D. Lu, Y. Zhang, Physica B 406 (2011) 2289.
- [34] J.S. Amaral, M.S. Reis, V.S. Amaral, T.M. Mendonça, J.P. Araújo, M.A. Sa, P.B. Tavares, J.M. Vieira, J. Magn. Magn. Mater. 290–291 (2005) 686.
- [35] B.K. Banerjee, Phys. Lett. 12 (1964) 16.
- [36] V.K. Pecharsky, K.A. Gschneidner, J. Magn. Magn. Mater. 200 (1999) 44.
- [37] J.S. Amaral, V.S. Amaral, J. Magn. Magn. Mater. 322 (2010) 1552.
- [38] M.H. Phan, S.C. Yu, N.H. Hur, Y.H. Yeong, J. Appl. Phys. 96 (2004) 1154.
- [39] P.G. Radaelli, D.E. Cox, M. Marezio, S.W. Cheong, P.E. Schiffer, A.P. Ramirez, Phys. Rev. Lett. 75 (1995) 4488.
- [40] Z.B. Guo, Y.W. Du, J.S. Zhu, H. Huang, W.P. Ding, D. Feng, Phys. Rev. Lett. 78 (1997) 1142.
- [41] P.G. Radaelli, G. Iannone, M. Marezio, H.Y. Hwang, S.W. Cheong, J.D. Jorgensen, D.N. Argyriou, Phys. Rev. B 56 (1997) 8265.
- [42] M. Muroi, R. Street, P.G. McCormick, J. Appl. Phys. 87 (2000) 3424.
- [43] M.A. Oumezzine, O. Peña, S. Kallel, N. Kallel, T. Guizouarn, F. Gouttefangeas, M. Oumezzine, Appl. Phys. A 8 (2013) 7681.
- [44] M.A. Oumezzine, O. Peña, T. Guizouarn, R. Lebullenger, M. Oumezzine, J. Magn. Magn. Mater. 324 (2012) 2821.
- [45] A.N. Ulyanov, J.S. Kim, Y.M. Kang, D.G. Yoo, S.I. Yoo, J. Appl. Phys. 104 (2008) 113916.
- [46] K. Yadav, M.P. Singh, F.S. Razavi, G.D. Varma, Mater. Chem. Phys. 137 (2012) 323.
- [47] A. Rostamnejadi, M. Venkatesan, P. Kameli, H. Salamati, J.M.D. Coey, J. Magn. Magn. Mater. 323 (2011) 2214.
- [48] H. Yang, Y.H. Zhu, T. Xian, J.L. Jiang, J. Alloys Compd. 555 (2013) 150.
- [49] M.H. Phan, H.X. Peng, S.C. Yu, N.D. Tho, H.N. Nhat, N. Chau, J. Magn. Magn. Mater. 316 (2007) e562.
- [50] V.K. Pecharsky, K.A. Gschneidner, Annu. Rev. Mater. Sci. 30 (2000) 387.
- [51] H. Oesterreicher, F.T. Parker, J. Appl. Phys. 55 (1984) 4334.
- [52] M. Pekala, J. Appl. Phys. 108 (2010) 113913.
- [53] C.P. Reshmi, S. Savitha Pillai, M. Vasundhara, G.R. Raji, K.G. Suresh, M. Raama Varma, J. Appl. Phys. 114 (2013) 033904.
- [54] V. Franco, C.F. Conde, J.S. Blazquez, A. Conde, P. Svec, D. Janičković, L.F. Kiss, J. Appl. Phys. 101 (2007) 093903.
- [55] P. Nisha, S. Savitha Pillai, M. Raama Varma, K.G. Suresh, Solid State Sci. 14 (2012) 40e47.
- [56] Kh.K. Aliev, I.K. Karnilov, A.M. Ornarov, Sov. Phys. JETP 67 (1988) 11.