



Life cycle assessment of lithium nickel cobalt manganese oxide (NCM) batteries for electric passenger vehicles

Xin Sun ^{a, b, c}, Xiaoli Luo ^{a, b}, Zhan Zhang ^{a, b}, Fanran Meng ^d, Jianxin Yang ^{a, b, *}

^a State Key Laboratory of Urban and Regional Ecology, Research Center for Eco-Environmental Sciences, Chinese Academy of Sciences, No.18 Shuangqing Road, Haidian District, Beijing, 100085, China

^b College of Resources and Environment, University of Chinese Academy of Sciences, No. 80 East Zhongguancun Road, Haidian District, Beijing, 100190, China

^c China Automotive Technology and Research Center Co, Ltd, No. 68 East Xianfeng Road, Dongli District, Tianjin, 300300, China

^d Sustainable Process Technologies Group, Faculty of Engineering, University of Nottingham, Nottingham, NG7 2RD, UK

ARTICLE INFO

Article history:

Received 26 September 2019

Received in revised form

18 June 2020

Accepted 21 June 2020

Available online 15 July 2020

Handling Editor: Cecilia Maria Villas Boas de

Keywords:

Lithium-ion power battery

Battery electric vehicle

Life cycle assessment

Battery recycling

ABSTRACT

This study evaluated and quantified the life cycle environmental impacts of lithium-ion power batteries (LIBs) for passenger electric vehicles to identify key stages that contribute to the overall environmental burden and to find ways to reduce this burden effectively. Primary data for the assessment were collected onsite from the two Chinese leading LIB suppliers, two leading cathode material producers and two battery recycling corporations from 2017 to 2019. Six environmental impact categories, including primary energy demand (PED), global warming potential (GWP), acidification potential (AP), photochemical oxidant creation potential (POCP), eutrophication potential (EP) and human toxicity potential (HTP), were considered in accordance with the ISO 14040/14044 standards.

The results indicate that material preparation stage is the largest contributor to the LIB's life cycle PED, GWP, AP, POCP, EP and HTP, with the cathode active material, wrought aluminum and electrolytes as the predominant contributors. In the production stage, vacuum drying and coating and drying are the two main processes for all the six impact categories. In the end-of-life stage, waste LIBs recycling could largely reduce the life cycle POCP and HTP.

Sensitivity analysis results depict that replacing NCM 622 by NCM 811 as the cathode active material could increase all the six environmental impacts. We hope this study is helpful to reduce the uncertainties associated with the life cycle assessment of LIBs in existing literatures and to identify opportunities to improve the environmental performance of LIBs within the whole life cycle.

© 2020 Elsevier Ltd. All rights reserved.

1. Introduction

To save energy and reduce environmental emissions from the automotive industry, the Chinese government has launched numerous policies and programs to promote new energy vehicles (NEVs), which include battery electric vehicles (BEVs), plug-in hybrid electric vehicles (PHEVs), and fuel cell electric vehicles (FCEVs). In 2009, China launched the "Ten Cities and Thousand Vehicles" project to promote NEVs. From 2009 to 2012, a total of 17,000 NEVs were promoted (MOST et al., 2009). Since 2014, China

has been in the stage of large-scale promotion and application of NEVs. In 2018, the cumulative sales of NEVs reached 3.0 million, accounting for more than 53% of global cumulative sales (Wan, 2019). China has become the world's largest market for NEVs. By the end of 2019, the stock of NEVs reached 3.8 million, accounting for 1.5% of the total vehicles in China (Jiang, 2020).

As the core component of NEVs, the capacity of power batteries has also increased by a significant amount each year. China has been the world's largest power battery producer (MIIT, 2017). The cumulative installed capacity of power batteries in China reached 144 GWh by the end of 2018, which represents the largest power battery market worldwide (MIIT, 2019).

Currently, lithium-ion power batteries (LIBs), such as lithium manganese oxide (LiMn₂O₄, LMO) battery, lithium iron phosphate (LiFePO₄, LFP) battery and lithium nickel cobalt manganese oxide

* Corresponding author. State Key Laboratory of Urban and Regional Ecology, Research Center for Eco-Environmental Sciences, Chinese Academy of Sciences, No.18 Shuangqing road, Haidian District, Beijing, 100085, China.

E-mail addresses: yangjx@rcees.ac.cn, yangjxm@gmail.com (J. Yang).

($\text{LiNi}_x\text{Co}_y\text{Mn}_z\text{O}_2$, NCM) battery, are widely used in BEVs in China. According to the data from China Automotive Technology and Research Center Co., Ltd, NCM batteries accounted for 42% of the cumulative installed capacity of power batteries and 77% of the cumulative installed capacity of passenger BEVs until 2018 in China. Current types of NCM batteries in Chinese market include old-fashioned NCM 111 ($\text{LiNi}_{1/3}\text{Mn}_{1/3}\text{Co}_{1/3}\text{O}_2$), state-of-art NCM 622 ($\text{LiNi}_{0.6}\text{Mn}_{0.2}\text{Co}_{0.2}\text{O}_2$) and upcoming technology NCM 811 ($\text{LiNi}_{0.8}\text{Mn}_{0.1}\text{Co}_{0.1}\text{O}_2$) while NCM 622 batteries have been the most commonly used in electric passenger vehicles in China (CATARC and BIT, 2019).

NEV sales will maintain long-term growth in China benefiting from various policy supports. The "Technology Roadmap For Energy Saving And New Energy Vehicles" (TRESNEV Steering Committee China-SAE, 2016) shows that the total sales of NEVs is forecasted to exceed 5 million in 2025 and 15 million in 2030. This projection will lead to a huge number of demand and disposal of power batteries in China in the near future.

With the fast expansion of NEVs, China will be facing with challenges of waste power battery recycling and disposal. The capacity of decommissioned power batteries was 1.2 GWh in 2018 in China, and it is expected to be more than 200,000 tons by 2020, which indicates that about 25 GWh of power batteries need to be recycled and reused by 2020 (MIIT, 2019).

The environmental impacts associated with LIBs within the life cycle are key challenges that restrict the sustainable development of NEVs. First, LIBs contain various types of valuable metal materials, which can produce large amount of pollutants in the exploitation and extraction stages. In addition, the assembly process of LIBs can be energy intensive (Dai et al., 2019; Ellingsen et al., 2017). Finally, the improper recycling and waste disposal processes may incur negative environmental pollution and human toxicity. Therefore, an environmental assessment is required to quantify the overall environmental impacts of LIBs in BEVs application from a full life cycle perspective.

To address the gaps in environmental aspects of LIBs production and promote NEVs development in China. In this study, we aim to quantify the life cycle environmental impacts of NCM 622 batteries for electric passenger vehicles using the primary data collected from the latest and representative onsite investigations in China covering material production, LIB production and battery recycling plants. Inventory data is also supplemented by Ecoinvent 3.0, ANL GREET, 2018 database (ANL GREET, 2018) where available. The results can help identify the key contributors to the LIB life cycle environmental impacts and propose strategies to reduce these impacts effectively.

2. Literature review

Life cycle assessment (LCA) is a tool to assess the potential environmental impacts and resources used throughout a product's life cycle, i.e., from material preparation, via production and use phases, to waste management (ISO, 2006). Until now, there have been several LCA studies of LIBs. Notter et al. (2010) conducted an early LCA study of LMO batteries and the contributions to the environmental burden caused by different battery materials were analyzed. USEPA (2013) conducted a LCA study to bring together and use life cycle inventory data directly provided by LIB suppliers, manufacturers, and recyclers. Ellingsen et al. (2014) studied the cradle-to-gate environmental impacts of NCM batteries by using midpoint indicators, which include 13 impact categories. Kim et al. (2016) chose a commercial BEV and assessed the life cycle greenhouse gas (GHG) emissions and other air emissions of traction batteries.

In addition, other scientists have provided richer perspectives and deeper discussions. MajeauBettez et al. (2011) compared the

environmental impacts of three different LIBs, NCM, NiMH, and LFP batteries, during production and operation phases. They concluded that NiMH batteries have the highest environmental burden, followed by NCM and then LFP. Li et al. (2014) and Deng et al. (2017) reported the environmental impacts of next-generation LIBs compared with conventional LIBs to support the selection and development of future LIBs. Ellingsen et al. (2017) pointed out that both Notter et al. (2010) and Dunn et al. (2012) neglected processes in cell manufacturing and therefore underestimated the energy demand. Ellingsen et al. (2017) indicated that USEPA (2013) reported very different energy use associated with cell manufacturing and pack assembly for NCM, LFP, and LMO batteries without clear explanations. Peters et al. (2017) provided a review of LCA studies on LIB and found that only a few publications contributed original life cycle inventory (LCI) data. Peters et al. (2017) pointed that the majority of existing studies focus on GHG emissions or energy demand only, while the impacts in other categories such as toxicity might be even more important. Dai et al. (2019) analyzed the cradle-to-gate energy use, GHG emissions, SO_x , NO_x , PM_{10} emissions, and water consumption associated with current industrial production of NCM batteries. Dai et al. (2019) pointed out that the existing LCA studies of LIB, including the studies conducted by Notter et al. (2010), MajeauBettez et al. (2011), Dunn et al. (2012) and Ellingsen et al. (2014) were carried out when automotive LIBs were at their early commercialization stage which might be different from current practices. Besides, Dai et al. (2019) also identified knowledge gaps, such as the LCI data for graphite, LiPF_6 , and the separator, which should be improved in future studies.

Moreover, some studies have deeply discussed the environmental impacts during the recycling process of LIBs. Dunn et al. (2012) calculated the energy consumed and the air emissions generated when recycling LMO batteries in the U.S. and estimated that direct recycling could avoid 48% energy consumption associated with primary material production. Hendrickson et al. (2015) distinguished hydrometallurgical and pyrometallurgical recycling methods of LMO, LFP, and NCM batteries, and the results showed that hydrometallurgy achieves greater energy savings.

Although several LCA studies assessed LIBs, they presented significantly different results with large uncertainties associated with data and results (Dai et al., 2019; Ellingsen et al., 2017; Peters et al., 2017). First, for the background data, most of these studies used secondary LCI databases, disunified LCI databases, or literature publications as data sources. In addition, for the foreground data, most studies were conducted based on previous literature publications, engineering calculations and secondary data, and therefore did not reflect the current commercial-scale automotive LIB production. Furthermore, for the life cycle stages, most studies only focused on production (cradle-to-gate), while only a few have clearly assessed the end-of-life stage. Therefore, it is essential to assess the life cycle environmental impacts of LIBs with primary life cycle data in the context of China and identify the potential for reducing the environmental impacts of LIBs.

3. Methods

3.1. Goal and scope

The goal of this study is to assess the environmental impacts of NCM batteries within the battery life cycle and to identify the key contributory processes exploring improvement opportunities. In this study, the functional unit is defined as 1 kWh of the NCM 622 pack for a passenger BEV. As shown in Fig. 1, the system boundaries cover the life cycle stages of the LIB, including material preparation, production and end-of-life stages. The use stage is excluded in the LIB's system boundaries due to the large uncertainty of some key parameters, such as the real world driving cycles, different charging

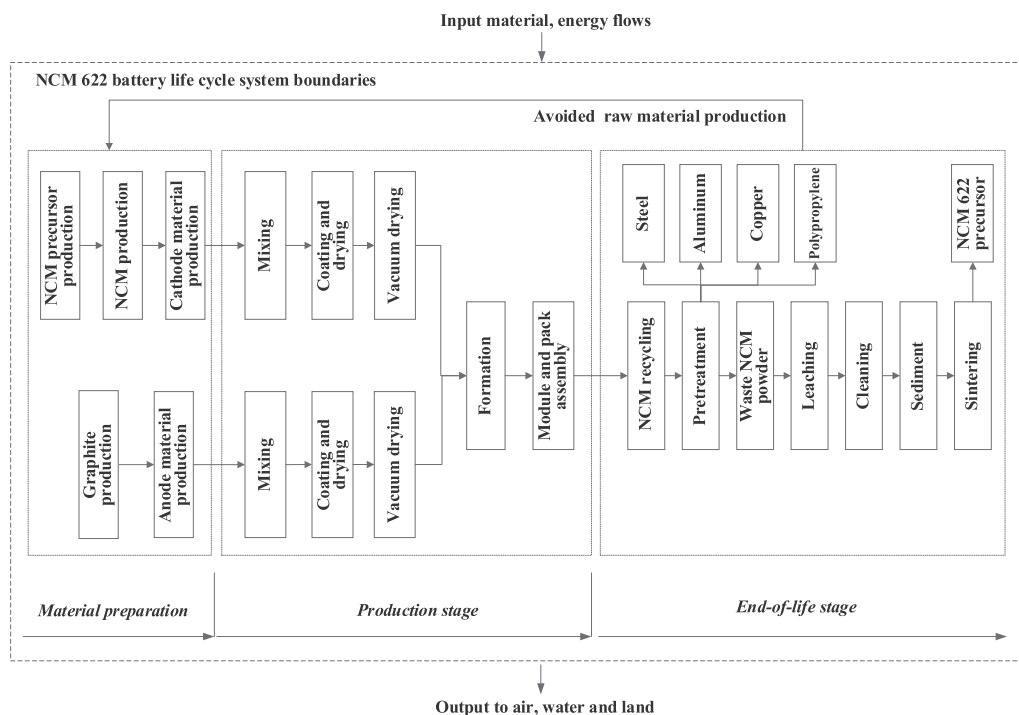


Fig. 1. System boundaries of NCM 622 batteries excluding use phase.

behaviors, battery replacement times, and the lack of unified allocation method of the electricity consumption of the battery pack.

This study was conducted in accordance with the principles of the ISO 14040 series standards for LCA (ISO, 2006). SimaPro 8 software (PRé Sustainability, Netherlands) was used as a support tool to establish the LCA model and perform the impact assessment.

3.2. Methods and databases

To collect the cradle to grave primary LCI data, this study conducted onsite investigations in six leading LIB factories (with a total China market share of over 75% in 2018), five leading LIB material producer and two battery recycling corporations from 2017 to 2019 in China. Considering the representative and completeness of the onsite data, this study chose the primary data from two Chinese leading LIB suppliers (world's top three), two leading cathode material producer (world's top five), and two battery recycling corporation (one owned by the world's top three LIB supplier, and the other one is the world's leading waste battery and cobalt nickel tungsten rare metal recycling corporation). A sensitivity analysis has been conducted to evaluate the data uncertainties.

The upstream materials and energy flows for NCM 622 precursor and NCM 622 production were obtained from onsite investigations of two leading cathode material producer in 2018 in China, which are of the world's top five NCM suppliers (Tables S 2 and S 3). For the LCI data of dimethyl carbonate (DMC), polyvinylidene fluoride (PVDF) and electronic parts, the foreground data were acquired from the ANL GREET, 2018 (Greenhouse Gases, Regulated Emissions, and Energy Use in Transportation) model, (ANL GREET, 2018). The background data were primarily based on the China Automotive Life Cycle Database (CALCD) (Sun et al., 2015, 2017, 2019) with Ecoinvent 3.0 database as supplements. The CALCD, a local Chinese LCI database developed by the China Automotive Technology and Research Center, is a process-based life cycle database. Detailed data source information is listed in Table S 1, Table S 2 and Table S 3 in the Supporting Information.

The CML-IA baseline V3.02 method developed by the Institute of Environmental Sciences of Leiden University is selected as the base method. Six impact categories, including primary energy demand (PED), global warming potential (GWP), acidification potential (AP), photochemical oxidant creation potential (POCP), eutrophication potential (EP) and human toxicity potential (HTP) are chosen from this approach to assess the impact characterization results, and these categories are easily communicated, of general interest, and important with respect to LIBs. As a comparison, ReCiPe Midpoint (H) V1.11/World Recipe H method is applied to present ten impact categories. The normalization and weighting phases are not included in this study.

3.3. Life cycle inventory analysis

3.3.1. Material preparation

For the investigated NCM 622 pack in this study, which is used by one passenger BEV, the pack energy capacity is 72.5 kWh, the pack weight is 630 kg, and the cycle life is 2000 times or 10 years. The energy density of the battery is 180 Wh/kg at the cell level and 115 Wh/kg at the pack level. Fig. 2 shows the material compositions of a 1 kWh LIB pack, including the cell materials and battery components. The cathode active material, NCM 622, accounts for 26.7% of the total LIB mass. The anode active material, graphite, accounts for 15.3% of the total LIB mass. The wrought aluminum used for the cathode electrode and enclosure represents 23.0% of the total LIB mass. The copper used for the anode electrode and terminal represents 8.6% of the total LIB mass. The electrolytes, including LiPF₆, Ethylene Carbonate (EC) and DMC, account for 18.5% of the total LIB mass. The polypropylene used for the separator comprises 1.5% of the total LIB mass. The battery components, including steel, thermal insulation, coolant electronic parts and wrought aluminum, account for 9.3% of the LIB mass. Detailed material compositions of NCM 622 pack are presented in Table S5 in the Supporting Information.

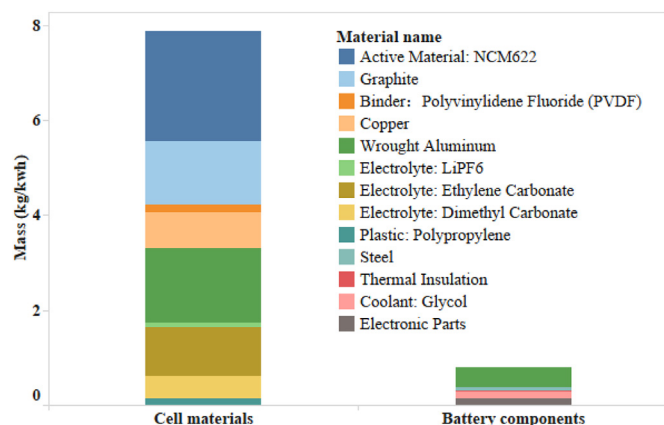


Fig. 2. Material compositions of per kWh NCM 622 battery.

3.3.2. Production stage

The production stage of NCM 622 battery includes cell manufacturing, module and pack assembly. Cell manufacturing consists of the mixing, coating and drying, vacuum drying and formation processes. The primary data are based on a cell production capacity of nearly 30 GWh/yr. A process-based and attributional approach was used to compile the inventory data.

In order to manufacture 1 kWh of cell, 72.0 MJ of electricity and 34.0 MJ of steam are consumed. The coating and drying process (dry room) consumes 25.2 MJ (35%) of electricity and 17.0 MJ (50%) of steam for dehumidification. Subsequently, the electrode vacuum drying process consumes 28.8 MJ (40%) of electricity and 17.0 MJ (50%) of steam. Then, the formation process consumes 10.8 MJ (15%) of electricity. In addition, the mixing process and module and pack assembly process consumes 3.6 MJ (5%) of electricity, respectively. Energy consumption for per kWh NCM 622 battery production are presented in Table S6 in the Supporting Information.

Therefore, considering the 4 MJ/kWh electricity required to fully charge the battery, it is estimated that the total energy consumption of the LIB production is 110.0 MJ/kWh. The vacuum drying contributes the largest share (42%) of the total energy demand, followed by the coating and drying process (38%). Formation accounts for 10% of the total energy demand. While the contribution of mixing process and module and pack assembly process are relatively lower than the other processes, accounting for 3%, respectively. Besides, 33.9 kg water is used in the mixing process, and 20 g particulate matter is emitted during the 1 kWh cell manufacturing.

3.3.3. End-of-life stage

The current main recycling technology for waste LIB include physical dismantling (Saeki et al., 2004; Zhang et al., 2007), pyrometallurgy (Bahat et al., 2007; Song et al., 2013) and hydrometallurgy (Chen et al., 2015; Nayaka et al., 2016; Sun and Qiu, 2012). In hydrometallurgy the materials in LIBs are selectively dissolved by chemical solvents and the metal elements are separated in the leachate. It could be used alone or in combination with pyrometallurgy and does not require high equipment and processing cost (Nayaka et al., 2016). Under optimized experimental conditions the recovery efficiency of 98.7% for Ni, 97.1% for Mn, 98.2% for Co and 81.0% for Li could be attained (Chen et al., 2015). Due to the wide application of hydrometallurgical methods for recycling waste LIBs in China and in order to simplify our model, it is assumed that used NCM 622 batteries are 100% collected and recycled by hydrometallurgical methods to feed into NCM 622 production loop and thus avoid the production of primary materials, such as steel, aluminum, polypropylene and copper. From the onsite investigations in two

Chinese large waste battery recycling corporations, including the one owned by the world's top three LIB supplier (Xie et al., 2015), and the other one that is the world's leading waste battery and cobalt nickel tungsten rare metal recycling corporation, the inventory data associated with the recycling of 1 kWh of waste LIBs are shown in Table 1. The primary data is based on a waste battery treatment capacity of 3,000 t/yr.

4. Results and discussion

4.1. Life cycle assessment results

The LCA results for the six environmental impact categories are shown in Fig. 3. The material preparation stage is the primary contributor to all of the six environmental impact categories, accounting for more than 95% of the total value, respectively. These impacts are mainly attributed to the production of the cathode active material (NCM 622), wrought aluminum and DMC. For POCP and HTP, the contribution from the material preparation stage takes account of around 200%, largely due to the production of wrought aluminum. The contribution of the production stage is relatively lower than the material preparation stage, accounting for 20.3% of the total GWP, 12.8% of the total PED and 9.2% of the total AP, 7.0% of the total POCP, around 2% of the total EP and HTP, respectively. In the production stage, cell manufacturing is the main contributor (around 95%) for all six impact categories due to the high energy consumption. For all six impact categories, the end-of-life stage contributions are negative. Waste NCM 622 battery recycling in the end-of-life stage can reduce 0.03 kg C₂H₄ e (105.2%) of the life cycle POCP and 41.6 kg 1,4-DB e (139.8%) of the life cycle HTP, mainly because of the recycling of waste wrought aluminum. Besides, waste NCM 622 battery recycling could also reduce 30.9 kg CO₂ e (33.0%) of the life cycle GWP and 158.3 MJ (14.7%) of the life cycle PED, due to the reproducing of NCM 622. The life cycle assessment results for per kg NCM 622 battery are shown in Table S 7 in the Supporting Information.

Table 2 presents the LCIA results of 10 types of impact categories by using the ReCiPe Midpoint (H) V1.11/World Recipe H RECIPE method. It is found that the results of GWP, AP, POCP, EP and HTP are similar to those assessed by the CML-IA baseline V3.02 method.

Table 1
Inventory Data for the Recycling of 1 kWh Waste NCM 622 Battery.

Category	Name	Value	Unit
Materials	Waste NCM battery	1.0	kwh
	H ₂ SO ₄ (98%)	9.6	kg
	HCl (30%)	0.3	kg
	NaOH (30%)	16.3	kg
	Na ₂ CO ₃	0.2	kg
	Ammonia (28%)	1.0	kg
	Extracting reagent P507	17.4	g
	Kerosene	42.5	g
	H ₂ O ₂	3.2	kg
	Industrial water	121.6	kg
	Li ₂ CO ₃	1.1	kg
	Electricity	20.3	kWh
	Natural gas	1.2	m3
	Wastewater	86.9	kg
Emissions	Ammonia nitrogen	0.5	g
	CO ₂	0.6	kg
	SO ₂	0.01	kg
	Dust	3.1	kg
Recycled Substances	Polypropylene	0.1	kg
	Copper	0.7	kg
	Aluminum	1.8	kg
	Steel	0.1	kg
	NCM Precursor	2.1	kg

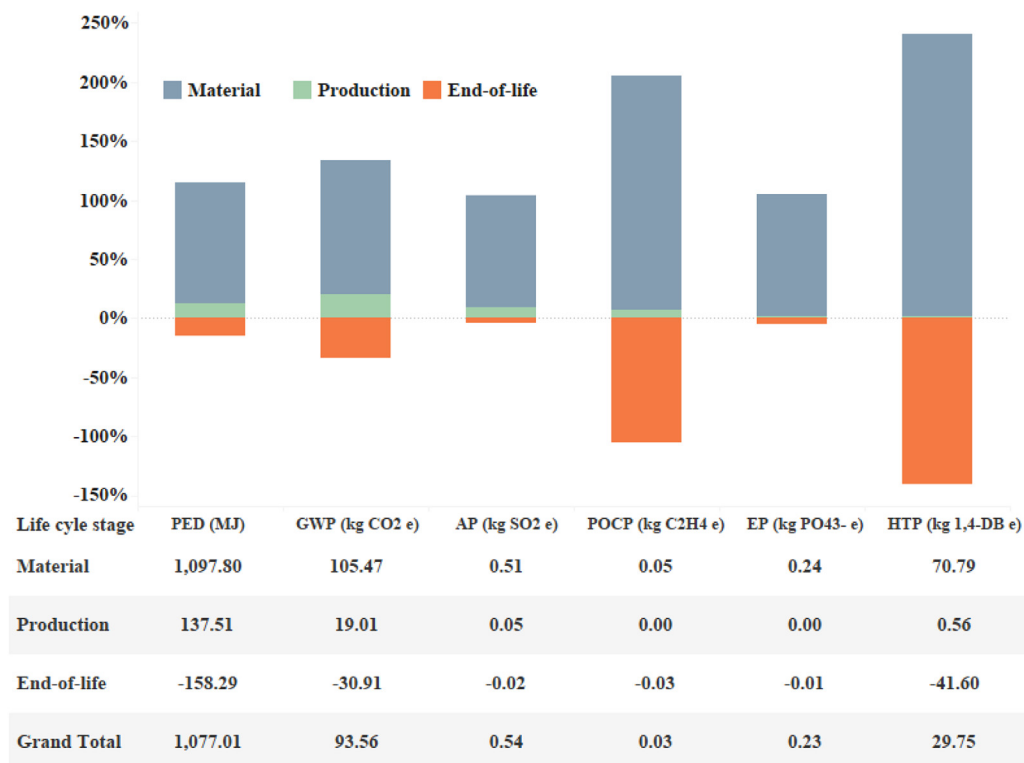


Fig. 3. Life cycle assessment results for per kWh NCM 622 battery (CML-IA baseline V3.02).

4.2. Identification of significant environmental impacts

Fig. 4 presents the relative contributions in the material preparation stage of 1 kWh NCM 622 battery. For the PED and GWP, the cathode active material (NCM 622) and wrought aluminum are the top two contributors, together accounting for around 75% of the battery materials. 60% of the AP, more than 40% of the PED and GWP is contributed by the NCM 622. Wrought aluminum is the most substantial contributor to the POCP and HTP, accounting for more than 60% and 70% of the battery materials, respectively. For the EP, however, the predominant contributor is the electrolytes DMC (73.3%), followed by NCM 622 (15.4%). Graphite contributes 10.8% for the PED, 6.9% for the GWP, 4.2% for the AP and less than 2% in the other three impact categories in the material preparation stage. For all the six impact categories, copper, LiPF₆ and electronic parts account for less than 4%, 7% and 7% of the battery materials, respectively.

Fig. 5 shows the relative contributions in the production stage of 1 kWh NCM 622 battery. Vacuum drying process accounts for the

largest proportion (more than 40%) for all the six environmental impact categories, followed by the coating and drying (around 36%), due to the large share of the energy demand in these two processes. Formation contributes to 10%–15% for the six environmental impact categories. The mixing process and module and pack assembly process account for less than 5% for the six environmental impact categories, respectively.

4.3. Comparative analysis

We compare the GHG emissions of NCM battery production (material preparation and production) with existing literature studies in Fig. 6. The total GHG emissions are disaggregated and associated with cell materials, battery components, cell manufacturing, module and pack assembly and others. Fig. 6 reports great variation in the overall production GHG emissions with results ranging between 73 and 200 kg CO₂ e/kWh, showing different contributions from cell materials, battery components, cell manufacturing and module and pack assembly. The result for

Table 2

Life cycle assessment results for per kWh NCM 622 battery (ReCiPe Midpoint (H) V1.11/World Recipe H).

Impact category	Unit	Material	Production	End-of-life	Total
Climate change (GWP)	kg CO ₂ eq	105.47	19.01	−30.91	93.57
Terrestrial acidification (AP)	kg SO ₂ eq	0.47	0.05	−0.03	0.49
Photochemical oxidant formation (POCP)	kg NMVOC	0.34	0.04	−0.09	0.29
Freshwater eutrophication (EP)	kg P eq	0.01	0.00	0.00	0.01
Marine eutrophication (EP)	kg N eq	0.13	0.00	−0.11	0.02
Human toxicity (HTP)	kg 1,4-DB eq	26.01	0.61	−14.09	12.53
Terrestrial ecotoxicity	kg 1,4-DB eq	0.03	0.00	−0.02	0.01
Freshwater ecotoxicity	kg 1,4-DB eq	21.43	0.00	−19.93	1.5
Particulate matter formation	kg PM10 eq	0.15	0.01	−0.01	0.15
Metal depletion	kg Fe eq	6.06	0.00	1.73	7.79
Fossil depletion	kg oil eq	24.67	3.12	−3.65	24.14

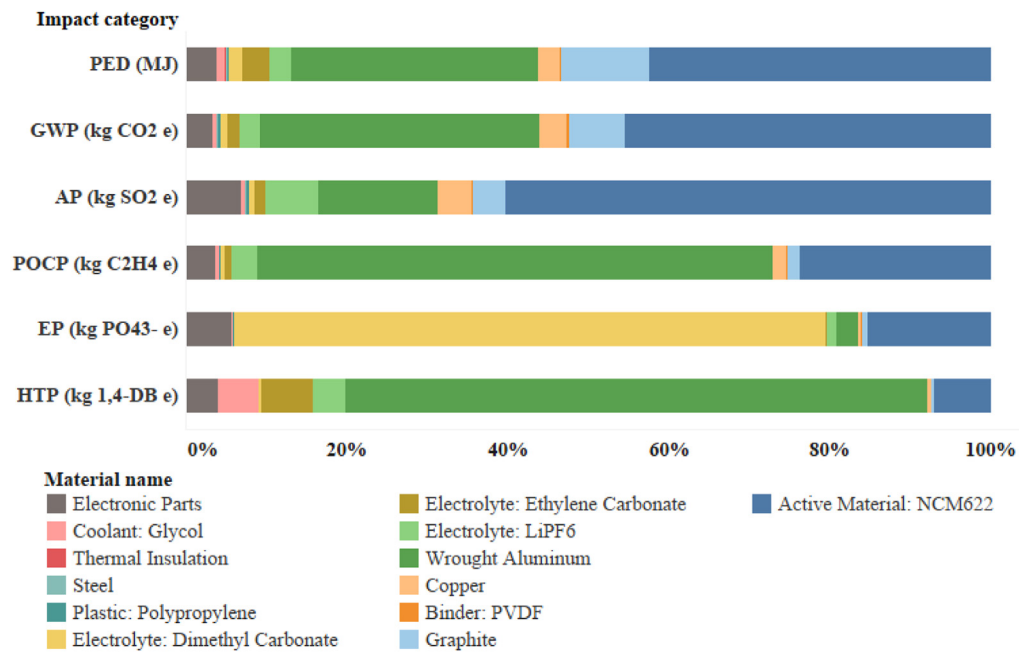


Fig. 4. Relative contributions of per kWh NCM 622 battery material.

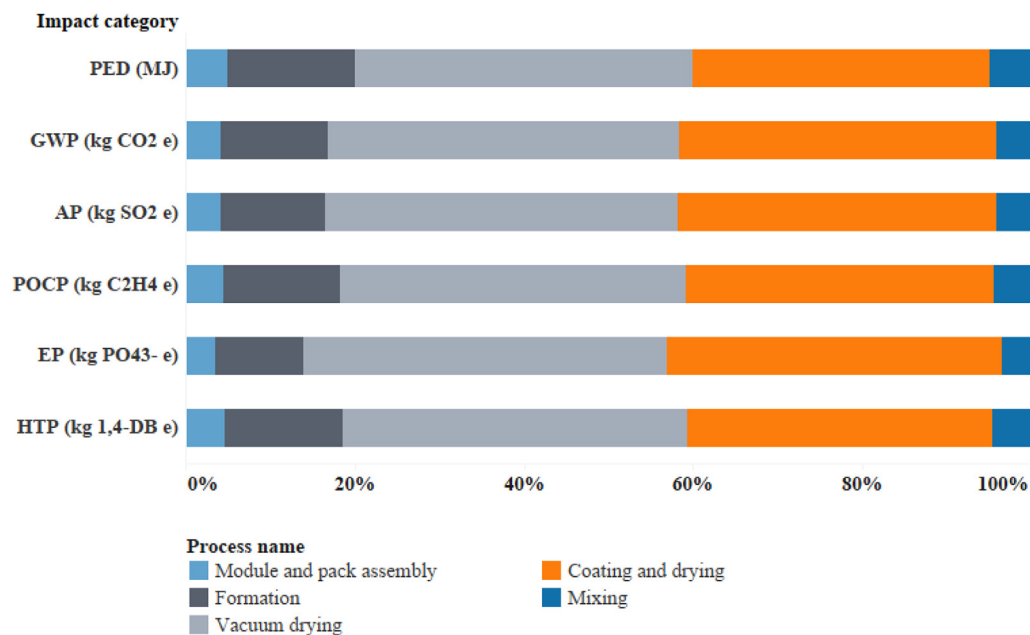


Fig. 5. Relative contributions of per kWh NCM 622 battery production.

NCM battery production GHG emissions in this study is 124.5 kg CO₂ e/kWh, which is similar to that reported by USEPA (2013). The production GHG emissions determined by MajeauBettez et al. (2011) where inventory data from Ecoinvent 2.2 database were used are nearly two times higher than this study. They based their energy data on industry reports published nearly 15 years ago, at their early commercialization stage, therefore it might not reflect current NCM battery production practices (Dai et al., 2019; Rydh and Sandén, 2005). It seems that Ellingsen et al. (2014) and Kim et al. (2016) where inventory data from Ecoinvent 3.1 database were used overestimated the energy consumption during the cell

manufacturing process, which are nearly six times higher than those in this study. The GHG emissions of the plant in the study of Ellingsen et al. (2014) and the underutilization of the plant in the study of Kim et al. (2016) would lead to the overestimation of energy intensity for cell production (Dai et al., 2019). The GHG emissions for cell manufacturing of this study (NCM 622) is similar with those of the study of Dai et al. (2019) (NCM 111), because the energy consumption data of this process are both based on Chinese factories. The GHG emissions for cell materials of this study is much higher than Dai et al. (2019) where inventory data were also supplemented by GREET model, as our study is for NCM 622 which

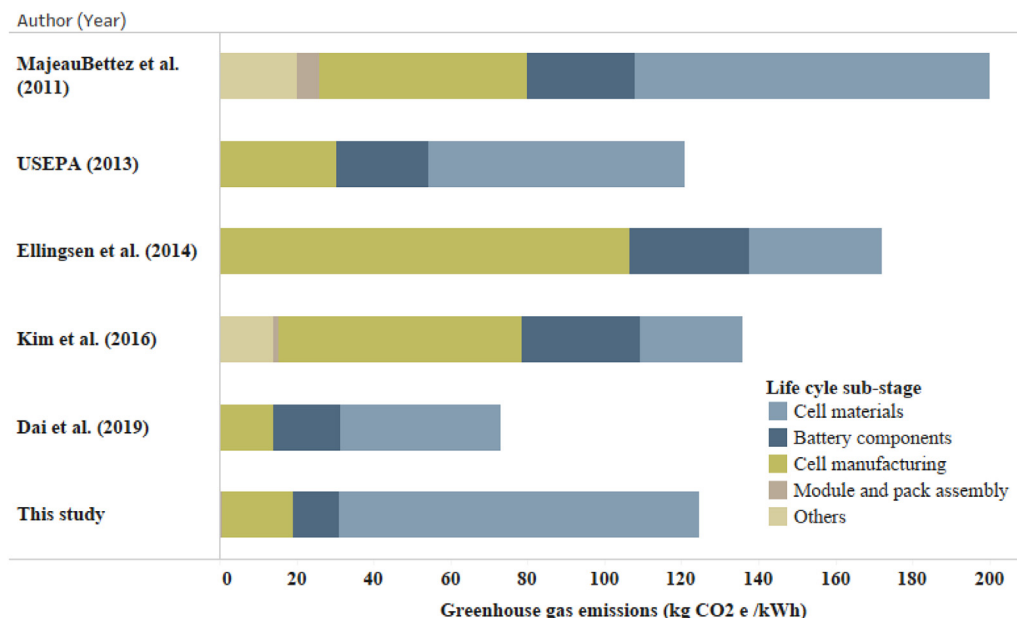


Fig. 6. GHG emissions of per kWh NCM battery production.

represents the state-of-art technology in China, while Dai et al. (2019) analyzed NCM 111 which represents the old-fashioned technology in China. The proportion of GHG emissions in the module and pack assembly is less than 1% for all the studies except MajeauBettez et al. (2011) (3%).

4.4. Sensitivity analysis

As shown in section 4.1, the material preparation stage is the primary contributor to all the six environmental impact categories, especially for the cathode active material, NCM 622. The current trend of NCM battery technology is to replace NCM 622 by NCM 811. Therefore, the sensitivity analysis is performed to evaluate the impacts of replacing NCM 622 by NCM 811. Based on expert consultation, the mass of cathode active material and battery energy density of the LIB are assumed to be not change despite the changes of the cathode active material chemistry. The sensitivity analysis results show that the total life cycle GWP, AP and POCP could be increased by around 1%, while the total life cycle PED, EP and HTP could be increased slightly by less than 0.3%. This is primarily because the increased content of NiSO₄ in the production of NCM 811 Precursor results in increased consumptions of steam, LiOH and oxygen for the final production of NCM 811 relative to per kg of NCM 622 (see Table S 2 and S 3 in the Supporting Information).

5. Conclusions

In this study, the environmental impacts of the most commonly used NCM 622 battery for passenger BEVs in China were assessed throughout the life cycle. Primary data were collected from two Chinese leading LIB suppliers (world's top three), two leading cathode material producer (world's top five), and two battery recycling corporations (one is owned by the world's top three LIB supplier, and the other one is the world's leading waste battery and cobalt nickel tungsten rare metal recycling corporation) from 2017 to 2019. The evaluation is presented in terms of six impact categories following the CML-IA baseline V3.02 method: primary

energy demand (PED), global warming potential (GWP), acidification potential (AP), photochemical oxidant creation potential (POCP), eutrophication potential (EP), and human toxicity potential (HTP). The study results can be listed as follows.

Firstly, the material preparation stage is the largest contributor to all the six environmental impact categories, largely due to the production of the cathode active material (NCM 622), wrought aluminum and electrolytes. The contribution of the production stage is relatively lower than the material preparation stage. Waste LIB recycling in the end-of-life stage could largely reduce the life cycle POCP and HTP of LIB, mainly because of the recycling of waste wrought aluminum. Secondly, in the material preparation stage, the battery cell materials, including the cathode active material and wrought aluminum are the predominant contributors to the PED and GWP. Wrought aluminum is the most substantial contributor to the POCP and HTP, while the electrolytes are the predominant contributor to the EP. In the production stage, vacuum drying and coating and drying processes are the top two contributors. Finally, from the sensitivity analysis, replacing NCM 622 by NCM 811 as the cathode active material could increase all the six environmental impacts.

However, the use stage is not included in the NCM 622 battery's system boundaries due to the large uncertainty of some key parameters, such as the real world driving cycles, different charging behaviors, battery replacement times, and the lack of unified allocation method of the electricity consumption of the battery pack. Therefore, when considering the whole LIB life cycle, it could cause quite different results for different impacts when including the use stage which shall be evaluated in the future studies when the key information is available. In order to better perform LIB eco-design, future LIB technologies should also emphasize by optimizing of the cathode active material with the preference on the impacts of different life cycle stages.

In addition, with the progress of LIB technology, continued environmental LCA efforts combined with the cost analysis based on primary data, especially for the recycling stage, are necessary to provide efficient strategies for full life cycle environmental impact reduction in LIBs and the whole value chain in sustainable development of BEVs.

Funding

This research was funded by the Key Projects of the National Natural Science Foundation of China (Grant No. 71734006).

Role of the funding source

The funding sources had no such involvement.

Declaration of competing interest

None.

Nomenclature

AP	Acidification potential
BEVs	Battery electric vehicles
CALCD	China automotive life cycle database
DMC	Dimethyl carbonate
EC	Ethylene carbonate
EP	Eutrophication potential
FCVs	Fuel cell electric vehicles
GWP	Global warming potential
HTP	Human toxicity potential
LCA	Life cycle assessment
LCI	Life cycle inventory
LiFePO ₄ , LFP	Lithium iron phosphate
LiMn ₂ O ₄ , LMO	Lithium manganese oxide
LiNi _{1-x-y} Co _y Mn _z O ₂ , NCM	Lithium nickel cobalt manganese oxide
LIBs	Lithium-ion power batteries
LIB	Lithium-ion power battery
NEVs	New energy vehicles
POCP	Photochemical oxidant creation potential
PHEVs	Plug-in hybrid electric vehicles
PVDF	Polyvinylidene fluoride
PED	Primary energy demand

Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.jclepro.2020.123006>.

References

- ANL GREET, 2018. The Greenhouse Gases, Regulated Emissions, and Energy Use in Transportation Model. Argonne National Laboratory, Chicago.
- Bahat, M., Farghaly, F.E., Basir, S.M.A., Fouad, O.A., 2007. Synthesis, characterization and magnetic properties of microcrystalline lithium cobalt ferrite from spent lithium-ion batteries. *J. Mater. Process. Technol.* 183, 117–121.
- CATARC and BIT, 2019. Development Report of New Energy Automobile Power Battery Recycling Industry in China. China gongxin publishing house Electronic Industry Press, Beijing.
- Chen, X., Chen, Y., Zhou, T., Liu, D., Hu, H., Fan, S., 2015. Hydrometallurgical recovery of metal values from sulfuric acid leaching liquor of spent Lithium-ion batteries. *Waste Manag.* 38, 349–356.
- Dai, Q., Kelly, J.C., Gaines, L., Wang, M., 2019. Life cycle analysis of lithium-ion batteries for automotive applications. *Batteries* 52, 48.
- Deng, Y., Li, J., Li, T., Zhang, J., Yang, F., Yuan, C., 2017. Life cycle assessment of high capacity molybdenum disulfide lithium-ion battery for electric vehicles. *Energy* 123, 77–88.
- Dunn, J.B., Gaines, L., Sullivan, J., Wang, M.Q., 2012. Impact of recycling on cradle-to-gate energy consumption and greenhouse gas emissions of automotive Lithium-ion batteries. *Environ. Sci. Technol.* 46, 12704–12710.
- Ellingsen, A.W., Hung, C.R., Strømman, A.H., 2017. Identifying key assumptions and differences in life cycle assessment studies of lithium-ion traction batteries with focus on greenhouse gas emissions. *Transport. Res. Transport Environ.* 55, 82–90.
- Ellingsen, A.W., Majeau-Bettez, G., Singh, B., Srivastava, A.K., Valøen, L.O., Strømman, A.H., 2014. Life cycle assessment of a lithium-ion battery vehicle pack. *J. Ind. Ecol.* 18, 113–124.
- Hendrickson, T.P., Kavvada, O., Shah, N., Sathre, R., Scown, C.D., 2015. Life-cycle implications and supply chain logistics of electric vehicle battery recycling in California. *Environ. Res. Lett.* 10, 014011.
- ISO, 2006. ISO 14040: 2006 Environmental Management-Life Cycle Assessment-Principles and Framework. International Organization for Standardization, Geneva.
- Jiang, L., 2020. The number of private vehicles in China exceeded 200 million for the first time, and the number of vehicles in 66 cities exceeded one million. In: People's Public Security Report.
- Kim, H.C., Wallington, T.J., Arsenault, R., Bae, C., Ahn, S., Lee, J., 2016. Cradle-to-Gate emissions from a commercial electric vehicle Li-ion battery: a comparative analysis. *Environ. Sci. Technol.* 50, 7715.
- Li, B., Gao, X., Li, J., Yuan, C., 2014. Life cycle environmental impact of high-capacity lithium ion battery with silicon nanowires anode for electric vehicles. *Environ. Sci. Technol.* 48, 3047–3055.
- MajeauBettez, G., Hawkins, T.R., Strømman, A.H., 2011. Life cycle environmental assessment of Lithium-ion and nickel metal hydride batteries for plug-in hybrid and battery electric vehicles. *Environ. Sci. Technol.* 45, 4548–4554.
- MIIT, 2017. In: Website, C (Ed.), Ministry of Industry and Information Technology: China Has Become the World's Largest Power Battery Producer (China Website).
- MIIT, 2019. New Energy Vehicle Power Battery Recycling Research Report. Ministry of Industry and Information Technology, Beijing.
- MOST, MF, NDRC, MIIT, 2009. Ten Cities Thousands of Energy Saving and New Energy Vehicle Demonstration and Application Project. MOST, Beijing. MF, NDRC, MIIT.
- Nayaka, G.P., Pai, K.V., Santhosh, G., Manjanna, J., 2016. Dissolution of cathode active material of spent Li-ion batteries using tartaric acid and ascorbic acid mixture to recover Co. *Hydrometallurgy* 161, 54–57.
- Notter, D.A., Gauch, M., Widmer, R., Wäger, P., Stamp, A., Zah, R., Althaus, H.-J., 2010. Contribution of Li-ion batteries to the environmental impact of electric vehicles. *Environ. Sci. Technol.* 44, 6550–6556.
- Peters, J.F., Baumann, M., Zimmermann, B., Braun, J., Weil, M., 2017. The environmental impact of Li-Ion batteries and the role of key parameters – a review. *Renew. Sustain. Energy Rev.* 67, 491–506.
- Rydh, C.J., Sandén, B.A., 2005. Energy analysis of batteries in photovoltaic systems. Part I: performance and energy requirements. *Energy Convers. Manag.* 46, 1957–1979.
- Saeki, S., Lee, J., Zhang, Q.W., Saito, F., 2004. Co-grinding LiCoO₂ with PVC and water leaching of metal chlorides formed in ground product. *Int. J. Miner. Process.* 74, S373–S378.
- Song, D.W., Wang, X.Q., Zhou, E.L., Hou, P.Y., Guo, F.X., Zhang, L.Q., 2013. Recovery and heat treatment of the Li(Ni_{1/3}Co_{1/3}Mn_{1/3})O₂ cathode scrap material for lithium ion battery. *J. Power Sources* 232, 348–352.
- Sun, L., Qiu, K., 2012. Organic oxalate as leachant and precipitant for the recovery of valuable metals from spent Lithium-ion batteries. *Waste Manag.* 32, 1575–1582.
- Sun, X., Meng, F., Liu, J., McKechnie, J., Yang, J., 2019. Life cycle energy use and greenhouse gas emission of lightweight vehicle – a body-in-white design. *J. Clean. Prod.* 220, 1–8.
- Sun, X., Zhang, P., Zhao, M., 2015. The life cycle energy consumptions and environmental impact assessment of the gasoline engine. *Acta Sci. Circumstantiae* 36, 3059–3065.
- Sun, X., Zheng, J., Zhang, P., 2017. Comparative life cycle assessment of Chinese radial passenger vehicle tire. *Mater. Sci. Forum* 898, 2432–2445.
- TRESNEV Steering Committee China-SAE, 2016. Technology Roadmap for Energy Saving and New Energy Vehicles. China Machine Press, Beijing.
- USEPA, 2013. Application of Life-Cycle Assessment to Nanoscale Technology: Lithium-Ion Batteries for Electric Vehicles. United States Environmental Protection Agency.
- Wan, G., 2019. Promote the Healthy Development of the New Energy Vehicle Industry. China EV100 Forum 2019. China EV100, Beijing.
- Xie, Y., Yu, H., Yannan, O., Changdong, L., 2015. Environmental impact assessment of recycling waste traction battery. *Inorg. Chem. Ind.* 47, 43.
- Zhang, Q., Saeki, S., Tanaka, Y., Kano, J., Saito, F., 2007. A soft-solution process for recovering rare metals from metal/alloy-wastes by grinding and washing with water. *J. Hazard Mater.* 139, 438–442.