

Accepted Manuscript

Electrical transport, microstructure and optical properties of Cr-doped In_2O_3 thin film prepared by sol-gel method

H. Baqiah, N.B. Ibrahim, M.H. Abdi, S.A. Halim

PII: S0925-8388(13)01001-3

DOI: <http://dx.doi.org/10.1016/j.jallcom.2013.04.089>

Reference: JALCOM 28383

To appear in:

Received Date: 18 February 2013

Revised Date: 12 April 2013

Accepted Date: 12 April 2013

Please cite this article as: H. Baqiah, N.B. Ibrahim, M.H. Abdi, S.A. Halim, Electrical transport, microstructure and optical properties of Cr-doped In_2O_3 thin film prepared by sol-gel method, (2013), doi: <http://dx.doi.org/10.1016/j.jallcom.2013.04.089>



This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Electrical transport, microstructure and optical properties of Cr-doped In_2O_3 thin film prepared by sol-gel method

H. Baqiah^a, N.B Ibrahim^{a*}, M.H. Abdi^a & S.A.Halim^b

^aSchool of Applied Physics, Faculty of Science and Technology, Universiti Kebangsaan Malaysia, 43600 Bangi, Selangor Malaysia

^bSuperconductors and Thin film laboratory, Department of Physics, Faculty of Science, University Putra Malaysia 43400 UPM Serdang, Selangor

Corresponding author: baayah@ukm.my

Abstract

High transparent In_2O_3 and Cr-doped In_2O_3 ($\text{In}_{2-x}\text{Cr}_x\text{O}_3$) nanocrystalline thin films were prepared using a simple sol-gel method followed by a spin coating technique. The effect of Cr concentration on the structural, microstructure, electrical and optical properties of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ were systematically investigated using X-ray diffractometer (XRD), atomic force microscopy (AFM), UV-vis spectroscopy, field emission scanning electron microscopy (FESEM) and Hall effect technique. The films have good crystallization with preferred orientation to (222) direction. The lattice parameters, a , of In_2O_3 system increased at lowest dopants ($x=0.025$) and decreased as the dopant was further increased. The optical transmittance of films increased up to 98 % for $x=0.05$ and decreased for further Cr concentrations. From AFM measurement the films nanocrystals morphology was depending on Cr concentrations. The band gap was around 3.76 eV for pure and with $x \leq 0.075$ however it increased. The effect of Cr concentrations on conducting mechanisms of In_2O_3 film has been investigated from 80-300 K using thermal activated conduction band and hopping models. The films, at $x=0.0-0.075$, have typical semiconductor behaviour. Three different conducting mechanisms have been estimated. All thermal activation energies and conduction hopping parameters have been determined and analysed in details.

Keywords: sol-gel - indium oxide- transmittance - porosity- conducting mechanism- hopping conductivity models- thermal activated conduction band

1. Introduction

Transparent semiconductor oxides (TCO) are transparent materials with good electrical conductivity. It has been used for many applications such as flat-panel displays, solar cells and gas sensors. Several types of dopants have been introduced into the semiconductor structures in order to make them suitable for certain applications. Many researchers have studied the effect of dopant concentrations on the microstructure, electrical, optical transmission and magnetic properties of TCO in order to improve the material properties [1-6]. The function of dopant is to tune microstructure, transmission and electrical conductivity [1-12] of the semiconductor materials.

Indium (III) oxide (In_2O_3) is one of the (TCO) with a wide band gap value i.e. 3.6 eV. Its electrical and physical properties could also be improved by a doping process. It has been reported that doping In_2O_3 with Sn improves its electrical property making it suitable as an electrode in solar cells, photovoltaics and flat-panel displays [8, 9, 13, 14]. High transmittance (90%) at near-infrared region has been achieved by doping W in In_2O_3 [7].

Cr doped indium oxide has received great attention [15-18] since it has been reported as a possible candidate for dilute magnetic semiconductors [19]. Some researchers have been focused on the structural, optical and electrical properties of Cr doped In_2O_3 thin film which could give an explanation for possible magnetic properties [20, 21]. Hsu et al. studied the crystalline structural transition effect on the electronic-band structure of chromium-doped indium oxide prepared on different substrate Si and yttria-stabilized zirconia (YSZ) substrates by a rf sputtering at room temperature. The growth condition and different type of substrate used, can produce Cr doped In_2O_3 thin films with a different band gap value. It was also reported that the transmission, band gap and electrical properties of laser ablated Cr doped In_2O_3 thin films are dependent on different oxygen pressure during the preparation process [21]. A sol-gel method is a simple and low price method. It also offers precise control of material composition [22-24]. In this paper we report the effect of Cr concentration on structure, microstructure, electrical transport and optical properties of Cr doped In_2O_3 thin film. The details of the conducting mechanism of pure and Cr doped In_2O_3 system were also discussed. It was found that the microstructure, optical and conducting mechanism of indium oxide is highly dependent on the doping concentration of Chromium.

2. Experimental

Indium nitrate hydrated $\text{In}(\text{NO}_3)_3 \cdot \text{H}_2\text{O}$ and chromium chloride hexahydrate $\text{CrCl}_3 \cdot 6(\text{H}_2\text{O})$ were used as source materials of In^{+3} and Cr^{+3} for the preparation of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ thin films. Absolute ethanol and acetylacetone were used as solvents. To get a sol, $\text{In}(\text{NO}_3)_3 \cdot \text{H}_2\text{O}$ was firstly dissolved in mixture of absolute ethanol and acetylacetone and $\text{CrCl}_3 \cdot 6(\text{H}_2\text{O})$ was dissolved in absolute ethanol. Then each solution was stirred for 1 h at room temperature (30 °C). The solutions were then mixed and stirred for 2 h then it was filtered using 0.45 μm syringe filter and aged for 2 d. Then the aged solution was dropped onto a cleaned soda lime glass substrate and spins coated at 1500 rpm for 30 s. The coated layer was dried at 70 °C for 20 min to evaporate the organic solvent, followed by an annealing process at 500 °C for 30 min. The phase and crystal structure were investigated using a Bruker X-ray diffractometer (XRD) (2 θ from 15 to 60 °). The surface morphology and roughness were studied using a Nova atomic force microscope (AFM). The optical properties of the films were characterized using a Perkin Elmer (Lambda35) UV-visible spectrophotometer. The Hall Effect measurement was done using a Keithley 2700 multimeter and a Keithley sourcemeter by a Van der Pauw method.

3. Results and Discussion:

3.1. Microstructure analysis using X-ray diffractometer

Fig. 1 shows the X-ray diffraction patterns of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ with $x = (0 - 0.15)$. All observed peaks belong to bixbyite cubic structure with a space group of Ia-3 (206). There is no peak related to chromium oxide or its compound can be observed. The samples have polycrystalline structures with preferred orientation to (222) direction. In order to elucidate the effect of Cr doping in the unit cell of indium oxide, all XRD patterns have been analysed using an EVA software. The XRD patterns of all samples match with JCPDS card number 006-0416 for bulk indium oxide. The lattice parameter for pure sample is 10.108 Å, which is less than the value for standard bulk In_2O_3 (10.118 Å). The lattice parameters of all samples are summarized in Table 1. The effect of Cr concentration ranged from $x=0.025$ (1.25%) to $x=0.15$ (7.5 %) on the unit cell of indium oxide can be divided to two effects. For low doping where there isn't enough Cr^{3+} ion to replace indium site, Cr^{3+} sits at an interstitial site in unit cell instead, resulting in a small expansion of a lattice parameter a . This phenomena is possible because the ionic radius of Cr^{3+} ion ($R_{\text{Cr}}=0.61\text{Å}$) is smaller than the ionic radius of In^{3+} ($R_{\text{In}}=0.80\text{Å}$) and In_2O_3 has a bixbyite unit cell consists of 32 In atoms and 48 oxygen atoms. A similar result has been reported for Sn doped In_2O_3 [25-27]. For higher dopants $x>0.025$ (1.25%) the lattice parameter, a was monotonically decreased by increasing Cr concentration. The inset in Fig. 1 shows (222) plane shifts to lower angle for sample with low doping $x=0.025$ (1.25%) and shifts to higher angle with $x>0.025$.

The crystallite size of all samples was calculated using Scherrer's eq. (1) followed,

$$D = k \lambda / \beta \cos \theta \quad (1)$$

Where D , K , λ , β and θ are the crystalline size, Scherrer constant which is equal to 0.9, the wavelength of Cu K α radiation ($\lambda=1.5406\text{ Å}$), width at half maximum FWHM in radian and Bragg angle, respectively. The crystallite size calculated from the most intense peak i.e. (222) plane is tabulated in Table 1. All the parameter in the eq. (1) was determined from the analysis of the XRD pattern using the EVA software. The results show that the crystallites sizes are independent from the Cr concentrations.

3.2. Morphology and Microstructure analysis

Fig. 2 shows AFM 2D and 3D of images (5 μm x 5 μm) of the thin films. It clearly shows that the morphology of indium oxide affected by chromium concentrations and has a different growth pattern. For samples $x=0.025$ and $x=0.05$, the grains have a spherical shape and tend to agglomerate to each other. Sample $x=0.075$, the surface has spherical particles with better distribution however small pores can be observed on the surface. By increasing the Cr

doping, the porosity increases and the spherical shape of grain changes and tend to elongate and form in flowers like shape for $x=0.15$. The root mean square roughness varied from 1.755 nm for sample $x=0.025$ to 7 nm for sample with $x=0.15$ and this variation depends on the grains agglomeration and porosity of the sample's surface as can be noted in Fig. 2.

Fig. 3 shows a typical FESEM cross section micrographs for the sample with $x=0.00$ and $x=0.05$. The films have smooth dense thin layer and consist of small particles. The film also shows good adhesion to glass substrate.

Fig. 4 shows the XPS spectra of elemental composition of sample with $x=0.05$. The In 3d spectra appear at 444.47 eV and 452.06 eV for In 3d_{5/2} and In 3d_{3/2} transition. The Cr 2p spectra appear at 576.83 eV and 586.23 eV for Cr 2p_{3/2} and Cr 2p_{1/2} which are related to Cr⁺³ states for Cr atom. The spectra of O 1s can be split into two peaks at 529.57 eV and 531.18 eV. The first transition belongs to In-O bonding in In₂O₃ system. The shifting of O 1s spectra in the second transition could be related to the change of the surrounding Oxygen atoms. Oxygen vacancies and Cr dopant have role to determine properties of TCO systems.

3.3. Electrical properties of Cr doped In₂O₃ at room temperature (30°C)

The electrical properties at room temperature (30°C) of Cr doped indium oxide thin films are shown in Fig. 5. The resistivity, carrier concentration and mobility of pure indium oxide are 0.29 $\Omega\cdot\text{cm}$, $1 \times 10^{19} \text{ cm}^{-3}$ and $2.1 \text{ cm}^2 \text{ V}^{-1} \text{ S}^{-1}$ respectively. In earlier reports of In₂O₃ prepared by the sol-gel method followed by multiple-dipping process, the resistivity, carrier concentration and mobility are around 0.6 $\Omega\cdot\text{cm}$, $2.1 \times 10^{19} \text{ cm}^{-3}$ and $0.2 \text{ cm}^2 \text{ V}^{-1} \text{ S}^{-1}$ for In₂O₃ thin film annealed twice at 500 °C. First annealing at 500 °C gives the resistivity of 5 $\Omega\cdot\text{cm}$ for [28]. Our pure In₂O₃ has lower resistivity and higher mobility compared with the previous report. This is due to the good crystallinity and dense layer of the films (see Fig. 1 and Fig. 3). Fig. 5 also shows that the resistivity of all films increases while the carrier concentration decreases gradually with the increment of Cr concentration. Based on the stoichiometry calculation involved during the sample preparation, increasing the Cr dopant will reduce the In. The conductivity of In₂O₃ system is originated from interstitial indium that acts as a shallow donor level near the conduction band. The generation of carrier concentration occurs when interstitial indium and oxygen vacancies exist in the system [29]. Thus increasing the dopant will reduce the carrier concentration and the resistivity will increase. Another factor that could cause the increase of resistivity of films is the porosity that starts to appear at $x=0.075$ and increases with the increment of Cr. Fig 5 also shows the effect of Cr concentrations on the mobility of the In₂O₃ thin films. The relation between carrier concentrations (n) and mobility (μ) is given by $\mu = 1/epn$ (ρ is the resistivity and e is the electron charge). This equation clearly indicates why mobility increases while the carrier concentration decreases. Similar results have been reported by [3, 30].

3.4 Conducting mechanism at low temperature

The conducting mechanism of pure and Cr-doped indium oxide below room temperature has been studied using thermal activated conduction band and hopping models which are commonly used to describe conducting mechanism in semiconductors [31-34]. Three different conducting regions could be estimated using linear fitting techniques. A minimum fitting coefficient that has been used is more than or equal to 0.99. The conducting mechanism of doped semiconductor could cross over from thermal activated to nearest-nearest neighbor hopping (NNH) to a variable range hopping with decreasing temperature [35]. First, the conductivity at room temperature has been fitted with eq. (2) in order to check the possibility of thermal activation conduction. Second, conductivity above 80 K has been fitted with hopping conductivity models. The third region has been determined by the mean of best line fit with all previous models as it is further illustrated below.

$$c = c_0 \exp(-E_{a1}/k_B T) \quad (2)$$

Fig. 6 shows an Arrhenius plot of pure and Cr doped indium oxide. All samples show typical semiconductor behavior in the temperature range from 80 K to 300 K. Maximum fitting of eq. (2) has been found nearly in the range 200-300 K. This indicates the electrical conductivity in this range is dominated by thermal activated conduction band. The temperature range, fitting coefficient R^2 and thermal activated conduction band are shown in Table 2. The thermal activated conduction band of thin films decreases when the Cr doping increases. It is known that the conductivity of pure In_2O_3 is originated from the coexistence of interstitial indium atoms and oxygen vacancy. Interstitial indium acts as a shallow donor while an oxygen vacancy helps the formation of carriers [29]. The doping of Cr may form a deep impurity band in band gap which causes a shallow donor or an oxygen vacancy decreases thus reduces the thermal activation energy, E_a . Similar behavior has been observed in Mn doped ZnO thin films [31].

For further investigation of the conductivity mechanism in the range 200-300 K, the effect of grain boundary on the transport properties is evaluated by calculating the Debye screening length for n type semiconductor as follows [36]

$$L_D = \left(\frac{\epsilon \epsilon_0 k_B T}{e^2 N_d} \right)^{1/2} \quad (3)$$

Where ϵ dielectric constant, ϵ_0 is the dielectric constant of vacuum and N_d is donor concentration from Hall effect measurement. If L_D is smaller than $l/2$, where l is the grain

size, there is a potential barrier affects the passing electron across the grain boundary. The calculated L_D is listed in Table 2. The L_D is smaller than $l/2$ which means that the grain boundary scatters the passing electron through it. The conductivity through grain boundary barrier σ_b is described by eq. (4) [33]

$$\sigma_b = CT^{-1/2} \exp(-E_b/k_B T) \quad (4)$$

Where C is constant and E_b is the activated energy for grain boundary limited conductivity K_B is the Boltzmann constant. The relation between $\ln \sigma_b T^{1/2}$ and $1/T$ has good linearity which confirms the thermionic emission through grain boundary. The E_b has been calculated from the slope line and listed in Table 2.

The second region is determined after region I and region III have been estimated with the benefit of the rule that thermal activated conduction band occurs at high temperature while the variable range hopping conduction occurs at low temperature [35]. The conductivity in region II for samples with $x=0.0-0.05$ is most suitable to be described with nearest-nearest hopping (NNH). This requirement of variable range hopping isn't fulfilled due to the small value of localize hope length in this region, $\xi < 1$ nm. Also the NNH mechanism occurs at relatively high temperature. The conductivity at high temperature can be generally expressed by eq. (5). The NNH mechanism in the range 150-200 K was also reported for SnO_2 film prepared by sol-gel spin coated method by [32].

$$c = c_{01} \exp(-E_{a1}/k_B T) \text{ Region II } \exp(-E_{a2}/k_B T) \quad (5)$$

The first part of the equation represents conductivity characterized by thermal activated conduction band and the second part represent conductivity by hopping between nearest-nearest neighbors [35]. The activated energy for NNH hopping is calculated from the second part of eq. (5). Fig. 7a shows the relation between $\ln \sigma$ and $1/T$ in the range of 130-200 K for samples with $x=0-0.05$. The temperature range and fitting coefficient are listed in Table 2. It can be noticed that $E_{a1} > E_{a2}$ because the first one E_{a1} is the thermal excitation of electrons from shallow donor to the conduction band while the E_{a2} is thermal excitation within donor level itself.

At lower temperature the number of free neighbor sites becomes too small and these results in freezing out the NNH hopes which could lead to new hopping mechanism called variable range hopping (VRH). The hopping arises between sites in vicinity of Fermi level and it doesn't have a constant distance like nearest-nearest neighbor hopping. If the density state around the Fermi level is constant, there is a possibility to Mott VRH mechanism. On the other hand if there is a gap at the Fermi level due to electron-electron interaction the hopping mechanism is related to Efros-Shklovskii (ES) VRH [35].

The conductivity via Mott VRH mechanism is given by eq. (6)

$$\sigma_{VRH\ Mott} = \sigma_{0\ Mott} T^{-1/2} \exp(-T_{0\ Mott}/T)^{1/q} \quad (6)$$

For thin film q is supposed to equal 3 for two dimensions hopping while it can be 4 for three dimensions hopping. $\sigma_{0\ Mott}$ is given by eq. (7)[37].

$$\sigma_{0\ Mott} = \frac{3e^2 v}{(8\pi)^{1/2}} \left(\frac{\xi N(E_F)}{k_B} \right)^{1/2} \quad (7)$$

And $T_{0\ Mott}$ is as follows

$$T_{0\ Mott} = \frac{18}{k_B \xi^3 N(E_F)} \quad (8)$$

Where $\sigma_{0\ Mott}$ is hopping conductivity, v is phonon length, $T_{0\ Mott}$ is characterized temperature depends on the density state on Fermi level $N(E_F)$ and ξ is localization length

For sample with $x=0.075$, it is interestingly found that it has best fitting and satisfy the conditions of Mott VRH for region II in the range 135-210 K. Fig. 7b show the relation between $\ln \sigma T^{1/2}$ and $T^{-1/3}$ is linear with fitness coefficient $R_2=0.9979$. The parameters of Mott variable hopping are given Table 3.

In order to verify the hopping condition, the hopping distance $R_{hop\ Mott}$ and hopping energy $\Delta_{hop\ Mott}$ has been calculated according to the eq. (9) and (10) [37].

$$R_{hop\ Mott} / \xi = \frac{3}{8} (T_{0\ Mott} / T)^{1/4} \quad (9)$$

$$\Delta_{hop\ Mott} = \frac{1}{4} k_B T (T_{0\ Mott} / T)^{1/4} \quad (10)$$

It can be noticed that the localize length ξ_{Mott} is in the order of nm and the ratio of hopping distance to localize length, $R_{hop\ Mott} / \xi_{Mott} > 1$ nm. This condition is satisfying the hopping condition of the system [38].

At lower temperature, in the range 85-130 K, the conducting mechanism for all samples is found to follow VRH ES, Fig. 8. The conductivity in VRH ES model is given by eq. (11)[39].

$$\sigma_{VRH ES} = \sigma_{0ES} T^{-1} \exp(-T_{0ES}/T)^{1/2} \quad (11)$$

Where T_{0ES} is given by

$$T_{0ES} = \frac{2.8e^2}{k_B \xi \mathcal{E}} \quad (12)$$

Where T_{0ES} is characteristic temperature and $\sigma_{VRH ES}$ hopping conductivity. The hopping parameters are listed in Table 4. The hopping distance $R_{hop ES}$ and hopping energy $\Delta_{hop ES}$ are calculated from the eq. (13) and (14) [39].

$$R_{hop ES} / \xi = \frac{1}{4} (T_{0ES} / T)^{1/2} \quad (13)$$

$$\Delta_{hop ES} = \frac{1}{2} k_B T (T_{0ES} / T)^{1/2} \quad (14)$$

The localize length ξ is in the order of nm while $R_{hop ES} / \xi_{ES} \geq 1$. These conditions are fulfilled the hopping conditions [38]. The increment of Cr concentration in In_2O_3 system reduces the hopping energy but increases the hopping distance and localize length, which result in reducing the hopping conductivity and characteristic temperature T_{0ES} . The VRH ES mechanism has been also observed at low temperature $T < 100K$ for SnO_2 thin film prepared by sol-gel spin coating method [32].

3.5. Optical properties of Cr doped In_2O_3

The optical transmission of undoped and chromium doped indium oxide is shown in Fig. 9a. The transmission is over 90% for all samples. Since the samples have different thickness, the absorption coefficient versus wavelength has been plotted in order makes a better optical properties comparison between the sample (Fig. 9b). It can be observed that the absorption above 560 nm decreases with the increment of Cr dopant up to $x=0.05$ then decreases for $x=0.075$. Table 5 presents a comparison between current results with other transparent thin film systems such as Al doped ZnO (AZO), Ga doped ZnO (GZO) and Sn doped In_2O_3

(ITO). It shows that our film with $x=0.05$ has highest transmission over all films and resistivity lower than GZO film however it has higher resistivity than ITO and AZO.

The relation between absorption coefficient and energy band gap can be given by the following eq. (14),

$$(\alpha h\nu)^n = (h\nu - E_g) \quad (15)$$

Where α is the absorption coefficient, $h\nu$ is the photon energy, and E_g is the energy band gap. n is a constant equal to 2, 2/3, 1/2, 1/3 for allowed direct, forbidden indirect, allowed indirect, forbidden indirect transitions, respectively. Band gap was estimated from the relation between $(\alpha h\nu)^2$ vs $h\nu$, see Fig. 10. This relation is parabolic curve and band gap was estimated by extrapolation straight line to the linear part to intersect $h\nu$ axis at E_g value. In our calculation, n was fixed to 2 because the extrapolation line has maximum fitness with curves at n equal 2.

The band gap for pure sample is 3.76 eV. This result was also reported by [43] for (222) oriented indium oxide thin film deposited on MgO (100) substrate by metal organic chemical vapour deposition (MOCVD). The band gaps of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ films have a little change for low dopant $x \leq 0.075$, however it increases at maximum Cr concentration, $x=0.15$, as summarized in Table. 1. The electrical measurement indicates that Cr dopant doesn't provide carrier (electrons) in In_2O_3 but decrease the carrier concentration gradually. So the widening of band gap doesn't follow Burstein–Moss (BM) shift for doped semiconductors associated with the increment of carrier concentration. This is in good agreement with a report in the literature. Caricato et al. have reported that the low Cr concentration in ITO narrows the band gap, however for high Cr concentration, the band gap is widening [44]. The doping of Cr at a high concentration could lead to disorder in crystal symmetry by shrinking the lattice parameters which leads to the reconstruction of band structure, thus widen the band gap (the relation between lattice parameter, a and band gap vs Cr concentrations is shown in Fig.11). On the other hand the relations between carrier concentration and band gap values is consistent with results reported for Cr-doped indium oxide prepared on Si substrate by rf sputtering at room temperature [20]. The carrier concentrations of annealed films are $7.8 \times 10^{20} \text{ cm}^{-3}$ and the band gap value is 3.63 eV. After heat treatment the carrier concentration is $2.0 \times 10^{20} \text{ cm}^{-3}$ and energy gap is 3.89 eV [20].

4. Conclusion

High quality In_2O_3 and Cr-doped In_2O_3 ($\text{In}_{2-x}\text{Cr}_x\text{O}_3$) nanocrystals thin films have been prepared by a simple sol-gel method followed spin coating technique. All films have single phase In_2O_3 structure and no traces of secondary phase related to Cr or its compound has been detected. The lattice parameter, of In_2O_3 system increased at lowest dopants ($x=0.025$) and decreases with the increment of dopants. In_2O_3 has 92% transmittance with resistivity,

mobility and band gap of 0.29 cm²V⁻¹S⁻¹ and 3.76 eV, respectively. The optical transmittance increased with the increment of Cr doping concentration up to 98% for x=0.05. The Cr dopant strongly affects the microstructure of In₂O₃ system. The sample's surface has spherical agglomerated particle at x=0.025-0.05. For samples with x≥0.075 the films surfaces become porous which increased with further doping. At x=0.15 the grains connect to each and form flower like microstructure. The root mean square roughness ranges from 1.755 nm for sample with x=0.025 to 7 nm for sample with x=0.15 and it is varied with dependence to the agglomeration of grains and porosity of the sample's surface. The band gap values show little change at low Cr concentration x≤0.075 and increased at x=0.15. The grain boundary affected the conduction in the range 300-200 K and its thermionic emission energy decreased with the increment of Cr dopant. The electrical conduction in the range 210-140 K was characteristic by nearest-nearest hopping conduction at x=0.00-0.05 and by Mott variable hopping at x=0.075. Efros-Shklovskii variable range hopping is found to dominant in the range 85-130 K for all samples. In₂O₃ and Cr doped In₂O₃ compound can be used as sensors and in transparent oxide applications.

Acknowledgement

This work was supported by Malaysian Ministry of Science and Technology via grant No. 03-01-02-SF0742 and UKM- OUP -FST -2012.

Reference:

- [1] V. Shelke, M.P. Bhole, D.S. Patil, Open air annealing effect on the electrical and optical properties of tin doped ZnO nanostructure, *Solid State Sciences*, 14 (2012) 705-710.
- [2] V. Shelke, M.P. Bhole, D.S. Patil, Opto-electrical characterization of transparent conducting sand dune shaped indium doped ZnO nanostructures, *Journal of Alloys and Compounds*, 560 (2013) 147-150.
- [3] V. Shelke, B.K. Sonawane, M.P. Bhole, D.S. Patil, Effect of annealing temperature on the optical and electrical properties of aluminum doped ZnO films, *Journal of Non-Crystalline Solids*, 355 (2009) 840-843.
- [4] V. Shelke, B.K. Sonawane, M.P. Bhole, D.S. Patil, Electrical and optical properties of transparent conducting tin doped ZnO thin films, *Journal of Materials Science: Materials in Electronics*, 23 (2012) 451-456.
- [5] B.K. Sonawane, V. Shelke, M.P. Bhole, D.S. Patil, Structural, optical and electrical properties of cadmium zinc oxide films for light emitting devices, *Journal of Physics and Chemistry of Solids*, 72 (2011) 1442-1446.
- [6] B.K. Sonawane, M.P. Bhole, D.S. Patil, Structural, optical and electrical properties of post annealed Mg doped ZnO films for optoelectronics applications, *Opt Quant Electron*, 41 (2009) 17-26.
- [7] M. Yang, J. Feng, G. Li, Q. Zhang, Tungsten-doped In₂O₃ transparent conductive films with high transmittance in near-infrared region, *Journal of Crystal Growth*, 310 (2008) 3474-3477.
- [8] N. Manavizadeh, F.A. Boroumand, E. Asl-Soleimani, F. Raissi, S. Bagherzadeh, A. Khodayari, M.A. Rasouli, Influence of substrates on the structural and morphological properties of RF sputtered ITO thin films for photovoltaic application, *Thin Solid Films*, 517 (2009) 2324-2327.

- [9] Z.-H. Li, E.S. Cho, S.J. Kwon, Laser direct patterning of the T-shaped ITO electrode for high-efficiency alternative current plasma display panels, *Applied Surface Science*, 257 (2010) 776-780.
- [10] R.K. Gupta, K. Ghosh, S.R. Mishra, P.K. Kahol, Structural, optical and electrical characterization of highly conducting Mo-doped In_2O_3 thin films, *Applied Surface Science*, 254 (2008) 4018-4023.
- [11] C. Shekhar, K.I. Gnanasekar, E. Prabhu, V. Jayaraman, T. Gnanasekaran, $\text{In}_2\text{O}_3+\text{xBaO}$ ($\text{x}=0.5\text{--}5\text{at.}\%$) – A novel material for trace level detection of NO_x in the ambient, *Sensors and Actuators B: Chemical*, 155 (2011) 19-27.
- [12] M.P. Bole, D.S. Patil, Effect of annealing temperature on the optical constants of zinc oxide films, *Journal of Physics and Chemistry of Solids*, 70 (2009) 466-471.
- [13] D.-W. Kang, S.-H. Kuk, K.-S. Ji, H.-M. Lee, M.-K. Han, Effects of ITO precursor thickness on transparent conductive Al doped ZnO film for solar cell applications, *Solar Energy Materials and Solar Cells*, 95 (2011) 138-141.
- [14] D. Antonia Sonia Alves Cardoso, The effects of various annealing regimes on the microstructure and physical properties of ITO ($\text{In}_2\text{O}_3:\text{Sn}$) thin films deposited by electron beam evaporation for solar energy applications, *Renewable Energy*, 36 (2011) 1153-1165.
- [15] D.J. Payne, E.A. Marquis, Three-Dimensional Spatial Distribution of Cr atoms in Doped Indium Oxide, *Chemistry of Materials*, 23 (2011) 1085-1087.
- [16] G.Z. Xing, J.B. Yi, D.D. Wang, L. Liao, T. Yu, Z.X. Shen, C.H.A. Huan, T.C. Sum, J. Ding, T. Wu, Strong correlation between ferromagnetism and oxygen deficiency in Cr-doped $\text{In}_{2-x}\text{O}_{3-\delta}$ nanostructures, *Physical Review B*, 79 (2009) 174406.
- [17] F.-X. Jiang, X.-H. Xu, J. Zhang, X.-C. Fan, H.-S. Wu, G.A. Gehring, Role of carrier and spin in tuning ferromagnetism in Mn and Cr-doped In_2O_3 thin films, *Applied Physics Letters*, 96 (2010) 052503-052503.
- [18] P. Kharel, C. Sudakar, M.B. Sahana, G. Lawes, R. Suryanarayanan, R. Naik, V.M. Naik, Room temperature ferromagnetism in Cr-doped In_2O_3 on high vacuum annealing of thin films and bulk samples, *Journal of Applied Physics*, 101 (2007) 09H117-109H117-113.
- [19] J. Philip, A. Punnoose, B.I. Kim, K.M. Reddy, S. Layne, J.O. Holmes, B. Satpati, P.R. LeClair, T.S. Santos, J.S. Moodera, Carrier-controlled ferromagnetism in transparent oxide semiconductors, *Nat Mater*, 5 (2006) 298-304.
- [20] H. C.Y, Effects of crystalline structural transition on electronic-band structure of chromium-doped indium oxide, *Thin Solid Films*, 520 (2012) 2311-2315.
- [21] N.B. Ukah, R.K. Gupta, P.K. Kahol, K. Ghosh, Influence of oxygen growth pressure on laser ablated Cr-doped In_2O_3 thin films, *Applied Surface Science*, 255 (2009) 9420-9424.
- [22] R. Shaiboub, N.B. Ibrahim, M. Abdullah, F. Abdulhade, The physical properties of erbium-doped yttrium iron garnet films prepared by sol-gel method, *J. Nanomaterials*, 2012 (2012) 1-5.
- [23] H.Z. Chen, M.C. Kao, S.L. Young, C.C. Yu, C.H. Lin, C.M. Lee, C.R. Ou, Effects of annealing atmosphere on microstructure and ferroelectric properties of praseodymium-doped $\text{Bi}_4\text{Ti}_3\text{O}_{12}$ thin films prepared by sol-gel method, *Thin Solid Films*, 517 (2009) 4818-4821.
- [24] F. Aldbea, N. B. Ibrahim, M. Abdullah, R. Shaiboub, Structural and magnetic properties of $\text{Tb}_x\text{Y}_{3-x}\text{Fe}_5\text{O}_{12}$ ($0 \leq x \leq 0.8$) thin film prepared via sol-gel method, *Journal of Sol-Gel Science and Technology*, 62 (2012) 483-489.
- [25] A. Bourlange, D.J. Payne, R.G. Palgrave, H. Zhang, J.S. Foord, R.G. Egdell, R.M.J. Jacobs, T.D. Veal, P.D.C. King, C.F. McConville, The influence of Sn doping on the growth of In_2O_3 on Y-stabilized $\text{ZrO}_2(100)$ by oxygen plasma assisted molecular beam epitaxy, *Journal of Applied Physics*, 106 (2009) 013703-013709.
- [26] Y. Shigesato, Y. Hayashi, T. Haranoh, Doping mechanisms of tin-doped indium oxide films, *Applied Physics Letters*, 61 (1992) 73-75.
- [27] J. Popović, E. Tkalec, B. Gržeta, C. Goebbert, V. Ksenofontov, M. Takeda, Defect structure examination of Sn-doped indium oxide (ITO), *Zeitschrift für Kristallographie Supplements*, 2007 (2007) 489-494.

- [28] M.A. Flores-Mendoza, R. Castanedo-Perez, G. Torres-Delgado, J. Márquez Marín, O. Zelaya-Angel, Influence of the annealing temperature on the properties of undoped indium oxide thin films obtained by the sol-gel method, *Thin Solid Films*, 517 (2008) 681-685.
- [29] T. Tomita, K. Yamashita, Y. Hayafuji, H. Adachi, The origin of n-type conductivity in undoped In_2O_3 , *Applied Physics Letters*, 87 (2005) 051911-051913.
- [30] J. Mazloom, F.E. Ghodsi, Spectroscopic, microscopic, and electrical characterization of nanostructured $\text{SnO}_2\text{:Co}$ thin films prepared by sol-gel spin coating technique, *Materials Research Bulletin*, 48 (2013) 1468-1476.
- [31] J. Han, M. Shen, W. Cao, A.M.R. Senos, P.Q. Mantas, Hopping conduction in Mn-doped ZnO, *Applied Physics Letters*, 82 (2003) 67-69.
- [32] N. Serin, A. Yildiz, A.A. Alsaç, T. Serin, Estimation of compensation ratio by identifying the presence of different hopping conduction mechanisms in SnO_2 thin films, *Thin Solid Films*, 519 (2011) 2302-2307.
- [33] S.K. Neogi, R. Ghosh, G.K. Paul, S.K. Bera, S. Bandyopadhyay, Effects of Co doping on structural, morphological and transport properties of sol-gel AZO thin films, *Journal of Alloys and Compounds*, 487 (2009) 269-273.
- [34] R. Kumar, N. Khare, Temperature dependence of conduction mechanism of ZnO and Co-doped ZnO thin films, *Thin Solid Films*, 516 (2008) 1302-1307.
- [35] V.F. Gantmakher, *Electrons and Disorder in Solids*, Oxford University Press, New York, 2005.
- [36] J.W. Orton, M.J. Powell, The Hall effect in polycrystalline and powdered semiconductors, *Reports on Progress in Physics*, 43 (1980) 1263.
- [37] E.A.D. N. F. Mott, *Electronic Properties in Non-crystalline Materials*, Clarendon Press, Oxford, 1971.
- [38] A. Yildiz, S.B. Lisesivdin, M. Kasap, D. Mardare, Electrical properties of TiO_2 thin films, *Journal of Non-Crystalline Solids*, 354 (2008) 4944-4947.
- [39] A.L.E. B. I. Shklovskii, *Electronic Properties of Doped Semiconductors*, Springer, Berlin, 1984.
- [40] K.E. Lee, M. Wang, E.J. Kim, S.H. Hahn, Structural, electrical and optical properties of sol-gel AZO thin films, *Current Applied Physics*, 9 (2009) 683-687.
- [41] C.-Y. Tsay, K.-S. Fan, C.-M. Lei, Synthesis and characterization of sol-gel derived gallium-doped zinc oxide thin films, *Journal of Alloys and Compounds*, 512 (2012) 216-222.
- [42] C.-C. Ting, W.-L. Cheng, G.-C. Lin, Structural and opto-electrical properties of the tin-doped indium oxide thin films fabricated by the wet chemical method with different indium starting materials, *Thin Solid Films*, 519 (2011) 4286-4292.
- [43] L. Kong, J. Ma, C. Luan, Z. Zhu, Q. Yu, Domain structure and optical property of epitaxial indium oxide film deposited on $\text{MgO}(100)$ substrate, *Surface Science*, 605 (2011) 977-981.
- [44] A. Caricato, M. Cesaria, A. Luches, M. Martino, G. Maruccio, D. Valerini, M. Catalano, A. Cola, M. Manera, M. Lomascolo, A. Taurino, R. Rella, Electrical and optical properties of ITO and ITO/Cr-doped ITO films, *Applied Physics A: Materials Science & Processing*, 101 (2010) 753-758.

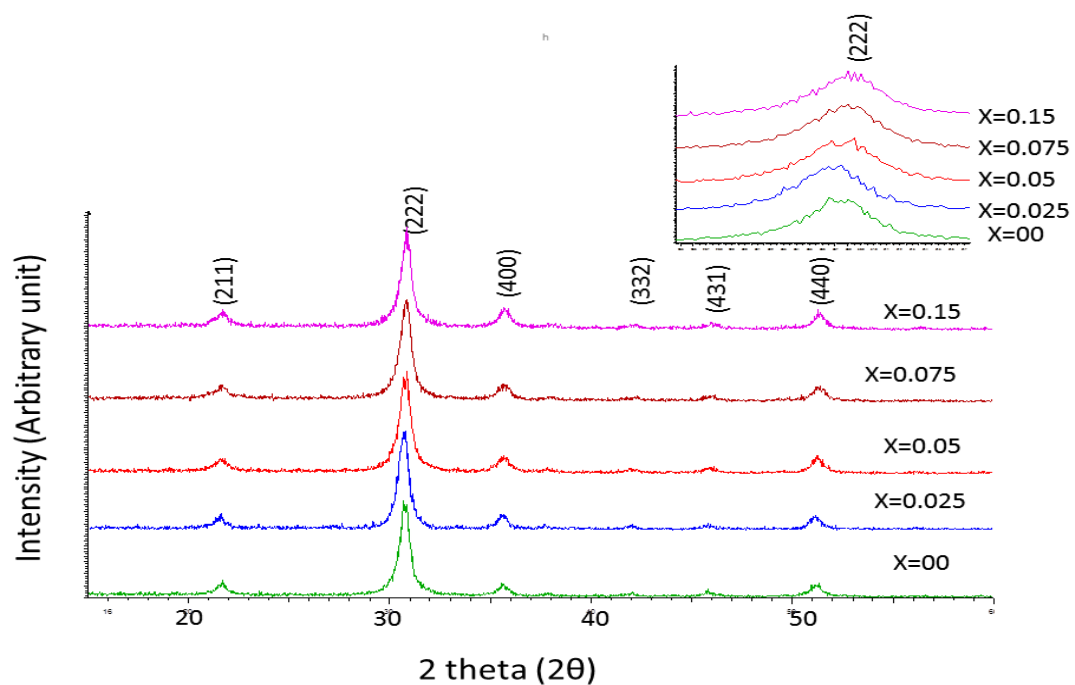


Fig. 1 X-rays diffraction pattern of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ films with ($x=0.0-0.15$)

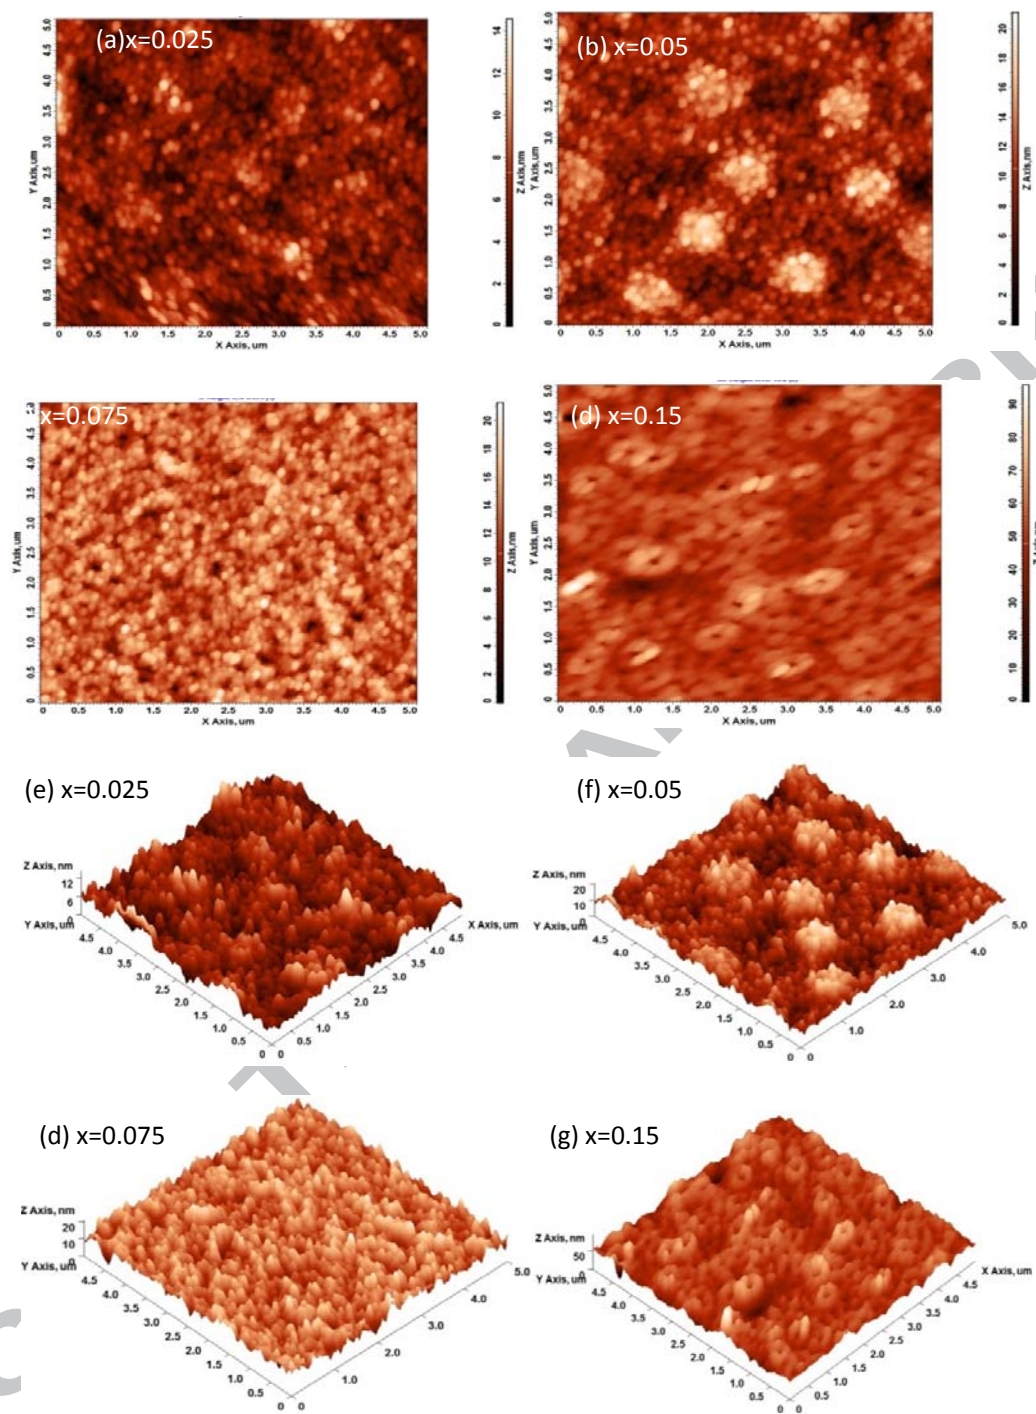


Fig. 2, AFM 2D and 3D images (5 $\mu\text{m} \times 5\mu\text{m}$) of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ thin films with $x = (0.0, 0.025, 0.05, 0.075 \text{ and } 0.15)$. 2D (above) and 3D (below)

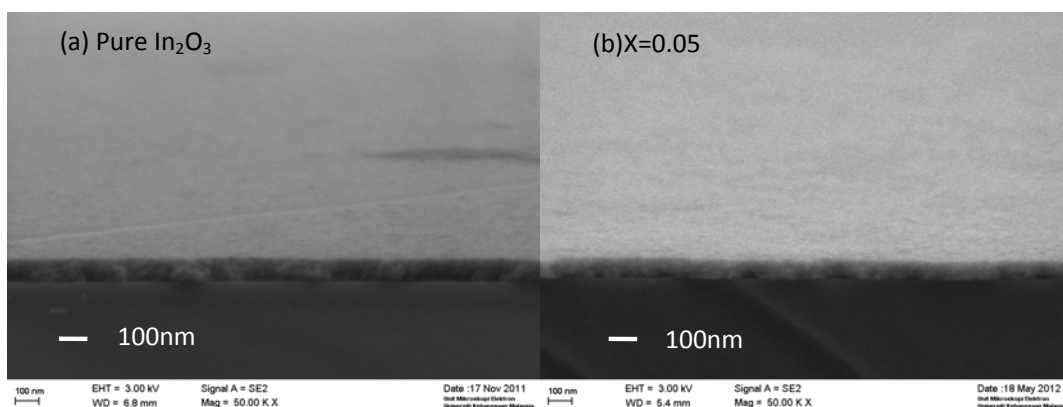


Fig. 3 Cross section of (a) pure In_2O_3 and (b) Cr doped-indium oxide film with $x=0.05$.

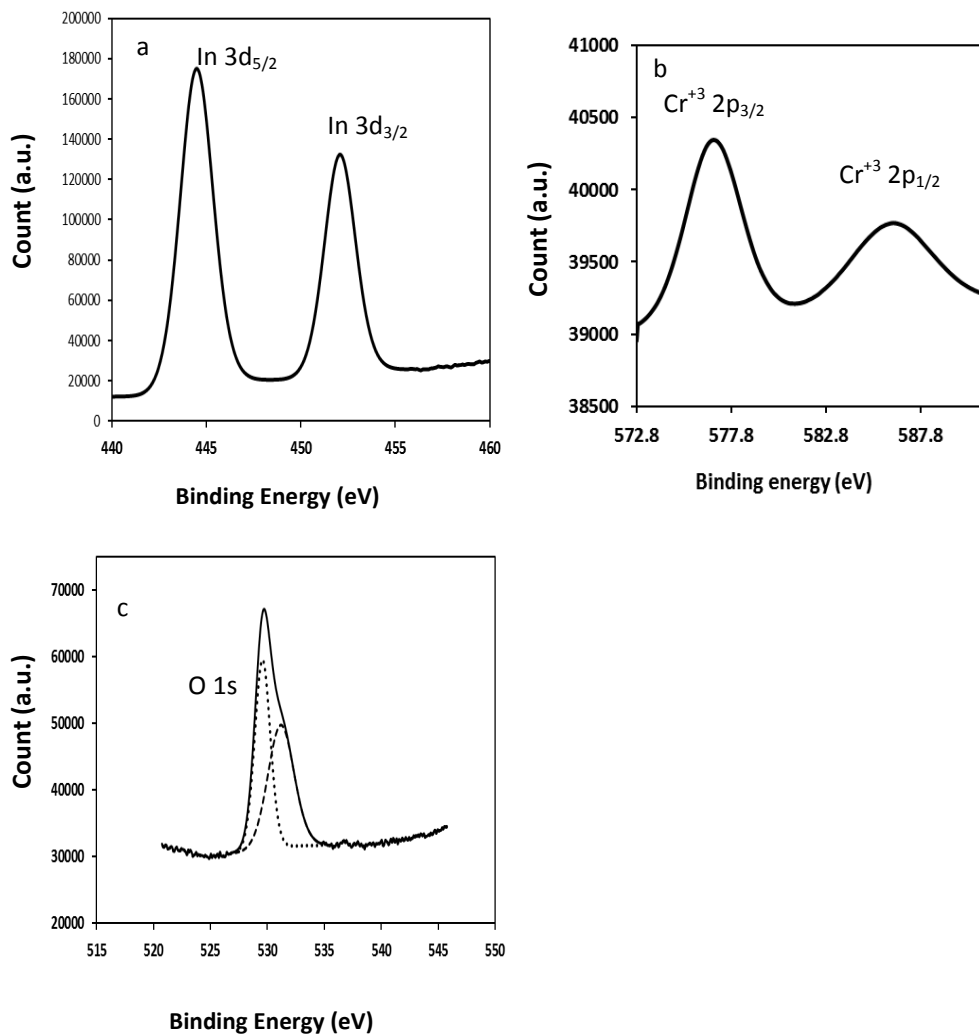


Fig. 4 Typical XPS spectra for the samples: (a) In 3d; (b) Cr 2p at $x=0.05$ of Cr doped In_2O_3 system and (c) O 1s

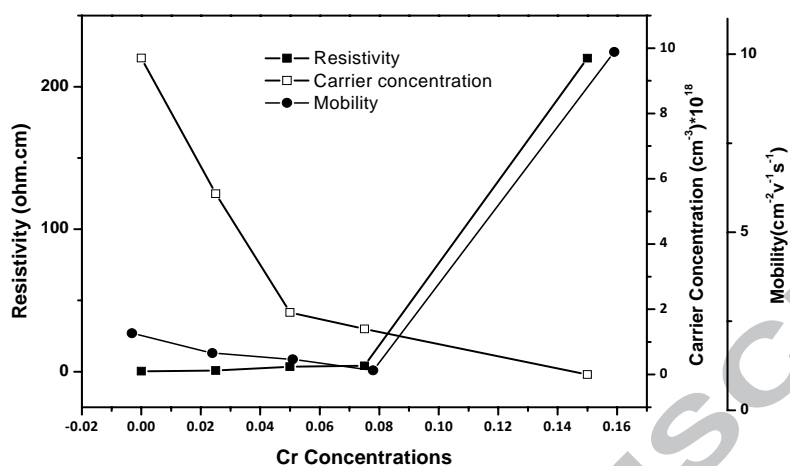


Fig. 5 Resistivity, carrier concentration and mobility against Cr concentration

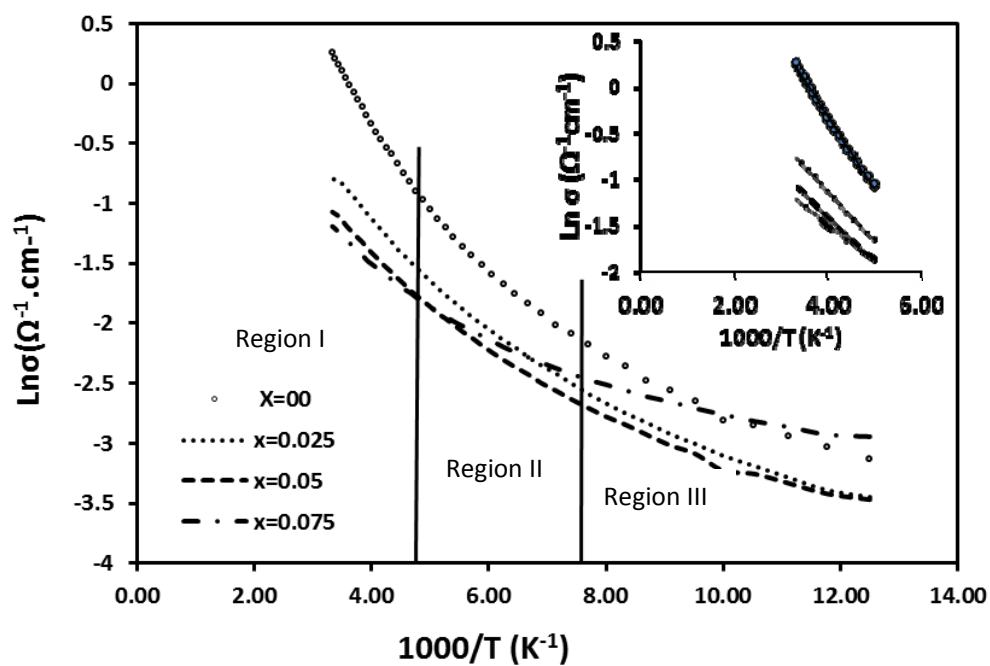


Fig. 6 Arrhenius plot of Cr doped In_2O_3 thin films with $x=0.0-0.075$. The inset is the best fit of Arrhenius plot in the range 300-200 K.

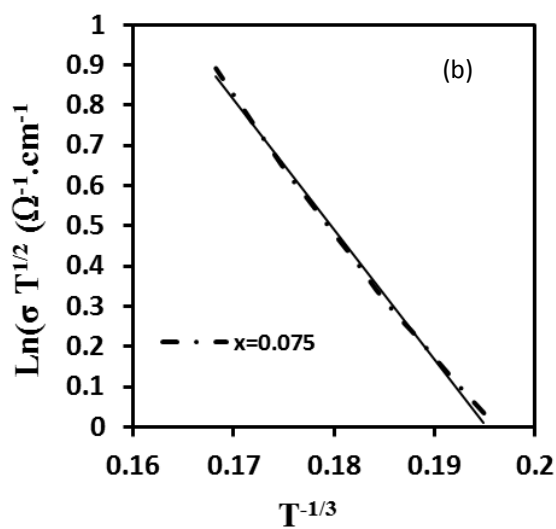
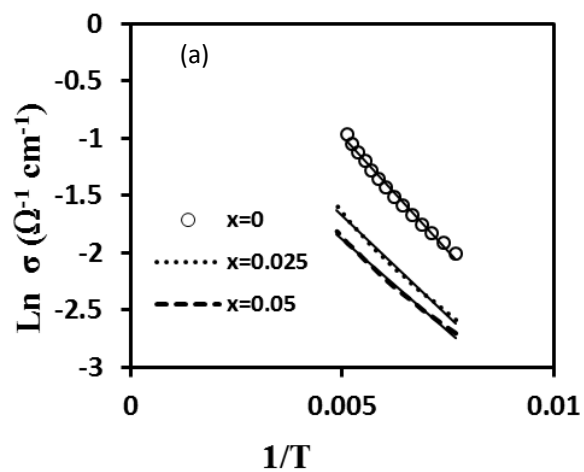


Fig. 7a $\ln \sigma$ against T^{-1} of thin films with $x=0.0-0.05$. **Fig. 7b** $\ln \sigma T^{1/2}$ against $T^{-1/3}$ of thin film with $x=0.075$.

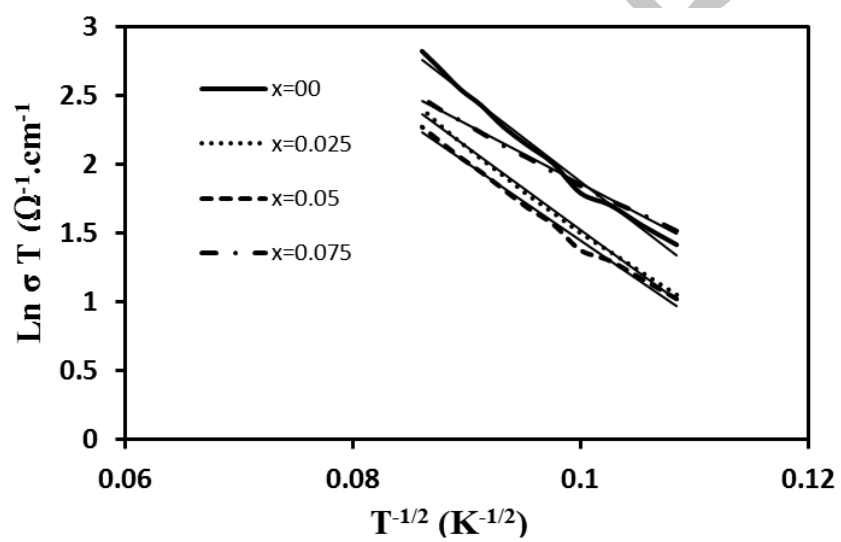


Fig. 8 $\ln \sigma T$ against $T^{-1/2}$ in the range 85-130 K, the solids are best with best fitting.

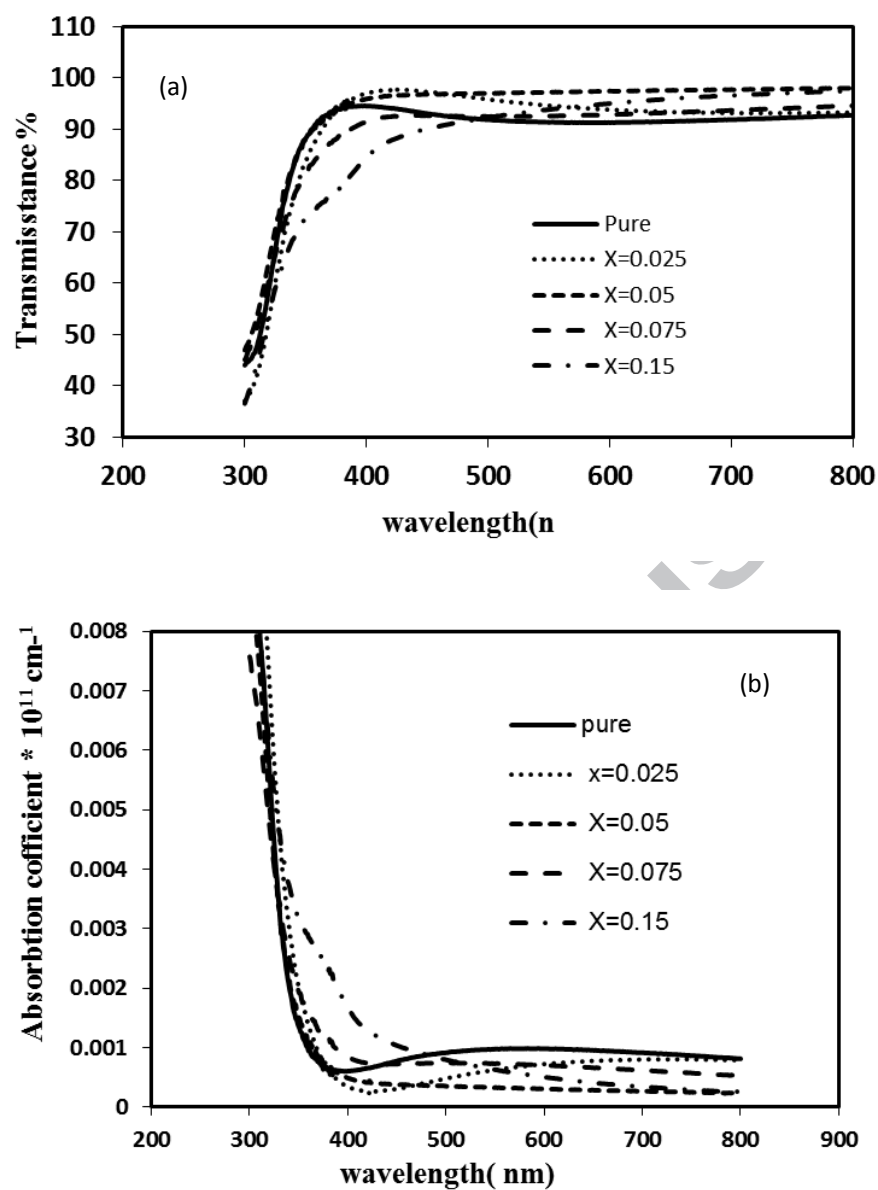


Fig. 9 Optical transmission (a) and (b) Absorption coefficient of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ thin films

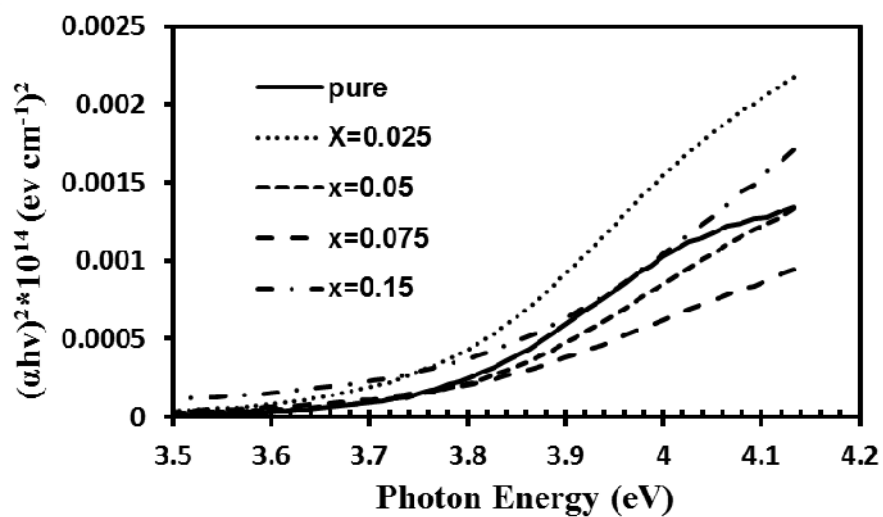


Fig. 10 Plot of $(ahv)^2$ against hv of $\text{In}_{2-x}\text{Cr}_x\text{O}_3$ thin films

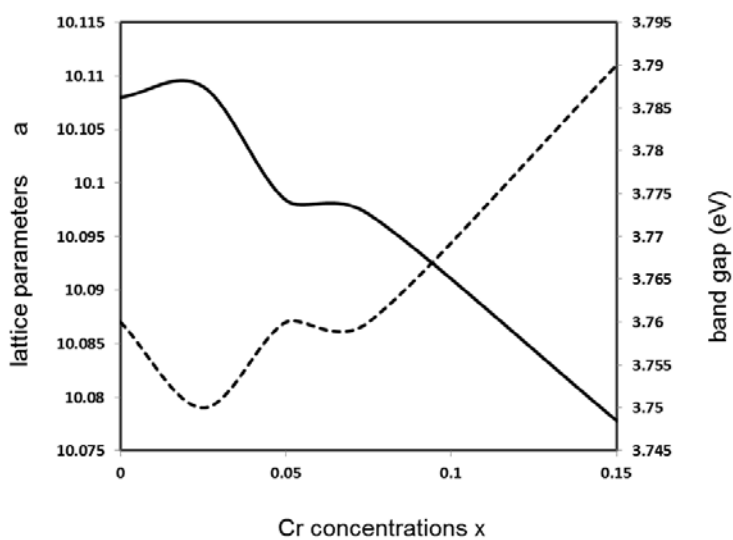


Fig. 11 Lattice parameter a and band gap vs Cr concentrations

Table 1

Lattice parameter, relative reliability of lattice parameter R/R_0 , crystal size, root mean square roughness, film thickness and band gap

Chromium concentrations	Lattice parameter (Å)	R/R_0	Crystal size(nm)	Root mean square roughness(nm)	Thickness (nm)	Band gap(eV)
x=0	10.108	1.2	12.1	2	93.4	3.76
x=0.025	10.109	1.3	13.3	1.7	87.84	3.75
x=0.05	10.0984	1.2	12	3.2	84.8	3.76
x=0.075	10.0971	1.2	12.6	2.6	104.97	3.76
x=0.15	10.0778	1.3	13	7	100.5	3.79

R/R_0 is the relative reliability of lattice parameter of simulation fitting of XRD pattern. For perfect fitting R/R_0 is 1.

Table 2

Thermal activation conduction band E_{a1} , Temperature range, fitting coefficient R^2 , Thermionic emission via grain boundary E_b and Thermal activated hopping E_{a2} of thin films

	Thermal activated conduction band		Thermionic emission via grain boundary			Thermal activated hopping	
	Temperature range/fitting coefficient, R^2	Thermal Activation energy E_{a1} (meV)	L_D (nm)	N_d (cm^{-3})	E_b (meV)	Temperature range/fitting R^2	E_{a2} (meV)
X=0	300-210K/0.9995	66.8	1.15	9.7×10^{18}	77	140-210K/0.9953	38
X=0.025	300-195K/0.9978	43.8	1.52	5.5×10^{18}	53.6	135-190K/0.9968	28
X=0.05	300-215K/0.9991	41	2.6	1.9×10^{18}	51.4	130-210K/0.995	26.3
X=0.075	300-220K/0.9967	35	3	1.4×10^{18}	45.8	—	—

Table 3

Temperature range, fitting coef., Characteristic temperature T_0 Mott, hopping conductivity σ_0 mott, localize hopping ξ mott, density state $N(E_F)$, hopping distance R_{hop} mott, hopping energy Δ_{hop} and R_{hop}/ξ Mott Of thin film with $x=0.075$

Temp. Range /Linear fitting R^2	T_{0Mott} (K)	σ_0 mott ($\Omega^{-1} \cdot cm^{-1}$)	ξ_{Mott} (nm)	$N(E_F)$ ($eVcm^{-3}$)	$R_{hopMott}$ (nm)	$\Delta_{hop}(meV)$	R_{hop}/ξ_{Mott}
135-210K/0.9979	1075037	492.7	1.86	3×10^{19}	6.4	29	3.45

Table 4

	Temp. Range /Linear fitting coefficient, R^2	$T_{0ES}(K)$	σ_{0ES} ($\Omega^{-1} \cdot cm^{-1}$)	$\xi_{ES}(nm)$	R_{hopES} (nm)	$\Delta_{hop}(meV)$	R_{hopES}/ξ_{ES}
x=00	85-135K/0.9903	3844	2981	1.35	2.2	25	1.63
x=0.025	85-130K/0.9945	3226	1339	1.6	2.4	23	1.5
x=0.05	85-130K/0.9929	3080	1096	1.7	2.5	22	1.46
x=0.075	80-135K/0.9943	1722	403	3	3.3	17	1.1

Temperature range, linear fitting coefficient R^2 , characteristic temperature T_{0ES} , hopping conductivity σ_{0ES} , localize hopping ξ_{ES} , distance hopping R_{hopES} , hopping energy Δ_{hop} and R_{hopES}/ξ_{ES}

Table 5

The electrical and transmission properties comparison between current study with AZO, GZO and ITO

TCO Thin film	Resistivity ($\Omega\cdot\text{cm}$),	Carrier concentration cm^{-3}	mobility	Transmission at 800 nm	Ref.
In_2O_3	0.29,	9.8×10^{18}	2.16	93	Current
$\text{In}_{1.95}\text{Cr}_{0.05}\text{O}_3$	3.5	1.9×10^{18}	1.43	98	Current
AZO (Al 2%)	~0.2	9×10^{18}	12	~85	[40]
GZO (Ga 2%)	~200	-	-	~91	[41]
ITO	~0.013-0.006	$\sim (1.4-1.8) \times 10^{20}$	~3.1-6	~92-94	[42]

Note: Samples from ref [40 – 42] were prepared using a sol-gel method and annealed at 500°C

Highlight

- High quality In_2O_3 and Cr-doped In_2O_3 ($\text{In}_{2-x}\text{Cr}_x\text{O}_3$) nanocrystals thin films have been prepared by a simple sol-gel method followed spin coating method.
- The optical transmittance of films increased up to 98 % for $x=0.05$ and decreased for further Cr concentrations.
- The pure In_2O_3 has good conductivity compared with previous reports and decreased with increasing Cr dopant.
- The effect of Cr concentrations on conducting mechanisms of In_2O_3 film has been investigated from 80-300 K using thermal activated conduction band and hopping models.
- Three different conducting mechanisms has been estimated and it was found that all electrical parameters calculated using thermal activation conduction and hopping model change with the Cr concentrations.